

NASA Contract Report 145245

# Research on Graphite Reinforced Glass Matrix Composites


J.F. Bacon, K.M. Prewo

Contract NAS1-14346  
June 1977



National Aeronautics and  
Space Administration

Langley Research Center  
Hampton, Virginia 23665

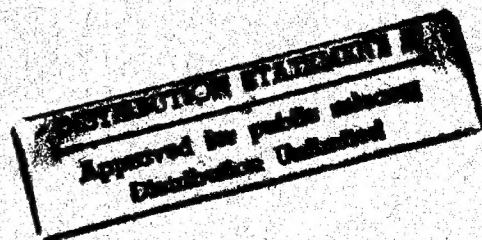

DTIC QUALITY INSPECTED 8

19951206 000

PLASTIC 27473

# DISCLAIMER NOTICE



**THIS DOCUMENT IS BEST  
QUALITY AVAILABLE. THE  
COPY FURNISHED TO DTIC  
CONTAINED A SIGNIFICANT  
NUMBER OF PAGES WHICH DO  
NOT REPRODUCE LEGIBLY.**

\*MSG DIA DROLS PROCESSING - LAST INPUT IGNORED

\*MSG DIA DROLS PROCESSING-LAST INPUT IGNORED

-- 3 OF 3

-- 1 - AD NUMBER: B958766

-- 2 - FIELDS AND GROUPS: 11/4, 11/6, 11/7

-- 5 - CORPORATE AUTHOR: TECHNICAL COOPERATION PROGRAM

MEMBERS OF THE SYMPOSIUM ON CORRELATION

-- 2 OF 2

\*\*\*OTIC DOES NOT HAVE THIS ITEM\*\*\*

-- 1 - AD NUMBER: D112302

-- 5 - CORPORATE AUTHOR: UNITED TECHNOLOGIES RESEARCH CENTER EAST HARTFORD  
CONN

-- 6 - UNCLASSIFIED TITLE: RESEARCH ON GRAPHITE REINFORCED GLASS  
MATRIX COMPOSITES,

-- 9 - DESCRIPTIVE NOTE: ANNUAL REPT.,

-- 10 - PERSONAL AUTHORS: BACON, J. F.; PREWO, K. M.; THOMPSON, E. R.;

-- 11 - REPORT DATE: JUN, 1977

-- 12 - PAGINATION: 109P

-- 14 - REPORT NUMBER: N78-12144, R77-912545-15

-- 15 - CONTRACT NUMBER: NAS1-14346

-- 18 - MONITOR ACRONYM: NASA

-- 19 - MONITOR SERIES: CR-145245

-- 20 - REPORT CLASSIFICATION: UNCLASSIFIED

-- 22 - LIMITATIONS (ALPHA): AVAILABILITY: NATIONAL TECHNICAL

INFORMATION SERVICE, SPRINGFIELD, VA 22161/ORDER NO. N78-12144, (CRO

COPIES FURNISHED BY MICROFILMS)

-- 33 - LIMITATION CODES: 1

-- END

Y FOR NEXT ACCESSION

END

Alt-Z FOR HELP3 ANSI

3 HDX 3

3 LOG CLOSED 3 PRINT OFF 3 PARITY

# UNITED TECHNOLOGIES RESEARCH CENTER



East Hartford, Connecticut 06108

Report R77-912545-15

Research on Graphite Reinforced  
Glass Matrix Composites


Annual Report  
Contract NAS1-14346

REPORTED BY

  
J. F. Bacon

  
K. M. Prew

APPROVED BY

  
E. R. Thompson, Manager  
Materials Sciences

DATE June 1977

NO. OF PAGES 109

COPY NO. \_\_\_\_\_

# ABSTRACT

This report contains the results obtained in the first twelve months of research under NASA Langley Contract NAS1-14346 for the origination of graphite-fiber reinforced glass matrix composites. Included in the report is a summary of the research by other investigators in this area. The method selected to form the composites consisted of pulling the graphite fiber through a slurry containing powdered glass, winding up the graphite fiber and the glass it picks up on a drum, drying, cutting into segments, loading the tape segment into a graphite die, and hot pressing. During the course of the work, composites were made with a variety of graphite fibers in a C.G.W. 7740 (Pyrex) glass matrix. The graphite fibers used included Hercules HMS, Hercules HTS, Thornel 300S, and Celanese DG-102 and, of these, the Hercules HMS and Celanese DG-102 graphite fibers in C.G.W. 7740 gave the most interesting but widely different results.

Hercules HMS fiber in C.G.W. 7740 glass (Pyrex) showed an average four-point flexural strength of 848 MPa or 127,300 psi. As the test temperature was raised from room temperature to 560°C in argon or vacuum, the strength was higher by 50%. However, in air similar tests at 560°C gave a severe loss in strength. These composites also have good thermal cycle properties in argon or vacuum, greatly increased toughness compared to glass, and no loss in strength in a 100 cycle fatigue test.

Celanese DG-102 fiber in C.G.W. 7740 glass (Pyrex) had a much lower flexural strength but did not suffer any loss in this strength when samples were heated to 560°C in air for 4 hrs.

|                               |                                     |
|-------------------------------|-------------------------------------|
| Accession For                 |                                     |
| NTIS GRA&I                    | <input checked="" type="checkbox"/> |
| DTIC TAB                      | <input type="checkbox"/>            |
| Unannounced                   | <input type="checkbox"/>            |
| Justification                 |                                     |
| <i>printed and released</i>   |                                     |
| By <i>DTIC RI memo 3-7-95</i> |                                     |
| Distribution/                 |                                     |
| Availability Codes            |                                     |
| Plot                          | Avail and/or Special                |
| <i>A-1</i>                    |                                     |

Report R77-912545-15

Research Services on Graphite Reinforced  
Glass Matrix Composites

TABLE OF CONTENTS

|  |     |
|--|-----|
| I. SUMMARY . . . . .   | 1   |
| II. BACKGROUND . . . . .   | 2   |
| A. Review of the Literature . . . . .                                    | 2   |
| B. Background Research on Glass Matrix Composites . . . . .              | 4   |
| III. MATERIALS USED DURING FIRST YEAR'S EFFORT . . . . .                 | 7   |
| A. Graphite Fiber . . . . .  | 7   |
| B. Glasses . . . . .   | 7   |
| IV. PROCESSING . . . . .   | 14  |
| A. Description of Fabrication Process . . . . .                          | 14  |
| B. Effect of Processing Variables and Material Constituents . . . . .    | 16  |
| V. PROPERTIES OF TWO SELECTED SYSTEMS . . . . .                          | 55  |
| A. Composites of Hercules HMS Graphite Fiber and 7740 Glass . . . . .    | 55  |
| B. Composites of Celanese DG-102 Graphite Fiber and Pyrex Glass. . . . . | 93  |
| VI. CONCLUSIONS AND RECOMMENDATIONS . . . . .                            | 106 |
| REFERENCES . . . . .   | 108 |

## LIST OF TABLES

| <u>No.</u> |  | <u>Page</u> |
|------------|--|-------------|
| I          | Early UTRC Experiments   | 5           |
| II         | Carbon Fibers and Their Characteristic Properties  | 8           |
| III        | Carbon Fiber Obtained for this Study   | 10          |
| IV         | Characteristic Properties of Glasses Used  | 11          |
| V          | Graphite Fiber Reinforced Glass Matrix Composites Prepared<br>and Evaluated  | 20          |
| VI         | Effect of Amount of Glass in Slurry on Achieved Flexural<br>Strength of Graphite Fiber Reinforced Glass Composite                    | 23          |
| VII        | Effect of Hot Pressing Pressure on Achieved Flexural<br>Strength of Graphite Fiber Reinforced Glass Composite                        | 24          |
| VIII       | Effect of Temperature on Achieved Flexural Strength of<br>Graphite Fiber-Glass Composite   | 25          |
| IX         | Fiber Content and Composite Strength for Several Celanese<br>Graphite Fibers in Corning Glass Works 7740 Glass Matrix<br>Composites  | 31          |
| X          | Choice of Graphite Fiber and Its Effect on Ultimate Three-<br>Point Flexural Strength of Graphite Fiber-Glass Matrix<br>Composite    | 37          |
| XI         | Elevated Temperature Exposure of Thornel 300S Graphite<br>Fiber Reinforced 7740  | 45          |
| XII        | Three-Point Bend Strength of Hercules HTS Fiber in C.G.W. 7740<br>Glass Measured at Elevated Temperatures                            | 46          |
| XIII       | Preliminary Evidence That Choice of Glass Effects the Three-<br>Point Flexural Strength of Graphite Fiber-Glass Matrix<br>Composites | 48          |
| XIV        | Three Point Flexural Strength Values for HTS Graphite in<br>Pyrex Glass Matrix Evaluated at Three L/D Ratios                         | 49          |
| XV         | Comparison of 3-Point Bend and 4-Point Bend Test Data for<br>Several Graphite Fiber-Glass Composites                                 | 50          |
| XVI        | Possible Reactions Between $\text{SiO}_2$ and Carbon at Temperatures<br>Above 1400°C   | 51          |
| XVII       | Loss in Weight of Celanese DG-102 Graphite Fiber Vycor Glass<br>Composites as a Function of Temperature                              | 53          |
| XVIII      | Flexural Strength of HMS Reinforced 7740   | 59          |
| XIX        | Flexural Properties of HMS Reinforced 7740   | 62          |
| XX         | Elevated Temperature Exposure of Hercules HMS-10K Graphite<br>Reinforced 7740  | 66          |
| XXI        | Room Temperature Elastic Modulus Comparison  | 67          |
| XXII       | Hercules HMS-10K Reinforced 7740 LB 139  | 69          |
| XXIII      | Fracture Toughness Specimen Dimensions   | 81          |

## LIST OF TABLES (Cont'd)

| <u>No.</u> |  | <u>Page</u> |
|------------|--|-------------|
| XXIV       | Fracture Toughness Comparison at 22°C  | 86          |
| XXV        | Thermal Cycling HMS Reinforced 7740  | 87          |
| XXVI       | Four Point Flexural Fatigue  | 88          |
| XXVII      | Determination of Graphite Fiber Content for Several Graphite<br>Fiber-Pyrex Glass Matrix Samples                     | 92          |
| XXVIII     | Effect of Atmosphere on Strength of Celanese DG-102 Graphite<br>Fiber Reinforced Pyrex Glass Composites              | 96          |
| XXIX       | Flexural Strength of Typical Specimens of Celanese Graphite<br>Fiber DG-102 Reinforced Pyrex Glass Matrix Composites | 98          |
| XXX        | Flexural Strength of Celanese Graphite Fiber DG-102 Reinforced<br>Pyrex Glass Composite at Elevated Temperatures     | 100         |



## LIST OF ILLUSTRATIONS

| <u>Fig. No.</u> |   | <u>Page</u> |
|-----------------|---|-------------|
| 1               | Typical Fibers as Seen in Scanning Electron Micrographs   | 9           |
| 2               | Viscosity-Temperature Curves  | 12          |
| 3               | Scanning Electron Micrographs of Glass Powders  | 13          |
| 4               | Slurry Method of Coating Graphite Fiber   | 15          |
| 5               | Micrographs of Typical UTRC Carbon Fiber Reinforced Glass Matrix Composites   | 17          |
| 6               | Fracture Strength of Thornel 75 - Glass Matrix Composite and Micrographs of Material Near the Fracture Surface            | 18          |
| 7               | Micrographs After Fracture of Three Typical Samples   | 19          |
| 8               | Optical Micrographs of Four Unfractured Samples   | 26          |
| 9               | Tape Map of Unfractured Sample LB94 Celanese DG-102 Fiber, 7740 Glass Matrix, Hot Pressed at 1025°C                       | 27          |
| 10              | Tape-Map of Unfractured Sample LB95 Celanese DG-102 Fiber, 7740 Glass Matrix, Hot Pressed at 1050°C                       | 28          |
| 11              | Tape-Map of Unfractured Sample LB96 Celanese DG-102 Fiber, 7740 Glass Matrix, Hot Pressed at 1075°C                       | 29          |
| 12              | Tape-Map of Unfractured Sample LB97 Celanese DG-102 Fiber, 7740 Glass Matrix, Hot Pressed at 1100°C                       | 30          |
| 13              | Scanning Electron Micrograph of Fracture Surface of LB95  | 33          |
| 14              | Scanning Electron Micrograph of Fracture Surface of LB96  | 34          |
| 15              | Scanning Electron Micrograph of Fractured Surface of LB97-L2  | 35          |
| 16              | Distribution of Strength of Three Graphite Fiber Glass Matrix Composites  | 36          |
| 17              | Thornel 300S Graphite Fiber in Pyrex Glass Matrix Tape-Map of Cross Section   | 40          |
| 18              | Optical Micrographs of Thornel 300 Fiber in C.G.W. 7740 Glass Matrix  | 41          |
| 19              | Thornel 300S Graphite Fiber-Pyrex Glass Matrix Cross-Section Perpendicular to Fiber Direction                             | 42          |
| 20              | Thornel 300S Graphite Fiber Pyrex Glass Matrix Cross-Section Parallel to Fiber Direction                                  | 43          |
| 21              | Tape-Map of Unfractured Sample LB 81 Thornel 300 Fiber C.G.W. 7740 Glass Matrix   | 44          |
| 22              | Flexural Strength of Hercules HTS Graphite Fiber Reinforced 7740 Glass Matrix Composite as a Function of Test Temperature | 47          |
| 23              | New Centorr Hot Press at UTRC   | 54          |
| 24              | Optical Tape Map LB135F Hercules HMS Graphite in Pyrex  | 56          |
| 25              | Typical Micrographs LB135F Hercules HMS Graphite Fiber in Pyrex   | 57          |

## LIST OF ILLUSTRATIONS (Cont'd)

| <u>Fig. No.</u> |  | <u>Page</u> |
|-----------------|--|-------------|
| 26              | Hercules HMS-10K Reinforced 7740   | 60          |
| 27              | Three Point Bend Strength of Specimens Tested at 22°C  | 61          |
| 28              | Load-Deflection Traces for the 3-Pt Bend Tests on Hercules<br>HMS-10K Reinforced 7740                          | 63          |
| 29              | Load-Strain Traces for the 4 Pt Bend Tests on Strain<br>Gauged Hercules HMS-10K Reinforced 7740                | 64          |
| 30              | Flexural Strength of Hercules HMS-10K Fiber Reinforced 7740<br>Glass as a Function of Test Temperature         | 68          |
| 31              | HMS-7740 Three Point Flexural Test Specimens   | 71          |
| 32              | Hercules HMS-10K Reinforced 7740   | 72          |
| 33              | Hercules HMS-10K Reinforced 7740   | 73          |
| 34              | Flexural Strength of Hercules HMS-10K Fiber Reinforced<br>7740 Thermoplastic as a Function of Test Temperature | 74          |
| 35              | Flexural Strength Comparison   | 75          |
| 36              | Specific Flexural Strength Comparison  | 77          |
| 37              | Flexural Strength Comparison   | 78          |
| 38              | Specific Flexural Strength Comparison  | 79          |
| 39              | Fracture Toughness Specimen  | 80          |
| 40              | Load vs Deflection Trace for Specimen LB-140-2 Tested at<br>22°C   | 83          |
| 41              | Instrumented Impact Trace  | 84          |
| 42              | Instrumented Impact Traces   | 85          |
| 43              | Temperature Cycle  | 87          |
| 44              | Flexural Strength of HMS Graphite-Pyrex Glass Composite<br>after Thermal Cycling                               | 89          |
| 45              | Effect of Fatigue on Bend Strength of HMS Graphite Fiber in<br>Pyrex Glass Matrix Composite                    | 91          |
| 46              | Tape-Map of Celanese DG-102 Fiber in C.G.W. 7740 Glass Matrix-<br>Unfractured Sample                           | 94          |
| 47              | Scanning Electron Micrographs Fracture Surface Celanese<br>DG-102 Fiber in C.G.W. 7740 Glass Matrix            | 95          |
| 48              | Flexural Strength of Celanese Fiber Reinforced 7740 Glass<br>as a Function of Test Temperature                 | 99          |
| 49              | Celanese Fiber Reinforced 7740   | 101         |
| 50              | Celanese Fiber Reinforced 7740   | 102         |
| 51              | Celanese Fiber Reinforced 7740   | 103         |
| 52              | 3 Point Bend Specimen LB98-CC  | 104         |

## I. SUMMARY

Fiber reinforced composites are widely accepted as structural materials because of their desirable attributes of high strength, high modulus and low density. However, even the best of the organic matrix composites reinforced by carbon, boron or glass fiber is limited in use to temperatures below 300°C. Substitution of a metallic matrix for the organic matrix, such as composites of boron or graphite fiber reinforced aluminum, extends the use temperature range only slightly. By contrast, the graphite fiber reinforced borosilicate glass matrix composite which is the subject of this report has exhibited excellent mechanical properties up to 650°C.

Of the two types of graphite fiber reinforced borosilicate-glass composites whose characteristics are given in detail in this report, the Hercules HMS graphite reinforced composite provides the highest level of structural performance. This system has exhibited a flexural strength of up to 977 MPa (142,000 psi) at room temperature. This high level of strength is maintained up to moderate temperatures becoming greater than 1292 MPa at 600°C, a value equal to the strength of HMS graphite fiber reinforced epoxy specimens tested at room temperature. Above 650°C, bend specimens of the HMS graphite fiber reinforced borosilicate glass do not fracture, but instead deform extensively. Specimens of this composite, when tested for fracture toughness, gave results which compare favorably with aluminum alloys and graphite fiber reinforced epoxy composites. The HMS fiber-reinforced glass composite also displays excellent strength retention after exposure to 100 fatigue or thermal cycles, but it suffers degradation of strength when heated to 560°C in air for 4 hrs. Overcoming this strength degradation will be a major task of the second year's research on these types of composites.

The second type of graphite fiber-borosilicate glass composite discussed in detail is reinforced with Celanese DG-102 graphite fiber. This composite has a flexural strength of 340 MPa (49,600 psi) at room temperature and again it increases in strength by almost 40% as the test temperature is increased to 650°C. The relatively low value of strength for this composite is maintained even after 4 hrs exposure to air at 560°C.

The contract monitor for this program is Dennis Dicus and his helpful comments are greatly appreciated.

## II. BACKGROUND

At the inception of this program the sales of high performance fiber reinforced composite materials exceeded a million pounds yearly. In general, most of these composites were organic polymer (epoxy resins, polyimides, polycarbonates, and similar materials) matrices reinforced with a great variety of fibers including Kevlar\*, carbon, graphite, fused silica, glass, and boron. In general, almost all of these composites were limited to use temperatures not exceeding 300°C.

At the start of this contract, there were no reinforced glass matrix composites commercially available except the age-old wire reinforced glass used for improving the burglar resistance of homes and stores and the AVCO developed tungsten mesh reinforced fused silica intercontinental ballistic missile nose cones. Yet if one conceives of glass as just a high-temperature thermoplastic, the substitution of a glassy matrix for the low temperature polymers in composite materials seems a natural way to proceed. This concept, however, had attracted sparse attention in the past.

### A. Review of the Literature

Siefert (Ref. 1) has patented two glass compositions particularly suitable for producing fiber (stainless steel, boron, graphite) reinforced glass composites by pulling the fibers through a molten glass bath and then through a constricting orifice. He states that the resulting composites exhibit high stiffness, a flexural strength higher than aluminum, high impact resistance (being much more impact resistant than monolithic glass), and a capability to withstand temperatures of 538°C for 100 hrs without loss of properties.

Siefert (Ref. 2) extended his work to boron, tungsten and molybdenum reinforced glass composite formed by fusing the glass coated metal fibers together by drawing the fiber through a glass tube and softening a narrow band of the glass tube around the fiber. His boron fiber glass reinforced matrix had flexural properties of 1103 MPa (160,000 psi), a compressive strength of 2069 MPa (300,000 psi), a modulus of 158 GPa ( $23 \times 10^6$  psi) and retained its properties when loaded to 50% ultimate tensile strength and kept in water for 5.7 days as well as after being held at 1000°F for 100 hrs. Finally, samples of his composites when notched and subjected to an impact test were found to have high impact strength and to show no decrease in strength over unnotched samples.

\*Registered trademark, DuPont Corp., Wilmington, Delaware

Sambell, et al (Ref. 3) fabricated carbon fiber composites using chopped fibers and magnesia, alumina, soda-lime glass, borosilicate glass, and a lithia aluminosilicate glass-ceramic as matrices. He found that thermal stresses resulting from a mismatch in thermal expansion coefficients ruled out any success with the magnesia, alumina, and soda-lime glass matrices but not with the Pyrex or low expansion glass ceramics. For these he found that the addition of carbon fibers produced substantial increases in the work of fracture and that all composites had lower strengths than the matrix materials if randomly oriented fibers were used (but that the borosilicate glass matrix with partially aligned fibers was stronger and had improved thermal shock characteristics).

Sambell, et al (Ref. 4) continued their investigations using continuous graphite fibers in the same matrix materials, i.e., alumina, magnesia, soda-lime glass, borosilicate glass and a lithia-aluminosilicate glass ceramic. They found that the reinforced glass had a strength sevenfold greater than the unreinforced glass and showed a tenfold increase in work of fracture.

Phillips (Ref. 5) investigated in detail the tenfold increase in work of fracture shown by the 40 vol % carbon fiber reinforced Pyrex glass and attempted to explain the results in terms of the initial rate of release of strain energy during fiber fracture and the interfacial strengths of the fibers during pull out. In Ref. 6, Phillips, et al discussed in detail the mechanical properties of the carbon fiber reinforced Pyrex glass in terms of volume fraction of fiber, the orientation of the fibers, fiber damage during fabrication, matrix porosity, matrix critical strain, interface properties and the mode of failure in bend tests. They found from preliminary stress cycling experiments, at stresses above that at which the matrix cracks are formed, that crack propagation is inhibited by the fibers. They also found that to a first approximation, Young's modulus for the composite is that predicted by the rule of mixtures.

Levitt (Ref. 7) developed graphite fiber reinforced composites where the matrix composition was  $\text{Li}_2\text{O} \cdot \text{Al}_2\text{O}_3 \cdot n\text{SiO}_2$  with  $n = 3, 4$  and  $8$ . He used a drum winding apparatus to produce graphite fiber/ceramic matrix tapes which were then hot pressed to their final dimensions. He obtained fivefold increases in modulus of rupture with no fall off after repeated thermal cycling to  $1200^\circ\text{C}$  for all three compositions reinforced by continuous graphite tows. His composites were generally characterized by low porosity, intimate fiber-matrix contact and an uncracked matrix, which was the result of a suitable thermal expansion match between fiber and matrix and the occurrence of a strong fiber-matrix bond. Izod impact energies of  $4.2$  to  $6.3 \text{ kJ/m}^2$  ( $20$  to  $30 \text{ ft/lb/in.}^2$ ) for the notched specimens and  $15.75 \text{ kJ/m}^2$  ( $75 \text{ ft-lbs/in.}^2$ ) for the unnotched specimens were obtained at room temperature.

Phillips (Ref. 8) has investigated the interfacial bonding and the toughness of four different carbon fiber reinforced glass and glass-ceramic composites and finds that he can explain his results on the basis of the difference in thermal shrinkage between the glass-ceramic and Pyrex matrices resulting in differences in fiber-matrix interfacial shear bond strength and consequent differences in pull out.

Lange (Ref. 9) found that a significant increase in fracture energy was observed (up to 5 times the fracture energy of the glass without second-phase dispersion) when 40 vol % of 44 micron average size alumina particles were dispersed uniformly in a sodium borosilicate glass and that the flexural strength was almost doubled for the same dispersion.

Hasselman and Fulrath (Ref. 10) developed a fracture theory for a composite system based on a dispersion of alumina particles in a continuous glass matrix and then proceeded to verify it experimentally. They found that for 47.5 vol % of 15 micron (average size) alumina particles, the strength (as determined by four-point bend tests) of the sodium borosilicate glass was increased from 101 MPa (14,700 psi  $\pm$  12.7%) to 162 MPa (23,600 psi  $\pm$  3.7%) in accordance with the predictions of their theory.

#### B. Background Research on Glass Matrix Composites

Because of the many favorable conclusions stated in the references just cited, UTRC, in the late fall of 1975, turned its attention to research on new high temperature fiber reinforced glass composites. This research was intended to supplant the widely used epoxy resin-glass, boron, or carbon fiber composites which are, as mentioned, limited in service to a few hundred degrees Fahrenheit, by the much higher temperature composites consisting of glass matrices reinforced by graphite, alumina, silicon carbide, or boron nitride fibers. These glass matrix composites should be suitable for use at intermediate to elevated temperatures (700-1100°C) where aluminum composites would fail by melting and nickel matrix composites by lack of thermochemical stability.

This initial research at UTRC was largely in the area of graphite fiber reinforced glass matrices. However, it also included experiments with alumina fiber, silicon carbide fiber, boron fiber, and Borsic (silicon carbide coated boron) fibers. As shown in Table I, even these early experiments gave promising results.

The first five samples in the table were hot pressed at 13.8 MPa (2000 psi) and 15 min dwell time. The best of these data indicated that the addition of carbon fiber even at this early date was capable of giving an approximate tenfold increase in strength compared to the unreinforced glass. In addition,

Table I

## Early UTRC Experiments

Mechanical Properties of Hot Pressed Samples  
(measured at room temperature except as noted)

| <u>Material</u>                                | <u>Temp. of Hot<br/>Pressing (°C)</u> | <u>% Fiber<br/>in Sample</u> | <u>3-Point Flexural<br/>Strength</u> |                |
|--|---------------------------------------|------------------------------|--------------------------------------|----------------|
|  |                                       |                              | <u>MPa</u>                           | <u>(psi)</u>   |
| 7740 Glass - Thornel 300                       | 1050                                  | 34.4                         | 300                                  | 43,500         |
| 7740 Glass - Thornel 300                       | 1100                                  | 40.5                         | 376                                  | 54,500         |
| 7740 Glass - Thornel 300                       | 1100                                  |                              | 364                                  | 52,750         |
| 7740 Glass - Thornel 300                       | 1150                                  | 40.5                         | 400                                  | 58,050         |
| 7740 Glass - Thornel 300                       | 1225                                  | 40.5                         | 305                                  | 44,300         |
| 7740 Glass - FP Al <sub>2</sub> O <sub>3</sub> | 1100                                  |                              | 138                                  | 20,000         |
| 1723 Glass - FP Al <sub>2</sub> O <sub>3</sub> | 1100                                  | 27                           | 232                                  | 33,600         |
| 7740 Glass - HM (u)                            | 880                                   |                              | 278                                  | 40,250         |
| 7740 Glass - 5.6B                              | 700                                   | 19                           | 383                                  | 55,500         |
| 7740 Glass - 5.6B                              | 700                                   | 30                           | 572                                  | 83,000         |
| 7740 Glass - 5.6B                              | 700                                   | 50                           | 603                                  | 87,400         |
| 7740 Glass - 5.6B                              | 700                                   | 34                           | 532                                  | 77,100         |
| 7740 Glass - 5.6B                              | 700                                   | 34                           | 590                                  | 85,600 @ 300°C |
| 7740 Glass - 5.6B                              | 700                                   | 34                           | 584                                  | 84,700 @ 600°C |
| 7740 Glass - Borsic                            | 700                                   | 30                           | 353                                  | 51,150         |
| 7740 Glass - 8.0B                              | 700                                   | 36                           | 587                                  | 85,100         |
| 7740 Glass - 5.6 SiC                           | 700                                   | 36                           | 531                                  | 77,000         |
| 7913 Glass - Thornel 300                       | 1550                                  | 37                           | 186                                  | 27,000         |
| 7913 Glass - Thornel 300                       | 1600                                  | 37                           | 145                                  | 21,000         |
| 7913 Glass - Thornel 300                       | 1650                                  | 37                           | 108                                  | 15,700         |

as the data for the boron fibers in Pyrex glass indicate, these composites can be expected to maintain their structural integrity as well as at least their original flexural strength up to the softening point of the particular glass used as the matrix, in this case, 600°C.



## III. MATERIALS USED DURING FIRST YEAR'S EFFORT

## A. Graphite Fiber

The types of fibers readily available in this country for a research program on the generation of new types of graphite fiber reinforced glass matrix composites are shown in Table II. It will be noted that they vary widely in several important characteristics such as the number of fibers in each, the strength and modulus of the fiber, the precursor used to make the fiber, and the price. It is perhaps not so obvious that the use of each fiber presents a distinct surface chemistry problem, but if one considers the finish on the fiber surface and the chemical elements found on the fiber surface as shown in Table II the problem is evident. This is particularly true if one examines the distinctive shape of each carbon fiber as shown in Fig. 1. It is apparent, therefore, that any given glass matrix reinforced with a given graphite fiber will show its own characteristic behavior.

To broaden the investigation as much as practicable, UTRC purchased some of each carbon fiber shown in Table III. In examining this table, it is obvious that the so-called low price fibers derived from a pitch base are far from low-priced at this time and possess only a mediocre strength. What is not obvious, however, is that one of the fibers highly considered for this program, namely Thornel 75 WYL 30 1/2, is no longer available. The Celanese DG-102 fiber has proven to be a suitable substitute in modulus although not in strength and the Hercules HMS fiber is a suitable substitute in strength but not in modulus.

## B. Glasses

The types of glasses which were considered for use on the UTRC/NASA-Langley program are shown in Table IV. Just as the graphite fibers show individual characteristics, the glasses also vary widely in their nature possessing different coefficients of linear expansion, different chemical compositions, varied environmental stability, and, of course, different temperature working ranges. Although all the glasses in the table have relatively low thermal expansion coefficients, only the titanium silicate glass has an expansion coefficient as low as that of the graphite fibers.

Just how different the working characteristics of these glasses are is shown in Fig. 2. It is apparent, therefore, that any resultant graphite fiber-glass matrix composites will have their own fabrication conditions. The glasses as they actually arrive at UTRC are shown in the scanning electron micrograph of Fig. 3. Although each glass is purchased solely on the basis that ninety percent must pass through a 36.0 mesh screen; actually all glasses contain numerous fine particles under one micron in size, and it is believed that these fine particles contribute greatly to the fabrication process to be described in the next section.

Table II  
Carbon Fibers and Their Characteristic Properties

| Type of Fiber               | No. of Fibers in Tow | Finish Used | Precursor Size of Fiber (microns) | Modulus GPa | Modulus psi x 10 <sup>6</sup> | Strength MPa | Strength ksi | Density gms/cm <sup>3</sup> | Coeff. Linear Expansion cm/cm°C (axial) | Cost per Pound \$ | Result of Spectroscopic Examination           |
|-----------------------------|----------------------|-------------|-----------------------------------|-------------|-------------------------------|--------------|--------------|-----------------------------|---|-------------------|---|
| Hercules HM/PVA             | 1,000                | PVA 0.86    | PAN                               | 385         | 55.9                          | 2427         | 352          | 1.850                       |   | 300               |   |
| Hercules HMS                | 10,000               | Oxidized    | PAN 7.3                           | 351         | 50.9                          | 2703         | 392          | 1.808                       | -5.7 x 10 <sup>-7</sup>                 | 90                | High Na, high Si, Cr                          |
| Hercules HTS                | 10,000               | Oxidized    | PAN 7.6                           | 256         | 37.2                          | 2830         | 410          | 1.658                       | -3.8 x 10 <sup>-7</sup>                 | 75                | High Na, very high K                          |
| Celanese DG-102             | 384                  | Oxidized    | PAN 8                             | 531         | 77.0                          | 1724         | 250          | 1.96                        |   | 250               | Very low Na, highest Fe, Si, Ti, Zr           |
| Thornel 300 Grade WYP30 1/0 | 3,000                | UC 309      | PAN 6.9                           | 234         | 34.0                          | 2482         | 360          | 1.76                        |   | 40                | Very high Na, high Cu, high Sn, Zn            |
| Thornel 300 Grade WYP90 1/0 | 1,000                | UC 309      | PAN 8.4                           | 228         | 33.0                          | 2655         | 385          | 1.75                        |   | 32                | Moderate Na, high Mg, Sn, P                   |
| Thornel 75 Grade WYL160 1/2 | 720                  | PVA         | Rayon 6.0                         | 538         | 78.0                          | 2620         | 380          | 1.80                        |   | 385               | Intermediate Na, very high P, high Ca, Ta, Zn |
| Thornel 50 Grade WYGL30 1/2 | 720                  | PVA         | Rayon 6.6                         | 393         | 57.0                          | 2172         | 315          | 1.66                        |   | 320               |   |

TYPICAL FIBERS AS SEEN IN SCANNING ELECTRON MICROGRAPHS



HERCULES HMS

2  $\mu$



THORNEL 300 GRADE WYP 30

2  $\mu$




THORNEL 75 GRADE WYL 160

2  $\mu$



HERCULES HTS

2  $\mu$

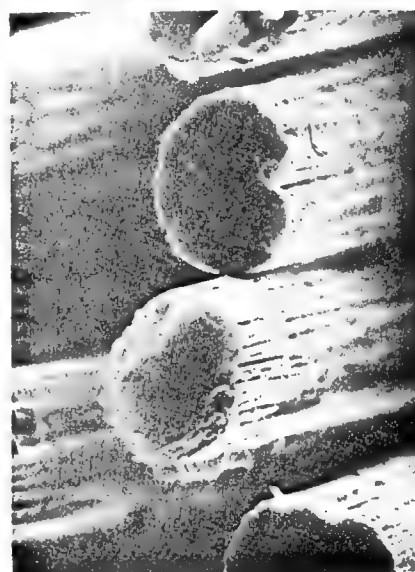

THORNEL 300 GRADE WYP 90

2  $\mu$



CELANESE DG 102

2  $\mu$

FIG. 1

Table III


## Carbon Fiber Obtained for this Study

|                             | Number of<br>Fibers<br>in Tow | Tensile<br>Strength<br>MPa (ksi) | Young's<br>Modulus<br>GPa (10 <sup>6</sup> psi) | Present<br>Cost<br>(\$/lb) |
|-----------------------------|-------------------------------|----------------------------------|---|----------------------------|
| Hercules HTS                | 10,000                        | 2979 432                         | 234 34  | 75                         |
| Hercules HTS Special        | 1,000                         | 2875 417                         | 234 34  | 300                        |
| Hercules HM ( $\mu$ ) - PVA | 1,000                         | 2427 352                         | 385 55.9  | 300                        |
| Hercules HMS - 10 K         | 10,000                        | 2344 340                         | 296-331 43-48                                   | 90                         |
| Hercules HMS - 3 K          | 3,000                         | 2330 338                         | 370 53.7  | 175                        |
| Thornel 50 WYG 130 1/2      | 1,540                         | 2172 315                         | 393 57  | 320                        |
| Thornel 75 WYL 160 1/2      | 1,540                         | 2620 380                         | 538 78  | 385                        |
| Thornel 300 WYP 30 1/2      | 3,000                         | 2482 360                         | 234 34  | 40                         |
| Thornel 300 WYP 90 1/0      | 1,000                         | 2655 385                         | 227 33  | 32                         |
| Thornel Pitch VS 0022-1     | 2,160                         | 1145 166                         | 469 68  | 55                         |
| Thornel Pitch VS 0022-2     | 2,160                         | 945 137                          | 345 50  | 55                         |
| Thornel Pitch VS 0022-3     | 2,160                         | 993 144                          | 414 60  | 55                         |
| Thornel Pitch VS 0032-1     | 720                           | 1282 186                         | 386 56  | 270                        |
| Thornel Pitch VS 0032-2     | 720                           | 1083 157                         | 400 58  | 270                        |
| Celanese DG 102             | 384                           | 1724 250                         | 531 77  | 250                        |





Table IV  
Characteristic Properties of Glasses Used

| Type of Glass | Nature of Glass            | Strain Point<br>#10 <sup>14.5</sup> | Anneal Point<br>#10 <sup>13.0</sup> | Softening Point<br>#10 <sup>7.5-8</sup> | Liquidus | Working Point<br>#10 <sup>4</sup> | $\rho$<br>gms/cm <sup>3</sup> | Index of Refract. | Dielectric Constant | Coef. Linear Expansion<br>cm/cm°C<br>x 10 <sup>-7</sup> | Modulus<br>10 <sup>6</sup> psi |
|---------------|----------------------------|-------------------------------------|-------------------------------------|---|----------|-----------------------------------|-------------------------------|-------------------|---------------------|---|--------------------------------|
| C.G.W. 7740   | Boro-silicate              | 510°C                               | 560°C                               | 821°C                                   | 1017°C   | 1252°C                            | 2.23                          | 1.474             | 4.6                 | 32.5  | 9.1                            |
| C.G.W. 1723   | Alumino-silicate           | 665                                 | 710                                 | 908                                     | 1070     | 1168                              | 2.64                          | 1.574             | 6.3                 | 46  | 12.7                           |
| Ferro S       | Magnesium-alumino-silicate | 760                                 | 810                                 | 970                                     | 1050     |                                   | 2.49                          | 1.547             | 5.2                 | 29  | 12.4                           |
| C.G.W. 7913   | High silica                | 890                                 | 1020                                | 1530                                    | 1700     |                                   | 2.18                          | 1.458             | 3.8                 | 5.5   | 9.8                            |
| C.G.W. 7940   | Pure silica                | 956                                 | 1084                                | 1580                                    | 1700     |                                   | 2.20                          | 1.459             | 3.8                 | 3.5   | 10.5                           |
| C.G.W. 7971   | Titanium silicate          |                                     | 1000                                | 1500                                    | 1600     |                                   | 2.21                          | 1.484             | 4.0                 | -2  | 9.8                            |

\*viscosity, in poises

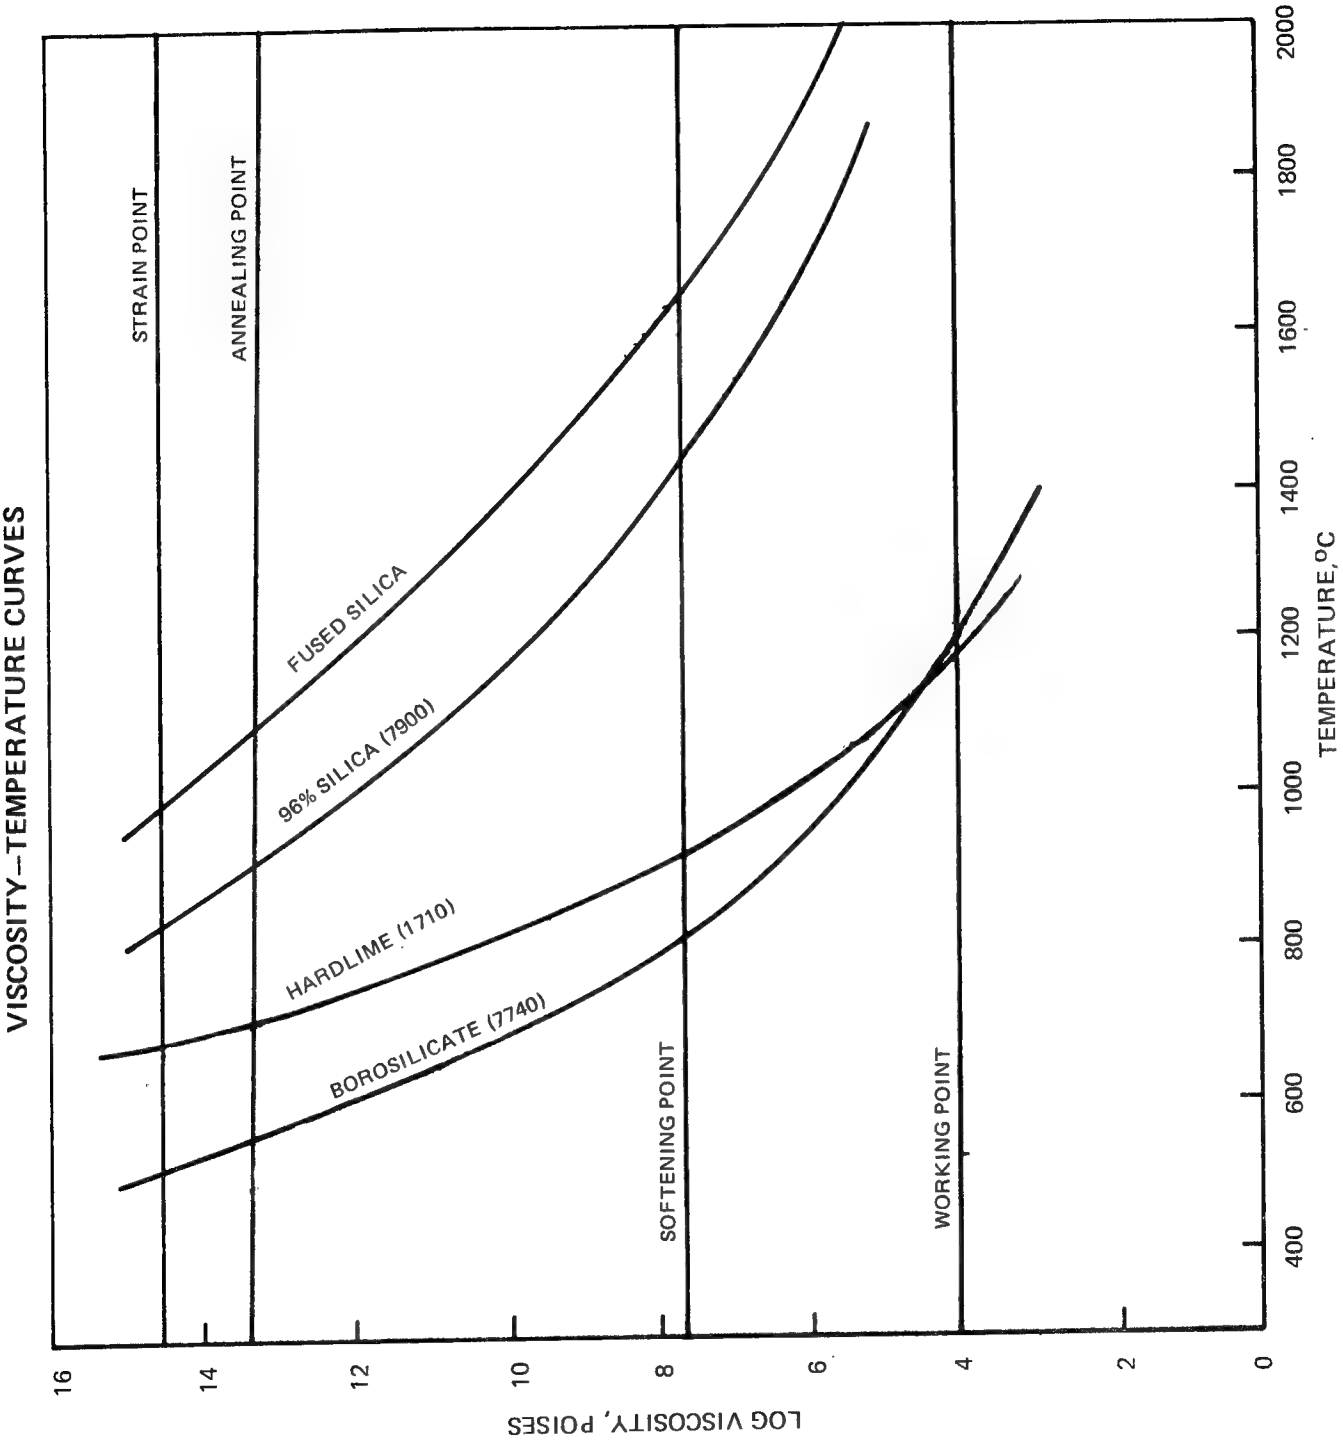

SCANNING ELECTRON MICROGRAPHS OF GLASS POWDERS

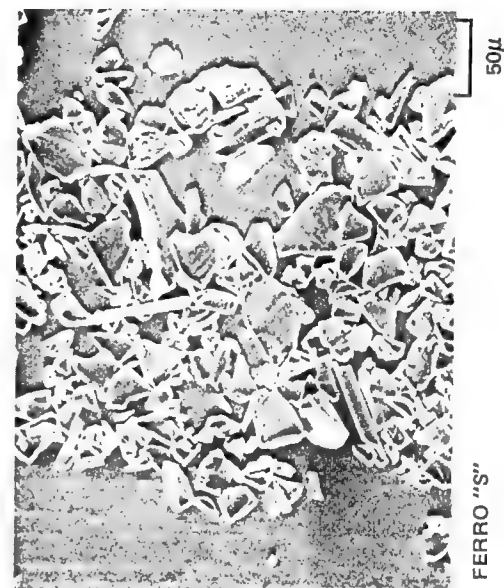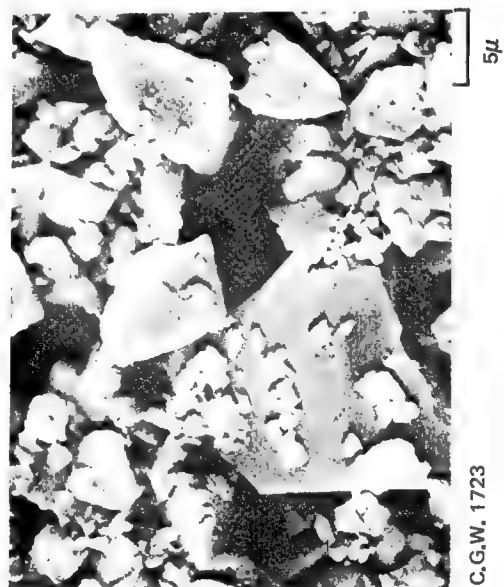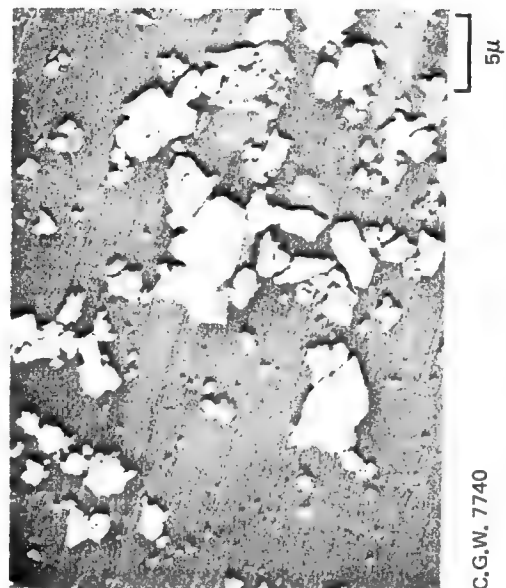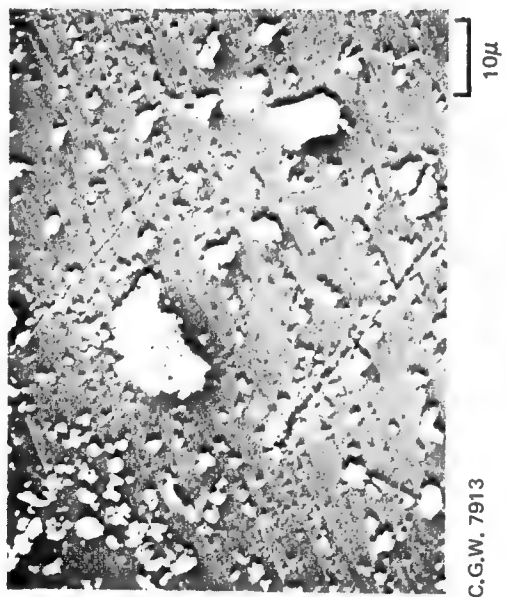

## IV. PROCESSING

## A. Description of Fabrication Process


As discussed earlier, several methods exist for coating the fiber as required in the construction of a fiber reinforced glass matrix composite and, indeed, in our earlier evaluation UTRC considered as many as six different processes. However, much the simplest and lowest cost method, if it can be made to work, consists of pulling the graphite fiber tow through a slurry containing the finely ground glass particles.

In the slurry process for coating the graphite fiber with glass, the graphite fiber is unwound from the spool and pulled through an agitated organic solution containing a suspension of fine glass particles. The process is shown schematically in Fig. 4. In greater detail, the continuous graphite tow is unwound from the drum on which it is received at a moderate rate of speed, pulled through a slip comprised of powdered glass, solvent and plasticizer to impregnate the tow, and rewound onto a large rotating drum covered with mylar tape to prevent sticking of the impregnated graphite fiber. The slip may be composed of 40 grams of powdered glass and 3 grams of polyvinyl alcohol dissolved in 100 grams of water to which 2 grams of ethylene glycol is added as a plasticizer. Alternately, the slip may comprise 85 grams of glass in 225 ml of toluene to which 5 grams of polystyrene and 5 drops of tergitol have been added. The large drum is run at one revolution per minute or a linear speed of 5 ft/min. Excess glass and solvent are removed by pressing a squeegee against the drum as it winds. The ground glass used is sized, currently, so that 90% passes through a 325 mesh sieve.

After the tape is dry (sometimes heating with a radiant heat source is necessary to remove excess solvent) it is cut and removed from the drum and then cut into strips or squares which are layed up to give unidirectional or crossplied fiber alignment and then hot pressed. The hot pressing may be carried out in vacuum using metal dies coated with colloidal boron nitride at pressures of 13.8 to 20.7 MPa (2000 to 3000 psi) and temperatures of 1050 to 1200°C for the common borosilicate glass. Alternately, the hot pressing may be done in argon using graphite dies sprayed with boron nitride powder, pressures of 13.8 to 27.6 MPa (2000 to 4000 psi), and a temperature of 1400°C for the Corning ultra-low expansion glasses. In addition, as each layer of tape is placed in the die, a packet of glass weighing 0.05 to 0.15 grams (the heavier the tape layer, the smaller the glass packet) is inserted between layers in an attempt to achieve a 60 to 70% volume loading of graphite fiber in the composite. The mold is then vibrated to ensure uniform distribution of the glass over the tape surface.



## SLURRY METHOD OF COATING GRAPHITE FIBER

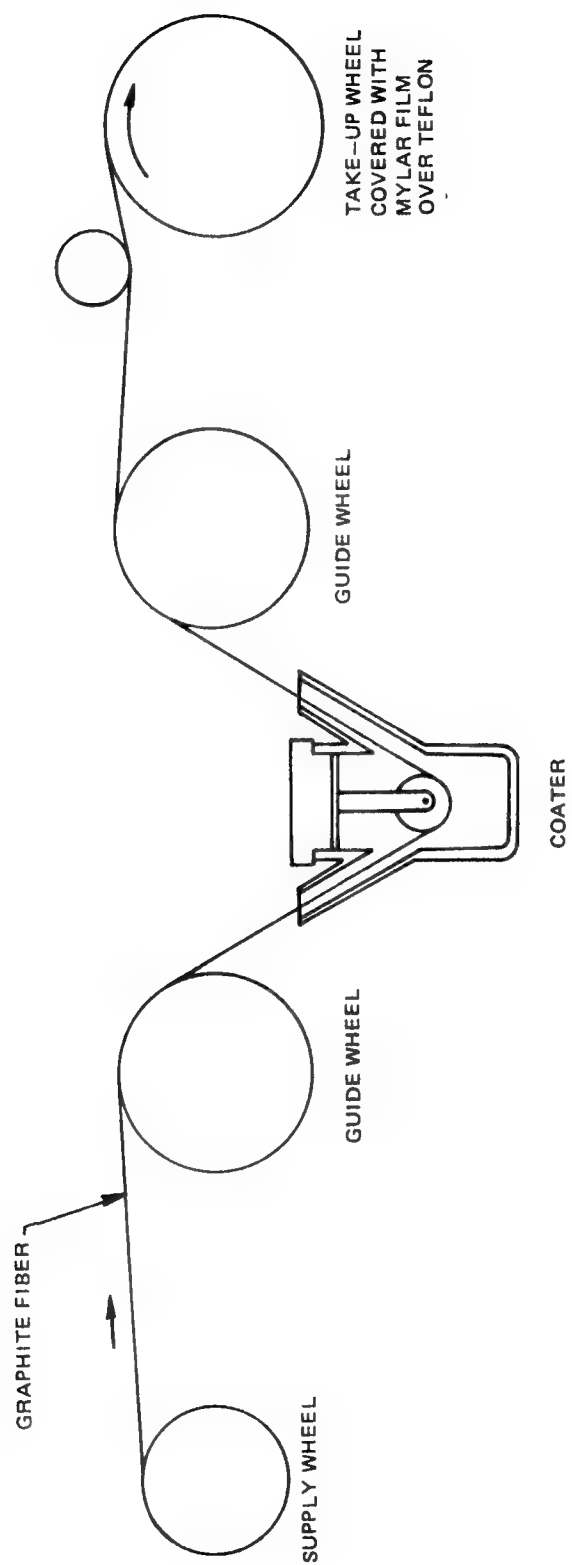




The process just described seems very straightforward. Nevertheless, as is shown in the following section, variables such as hot pressing temperature, hot pressing pressure, hot pressing atmosphere, dwell time in the hot press, amount of glass in the slurry, and amount of glass introduced between layers must all be standardized before an optimum composite can be produced. This learning process can be illustrated by examining Figs. 5, 6 and 7. Figure 5 shows the types of microstructures obtained at a very early stage in the UTRC graphite fiber reinforced glass matrix program as does Fig. 6 but with a second type of graphite fiber. Figure 7, on the other hand, is taken from the third monthly report and shows both the much greater fiber density and uniformity of fiber distribution obtained after 90 days of progress on the program. The fiber density and uniformity of fiber distribution continued to improve, as will be shown by micrographs of the most recent samples in the latter sections of this report.

In Table V data are given for all the graphite reinforced glass matrix composites fabricated to date. In this tabulation the temperature and pressure of hot pressing, the type of graphite fiber and the type of glass are the principal variables tabulated against the flexural strengths and densities achieved where these have been measured. The hot pressed sample size is typically 6.35 cm x 2.22 cm x 0.635 cm. From this sample nine flexural samples can be cut and these are typically 5.08 cm x 0.508 cm x 0.127 cm.

#### B. Effect of Processing Variables and Material Constituents


The procedure for assembling a graphite fiber reinforced glass matrix composite consists of a number of processes each with its own variables. In making the glass coated graphite fiber tape the speed with which the fiber moves through the slurry, the amount of glass in the slurry, the organic constituents in the slurry and their proportions can all be varied. In cutting the tape and stacking it into the die the amount of additional glass introduced between each layer and the number of layers must be determined experimentally. In the actual hot pressing operation the number of temperatures at which we stop to outgas, the hot pressing temperature, pressure, atmosphere and dwell time, the temperature to which the die is cooled before release of pressure, the mechanical fit of the die, and, indeed, even the particular hot press to be used must all be decided. Of course, the types of graphite fiber and of glass used in forming the glass matrix are of great importance. This section will examine the effect five of these variables have on flexural strength.

## MICROGRAPHS OF TYPICAL UTRC CARBON FIBER REINFORCED GLASS MATRIX COMPOSITES

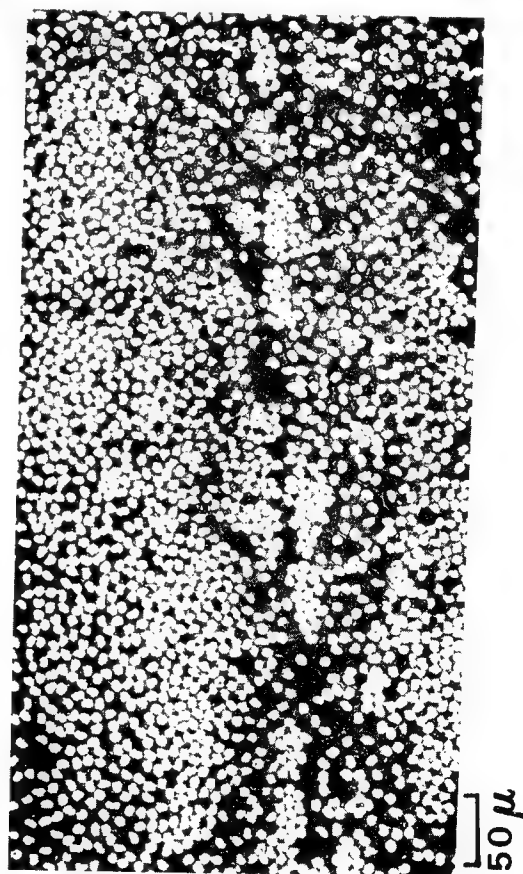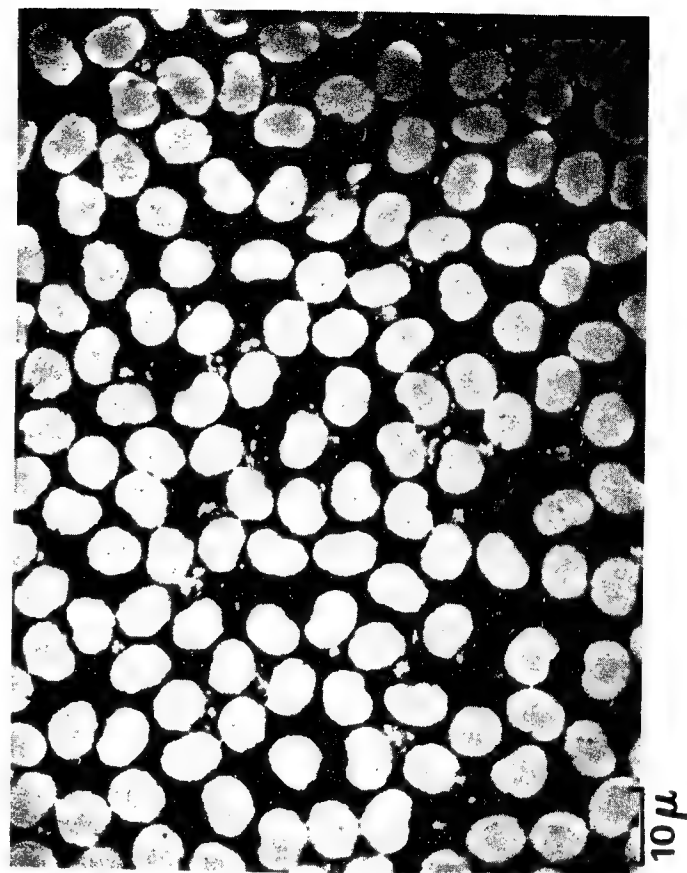
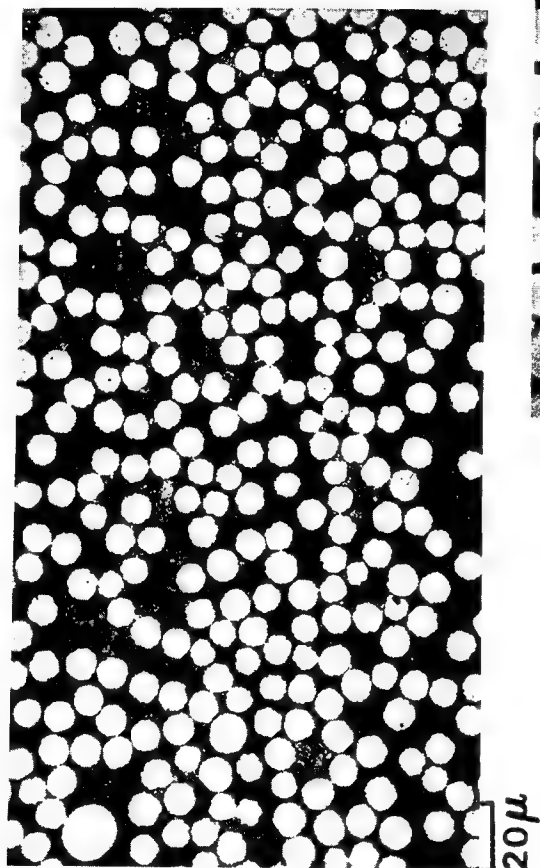


**FRACTURE STRENGTH OF THORNEL 75 -GLASS MATRIX COMPOSITE  
AND MICROGRAPHS OF MATERIAL NEAR THE FRACTURE SURFACE**


3 POINT FLEXURAL STRENGTH 359 MPa (52,100 psi)

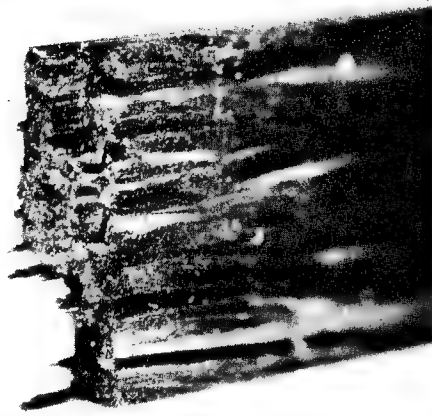


1000 $\mu$

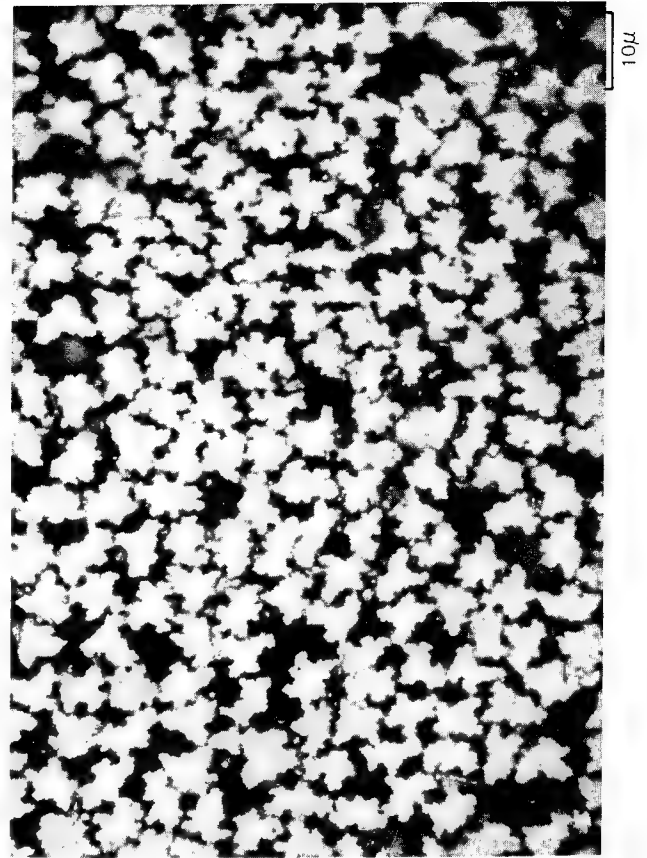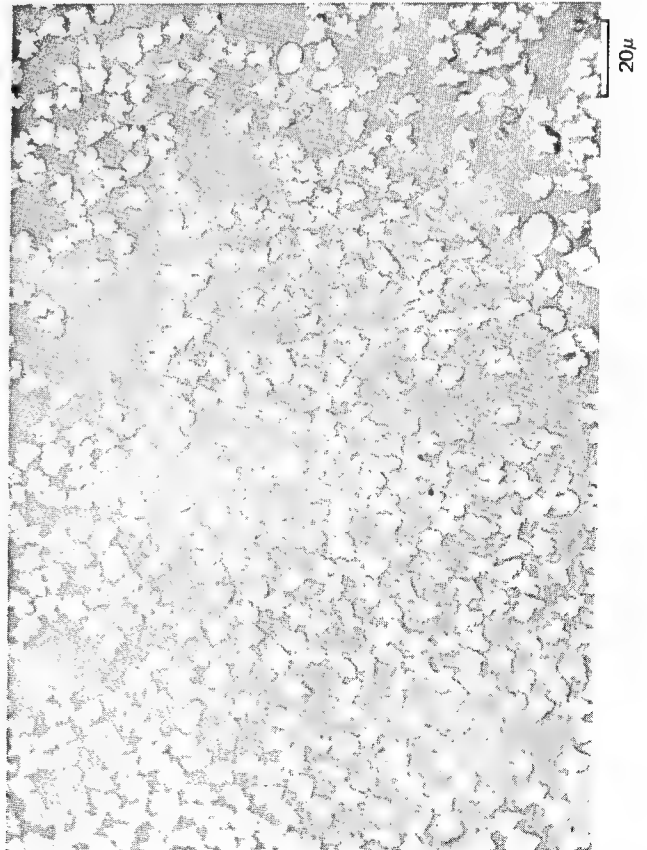


## MICROGRAPHS AFTER FRACTURE OF THREE TYPICAL SAMPLES ( 500X )

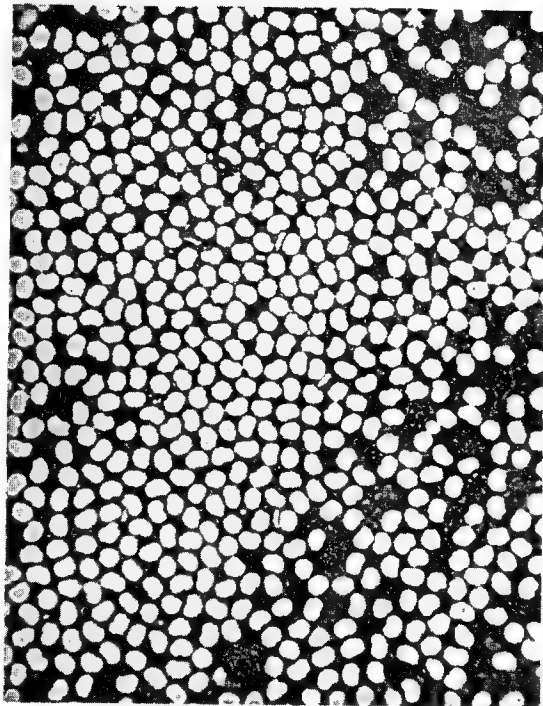

LB78-8, 506 MPa (73.4 ksi)

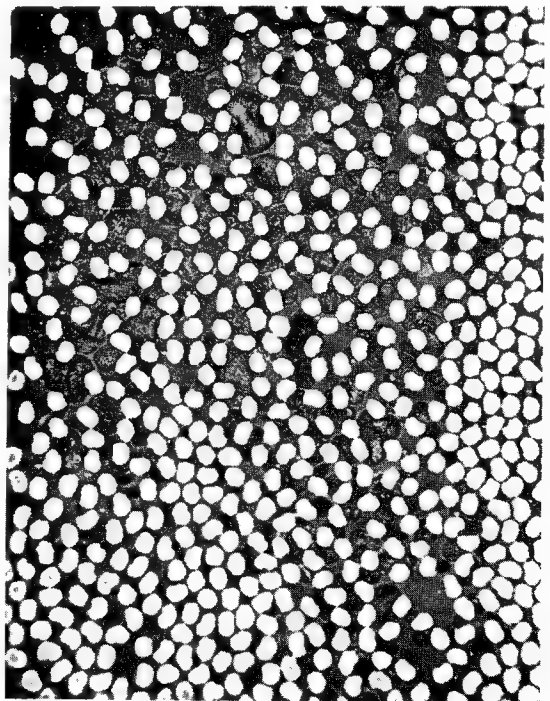

LB80-CR, 638 MPa (92.6 ksi)

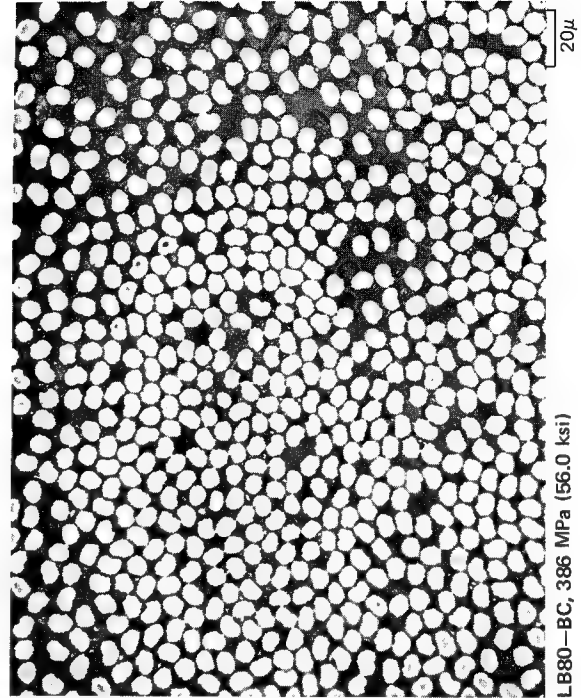

LB80-BC, 386 MPa (56.0 ksi)

Table V

## Graphite Fiber Reinforced Glass Matrix Composites Prepared and Evaluated

| Sample  | Glass     | Fiber           | Hot Pressing Conditions         |            | Three-Point Flexural Strength |          | Density<br>gms/cm <sup>3</sup> | Highest Density Achieved Similar Composite<br>gms/cm <sup>3</sup> |
|---------|-----------|-----------------|---------------------------------|------------|-------------------------------|----------|--------------------------------|---|
|         |           |                 | Pressure<br>lb/in. <sup>2</sup> | Temp<br>°C | MPa                           | psi      |                                |   |
| G1 10   | 7913      | Thornel 75      | 2000                            | 1550       | 165                           | 24,000   | 1.585                          | 2.138   |
| LB 11   | 7913      | ↓               | 13.8 MPa                        | 1600       | 198                           | 28,700   | 1.695                          |   |
| LB 12   | 7913      |                 |                                 | 1650       | 193                           | 28,000   | 1.605                          |   |
| LB 13   | 7913      |                 |                                 | 1550       | 165                           | 24,000   | 1.585                          |   |
| LB 53   | 7913+7740 |                 |                                 | 1600       | 319                           | 46,330   | 2.138                          |   |
| LB 53B  | 7913      |                 |                                 | 1600       | 199                           | 28,900   | 1.732                          |   |
| LB 90   | 7740      | Celanese DG 102 | 2000                            | 1120       | 250                           | 36,300   | 2.011                          | 2.060   |
| LB 91   | ↓         | ↓               | 13.8 MPa                        | 1120       | 227                           | 32,800   | 2.046                          |   |
| LB 92   |           |                 |                                 | 1115       | 187                           | 27,100   | 2.060                          |   |
| LB 93   |           |                 |                                 | 1110       | 330                           | 47,800   | 2.043                          |   |
| LB 94   |           |                 |                                 | 1025       | 356                           | 57,700   | 1.936                          |   |
| LB 95   |           |                 |                                 | 1050       | 230                           | 33,400   | 1.997                          |   |
| LB 96   |           |                 |                                 | 1075       | 289                           | 42,000   | 1.911                          |   |
| LB 97   | 7740      | Celanese DG 102 | 2000                            | 1100       | 342                           | 49,600   | 1.969                          | 2.060   |
| LB 97B  | ↓         | ↓               | 13.8 MPa                        | 1100       |                               |          | 1.980                          |   |
| LB 97C  |           |                 |                                 | 1100       |                               |          | 1.969                          |   |
| LB 97D  |           |                 |                                 | 1200       |                               |          | 2.025                          |   |
| LB 97E  |           |                 |                                 | 1200       | *309                          | *44,800  | 2.049                          |   |
| LB 97F  |           |                 |                                 | 1200       |                               |          | Cracked                        |   |
| LB 97G  |           |                 |                                 | 1200       |                               |          | Cracked                        |   |
| LB 97H  |           |                 |                                 | 1200       |                               |          | Cracked                        |   |
| LB 97I  |           |                 |                                 | 1200       |                               |          | Cracked                        |   |
| LB 98   | 7740      | Celanese DG 102 | 2000                            | 1120       | 310                           | 45,000   | 1.969                          | 2.060   |
| LB 112  | 8913      | ↓               | 13.8 MPa                        | 1850       |                               |          | 1.375                          |   |
| LB 107  | 7913      |                 |                                 | 1600       |                               |          |                                |   |
| LB 108  | 7913      |                 |                                 | 1650       |                               |          |                                |   |
| LB 131  | 7740      |                 |                                 | 1100       | 227                           | 32,900   | 1.952                          |   |
| LB 132  | 7740      |                 |                                 | 1100       | 243                           | 35,200   | 2.000                          |   |
| LB 135  | 7740      | Hercules HMS    | 2000                            | 1100       | 699                           | 100,000  | 1.960                          | 1.976   |
| LB 135B | ↓         | ↓               | 13.8 MPa                        | 1120       |                               |          |                                |   |
| LB 135C |           |                 |                                 | 1100       |                               |          | 1.972                          |   |
| LB 135D |           |                 |                                 | 1100       | 526                           | 76,300   |                                |   |
| LB 135E |           |                 |                                 | 1100       | *574                          | 83,300   | 1.976                          |   |
| LB 135F |           |                 |                                 | 1200       | 977                           | 142,000  | 1.920                          |   |
| LB 135G |           |                 |                                 | 1200       | *848                          | *127,300 | 1.939                          |   |
| LB 135H |           |                 |                                 | 1200       | *577                          | *83,700  | 1.957                          |   |
| LB 135I |           |                 |                                 | 1200       | *483                          | *70,100  | 1.955                          |   |
| LB 135J |           |                 |                                 | 1200       |                               |          | 1.949                          |   |
| LB 135K |           |                 |                                 | 1200       |                               |          | 1.943                          |   |
| LB 135L |           |                 |                                 | 1200       |                               |          | 1.937                          |   |
| LB 135M |           |                 |                                 | 1200       |                               |          | 1.955                          |   |
| LB 135N |           |                 |                                 | 1200       |                               |          | 1.951                          |   |
| LB 135O |           |                 |                                 | 1200       |                               |          | 1.958                          |   |

\*4-Point Flexural Test

Table V (Cont'd)

| Sample    | Glass | Fiber        | Hot Pressing Conditions         |            | Three-Point Flexural Strength |        | Density<br>gms/cm <sup>3</sup> | Highest Density Achieved Similar Composite<br>gms/cm <sup>3</sup> |
|-----------|-------|--------------|---------------------------------|------------|-------------------------------|--------|--------------------------------|---|
|           |       |              | Pressure<br>lb/in. <sup>2</sup> | Temp<br>°C | MPa                           | psi    |                                |   |
| LB 136    | 7740  | Hercules HMS | 2000                            | 1100       | 648                           | 94,000 | 1.960                          | 1.976   |
| LB 137    | 7740  | ↓            | 13.8 MPa                        | 1100       | 648                           | 94,000 | 1.957                          |   |
| LB 138    | 7740  |              |                                 | 1100       | 661                           | 96,000 | 1.952                          |   |
| LB 139    | 7740  |              |                                 | 1100       |                               |        |                                |   |
| LB 140    | 7740  |              |                                 | 1100       |                               |        |                                |   |
| LB 157    | 7740  |              |                                 | 1100       |                               |        |                                |   |
| LB 158    | 7740  |              |                                 | 1100       |                               |        | 1.977                          |   |
| LB 159    | 7740  |              |                                 | 1100       |                               |        |                                |   |
| LB 171    | 1723  |              |                                 | 1120       |                               |        | 1.9637                         |   |
| LB 172    | 1723  |              |                                 | 1120       | 353                           | 51,300 |                                |   |
| LB 173    | 1723  |              |                                 | 1120       |                               |        | 1.9489                         |   |
| LB 174    | 1723  |              |                                 | 1120       |                               |        |                                |   |
| LB 147    | 7740  | Hercules HTS | 2000                            | 1100       |                               |        |                                | 1.902   |
| LB 148    | ↓     | ↓            | 13.8 MPa                        | 1100       | 370                           | 53,700 | 1.902                          |   |
| LB 148B   |       |              |                                 | 1100       |                               |        | 1.597                          |   |
| LB 148C   |       |              |                                 | 1100       |                               |        | 1.858                          |   |
| LB 148D   |       |              |                                 | 1100       |                               |        | 1.886                          |   |
| LB 148E   |       |              |                                 | 1200       |                               |        | 1.865                          |   |
| LB 148F   |       |              |                                 | 1200       |                               |        | 1.800                          |   |
| LB 149    |       |              |                                 | 1100       | 324                           | 47,000 |                                |   |
| LB 150    |       |              |                                 | 1100       |                               |        |                                |   |
| LB 151    |       |              |                                 | 1100       |                               |        |                                |   |
| LB 152    |       |              |                                 | 1100       |                               |        |                                |   |
| C2639-2,3 | 7740  | Thornel 300  | 2000                            | 1100       | 364                           | 52,750 |                                | 2.013   |
| C265B-1,2 | ↓     | ↓            | 13.8 MPa                        | 1100       | 376                           | 54,450 | 1.931                          |   |
| Gl 1-1,2  |       |              |                                 | 1225       | 304                           | 44,000 | 1.603                          |   |
| Gl 2a,b   |       |              |                                 | 1600       | 147                           | 21,300 | 1.955                          |   |
| Gl 3a,b   |       |              |                                 | 1650       | 109                           | 15,800 | 2.013                          |   |
| Gl 4a,b   |       |              |                                 | 1550       | 187                           | 27,100 |                                |   |
| Gl 5a,b   |       |              |                                 | 1150       | 359                           | 52,000 |                                |   |
| Gl 6a,b   |       |              |                                 | 1050       | 259                           | 37,500 |                                |   |
| LB 75     |       |              |                                 | 1050       | 273                           | 39,700 | 1.757                          |   |
| LB 78     |       | Thornel 300S |                                 | 1050       | 312                           | 45,200 | 1.829                          |   |
| LB 79     |       | Thornel 300  | 4000                            | 1050       | 376                           | 54,600 |                                |   |
| LB 80     |       | Thornel 300  | 27.6 MPa                        | 1100       | 479                           | 69,400 |                                |   |
| LB 81     |       | Thornel 300  |                                 | 1100       | 210                           | 30,500 | 1.780                          |   |
| LB 82     |       | Thornel 300  |                                 | 1100       | 342                           | 49,600 |                                |   |
| LB 133    |       | Thornel 300S | 2000                            | 1100       |                               |        | 1.566                          |   |
| LB 160    |       | ↓            | 13.8 MPa                        | 1120       |                               |        |                                |   |
| LB 161    |       |              |                                 | 1120       | 498                           | 72,200 |                                |   |
| LB 151B   |       |              |                                 | 1120       |                               |        | 1.700                          |   |
| LB 161C   |       |              |                                 | 1120       |                               |        | 1.674                          |   |
| LB 161D   |       |              |                                 | 1120       |                               |        | 1.640                          |   |
| LB 161E   |       |              |                                 | 1200       |                               |        | 1.675                          |   |
| LB 161F   |       |              |                                 | 1200       |                               |        | 1.673                          |   |
| LB 162    |       |              |                                 | 1120       | 499                           | 72,500 | 1.823                          |   |
| LB 163    |       |              |                                 | 1120       | 488                           | 70,800 | 1.829                          |   |
| LB 134    |       |              |                                 | 1100       |                               |        |                                |   |

### 1. Effect of Amount of Glass in Slurry

In Table VI the effect of the amount of glass in the slurry used to coat the graphite is shown. As can be seen, doubling the glass added to the slurry results in a decrease of strength. Similar tests run with 45 grams of glass in the slurry and 135 grams of glass in the slurry confirm that the best choice seems to be about 85 grams of glass in 200 grams of isopropyl alcohol, 10 grams of polyvinyl alcohol and 5 drops of a wetting agent such as Tergitol's H.D. 527.

### 2. Effect of Hot Pressing Pressure

The effect of hot pressing pressure on the achieved flexural strength of a Thornel 300 7740 glass composite is shown in Table VII. Doubling the pressure applied to the hot press from 13.8 to 27.6 MPa (2000 to 4000 psi) increases the flexural strength approximately 10%. More importantly, however, it also appears to decrease the scatter shown by the three-point flexural strength data. However, since it has been found that a slight increase in hot pressing temperature achieves much the same result, this is a preferred operational procedure, for at 27.6 MPa (4000 psi) on the unsupported (not filament wound) graphite dies customarily used at UTRC, operation at the higher pressure greatly shortens die life.

### 3. Effect of Temperature

The effect of temperature on achieved flexural strength of the graphite fiber-glass matrix composite is much greater than the effect of pressure or of the amount of glass present in the slurry. Optical and scanning electron microscopic examination shows exactly what happens as the temperature is increased, and fully explains the data shown in Table VIII. When only the optical micrographs of selected areas of these samples are examined as in Fig. 8, one is unable to sense any significant difference in the samples. However, if one studies the optical tape maps of entire cross sections of the samples (taken at 50X) shown in Figs. 9, 10, 11 and 12, the complete story of what has happened to the samples as the hot pressing temperature is increased from 1025°C to 1100°C is apparent. At 1025°C, Fig. 9, the individual tows are distinct and surrounded by glass rich areas, i.e. they have maintained their individual identity. On the other hand, at 1100°C, Fig. 12, the memories of the individual tows are almost entirely eliminated. Figures 10 and 11, specimens prepared at 1050°C and 1075°C respectively, show intermediate steps in the progression from memories of individual tows to almost complete obliteration of tow identity. This is due to a factor of four change in viscosity of the 7740 glass as the temperature is increased from 1025°C to 1100°C. As shown in Table IX, these results cannot be explained by a variation in the fiber content of the composites.



Table VI

Effect of Amount of Glass in Slurry on Achieved Flexural Strength  
of Graphite Fiber Reinforced Glass Composite

| Specimen | Glass | Fiber       | Temp. of<br>Hot Press<br>°C | Pressure<br>psi | 3-Point<br>Flexural Strength<br>MPa | 3-Point<br>Flexural Strength<br>psi | Glass in<br>Slurry<br>gms | Glass Added<br>Between Layers |
|----------|-------|-------------|-----------------------------|-----------------|-------------------------------------|-------------------------------------|---------------------------|-------------------------------|
| LB 75-2  | 7740  | Thornel 300 | 1050 argon                  | 2000            | 287                                 | 41,700                              | 170                       | 0.11                          |
| -3       | →     | →           | →                           | →               | 277                                 | 40,200                              | →                         | →                             |
| -5       | →     | →           | →                           | →               | 242                                 | 35,000                              | →                         | →                             |
| -6       | →     | →           | →                           | →               | 261                                 | 37,800                              | →                         | →                             |
| -7       | →     | →           | →                           | →               | 271                                 | 39,300                              | →                         | →                             |
| -9       | →     | →           | →                           | →               | 306                                 | 44,400                              | →                         | →                             |
| Average  |       |             |                             |                 | 274                                 | 39,700                              |                           |                               |
| LB 78-1  | 7740  | Thornel 300 | 1050 argon                  | 2000            | 418                                 | 60,600                              | 85                        | 0.063                         |
| -2       | →     | →           | →                           | →               | 326                                 | 47,300                              | →                         | →                             |
| -4       | →     | →           | →                           | →               | 504                                 | 73,100                              | →                         | →                             |
| -5       | →     | →           | →                           | →               | 355                                 | 51,500                              | →                         | →                             |
| -7       | →     | →           | →                           | →               | 456                                 | 66,200                              | →                         | →                             |
| -8       | →     | →           | →                           | →               | 505                                 | 73,400                              | →                         | →                             |
| Average  |       |             |                             |                 | 427.5                               | 63,000                              |                           |                               |

Table VII

Effect of Hot Pressing Pressure on Achieved Flexural Strength of  
Graphite Fiber Reinforced Glass Composite





| Specimen | Material |             | Hot Pressing Conditions |              | Achieved 3-Point Flexural Strength |        | Glass Added Between Layers |     | Glass in Slurry |
|----------|----------|-------------|-------------------------|--------------|------------------------------------|--------|----------------------------|-----|-----------------|
|          | Glass    | Fiber       | Temp. °C                | Pressure psi | MPa                                | psi    | gms                        | gms |                 |
| LB 78-1  | 7740     | Thornel 300 | 1050 Argon              | 2000         | 418                                | 60,600 | 0.063                      |     | 85              |
| -2       |          |             |                         | 13.8 MPa     | 326                                | 47,300 |                            |     |                 |
| -3       |          |             |                         |              | 173                                | 25,100 |                            |     |                 |
| -4       |          |             |                         |              | 504                                | 73,100 |                            |     |                 |
| -5       |          |             |                         |              | 355                                | 51,500 |                            |     |                 |
| -6       |          |             |                         |              | 265                                | 38,500 |                            |     |                 |
| -7       |          |             |                         |              | 456                                | 66,200 |                            |     |                 |
| -8       |          |             |                         |              | 506                                | 73,400 |                            |     |                 |
| -9       |          |             |                         |              | 211                                | 30,600 |                            |     |                 |
| -10      |          |             |                         |              | 223                                | 32,300 |                            |     |                 |
| -11      |          |             |                         |              | 304                                | 44,100 |                            |     |                 |
| Average  |          |             |                         |              | 340                                | 49,300 |                            |     |                 |
| LB 79-1  | 7740     | Thornel 300 | 1050 Argon              | 4000         | 449                                | 65,080 | 0.074                      |     | 85              |
| -2       |          |             |                         | 27.6 MPa     | 335                                | 48,600 |                            |     |                 |
| -3       |          |             |                         |              | 417                                | 60,500 |                            |     |                 |
| -4       |          |             |                         |              | No Test                            |        |                            |     |                 |
| -5       |          |             |                         |              | 339                                | 49,200 |                            |     |                 |
| -6       |          |             |                         |              | 460                                | 66,700 |                            |     |                 |
| -7       |          |             |                         |              | 266                                | 38,600 |                            |     |                 |
| -8       |          |             |                         |              | 399                                | 57,900 |                            |     |                 |
| -9       |          |             |                         |              | 345                                | 50,000 |                            |     |                 |
| Average  |          |             |                         |              | 376                                | 54,600 |                            |     |                 |

Table VIII


Effect of Temperature on Achieved Flexural Strength of Graphite Fiber-Glass Composite

| Specimen | Material |          | Hot Pressing Conditions |                 | Density<br>gms/cm <sup>3</sup> | Strength on 3 Pt Flexural Test |                       | Vibrated Die | Glass Added Between Layers<br>gms | Glass in Slurry<br>gms |
|----------|----------|----------|-------------------------|-----------------|--------------------------------|--------------------------------|-----------------------|--------------|-----------------------------------|------------------------|
|          | Glass    | Fiber    | Temp °C<br>Argon        | Pressure<br>psi |                                | MN/m <sup>2</sup>              | x 10 <sup>3</sup> psi |              |                                   |                        |
| LB 94    |          |          |                         |                 |                                |                                |                       |              |                                   |                        |
| L-1      | 7740     | Celanese | 1025                    | 2000            | 1.97                           | 414                            | 60.0                  | yes          | 0.05                              | 85                     |
| L-2      |          |          |                         | 13.8 MPa        |                                | 330                            | 47.9                  |              |                                   |                        |
| L-3      |          |          |                         |                 |                                | 248                            | 35.9                  |              |                                   |                        |
| C-1      |          |          |                         |                 |                                | 301                            | 43.7                  |              |                                   |                        |
| C-2      |          |          |                         |                 |                                | 291                            | 42.2                  |              |                                   |                        |
| C-3      |          |          |                         |                 |                                | 285                            | 41.3                  |              |                                   |                        |
| R-1      |          |          |                         |                 |                                | 456                            | 66.1                  |              |                                   |                        |
| R-2      |          |          |                         |                 |                                | 418                            | 60.7                  |              |                                   |                        |
| R-3      |          |          |                         |                 |                                | 462                            | 67.0                  |              |                                   |                        |
|          |          |          |                         |                 |                                | avg                            | 356                   | 51.7         |                                   |                        |
| LB 95    |          |          |                         |                 |                                |                                |                       |              |                                   |                        |
| L-1      | 7740     | Celanese | 1050                    | 2000            | 2.021                          | 265                            | 38.5                  | yes          | 0.05                              | 85                     |
| L-2      |          |          |                         | 13.8 MPa        |                                | 218                            | 31.6                  |              |                                   |                        |
| L-3      |          |          |                         |                 |                                | 259                            | 37.6                  |              |                                   |                        |
| C-1      |          |          |                         |                 |                                | 202                            | 29.3                  |              |                                   |                        |
| C-2      |          |          |                         |                 |                                | 199                            | 28.9                  |              |                                   |                        |
| C-3      |          |          |                         |                 |                                | 252                            | 36.5                  |              |                                   |                        |
| R-1      |          |          |                         |                 |                                | 173                            | 25.1                  |              |                                   |                        |
| R-2      |          |          |                         |                 |                                | 215                            | 31.2                  |              |                                   |                        |
| R-3      |          |          |                         |                 |                                | 294                            | 42.6                  |              |                                   |                        |
|          |          |          |                         |                 |                                | avg                            | 230                   | 33.4         |                                   |                        |
| LB 96    |          |          |                         |                 |                                |                                |                       |              |                                   |                        |
| L-1      | 7740     | Celanese | 1075                    | 2000            | 1.937                          | 295                            | 42.8                  | yes          | 0.05                              | 85                     |
| L-2      |          |          |                         | 13.8 MPa        |                                | 274                            | 39.8                  |              |                                   |                        |
| L-3      |          |          |                         |                 |                                | 313                            | 45.4                  |              |                                   |                        |
| C-1      |          |          |                         |                 |                                | 271                            | 39.3                  |              |                                   |                        |
| C-2      |          |          |                         |                 |                                | 268                            | 38.9                  |              |                                   |                        |
| C-3      |          |          |                         |                 |                                | 320                            | 46.4                  |              |                                   |                        |
| R-1      |          |          |                         |                 |                                | 261                            | 37.8                  |              |                                   |                        |
| R-2      |          |          |                         |                 |                                | 302                            | 43.8                  |              |                                   |                        |
| R-3      |          |          |                         |                 |                                | 300                            | 43.5                  |              |                                   |                        |
|          |          |          |                         |                 |                                | avg                            | 290                   | 42.0         |                                   |                        |
| LB 97    |          |          |                         |                 |                                |                                |                       |              |                                   |                        |
| L-1      | 7740     | Celanese | 1100                    | 2000            | 1.969                          | 399                            | 57.8                  | yes          | 0.05                              | 85                     |
| L-2      |          |          |                         | 13.8 MPa        |                                | 411                            | 59.6                  |              |                                   |                        |
| L-3      |          |          |                         |                 |                                | 265                            | 38.4                  |              |                                   |                        |
| C-1      |          |          |                         |                 |                                | 339                            | 49.1                  |              |                                   |                        |
| C-2      |          |          |                         |                 |                                | 340                            | 49.3                  |              |                                   |                        |
| C-3      |          |          |                         |                 |                                | 293                            | 42.5                  |              |                                   |                        |
| R-1      |          |          |                         |                 |                                | 281                            | 40.8                  |              |                                   |                        |
| R-2      |          |          |                         |                 |                                | 362                            | 52.5                  |              |                                   |                        |
| R-3      |          |          |                         |                 |                                | 392                            | 56.8                  |              |                                   |                        |
|          |          |          |                         |                 |                                | avg                            | 342                   | 49.6         |                                   |                        |


## OPTICAL MICROGRAPHS OF FOUR UNFRACTURED SAMPLES

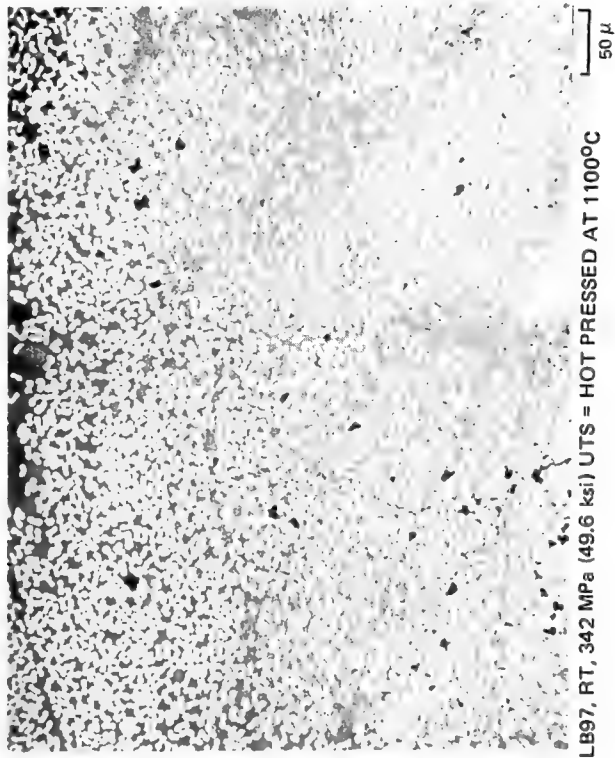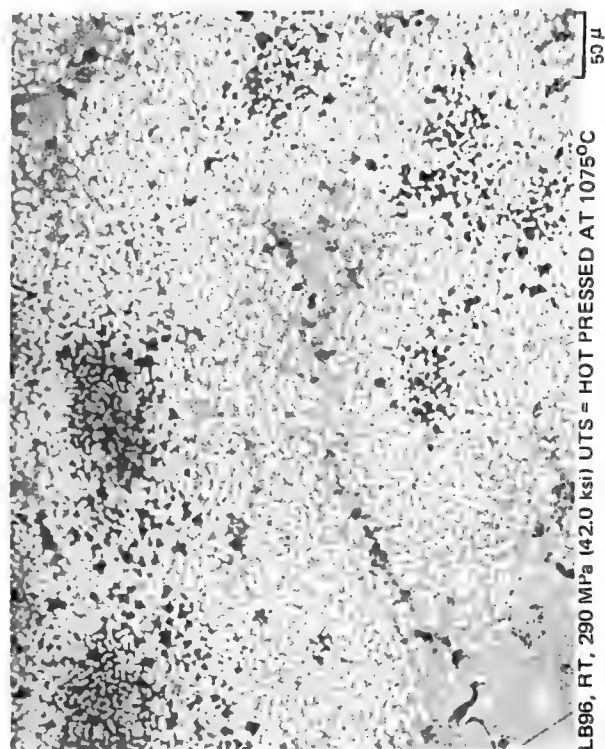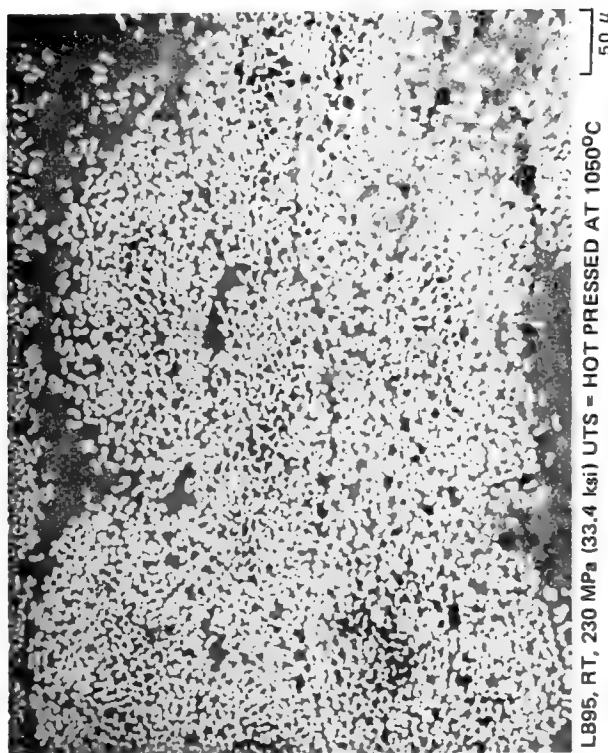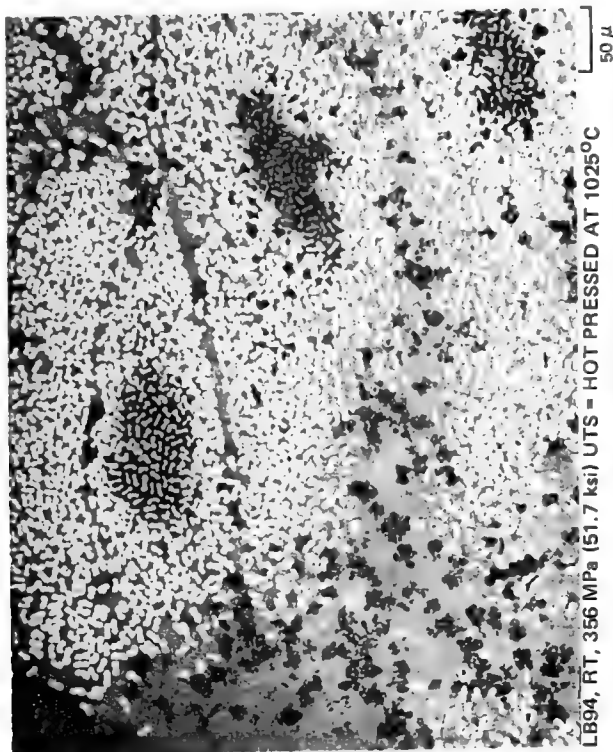

TAPE MAP OF UNFRACTURED SAMPLE LB94 CELANESE DG-102 FIBER, 7740 GLASS  
MATRIX, HOT PRESSED AT 1025 °C

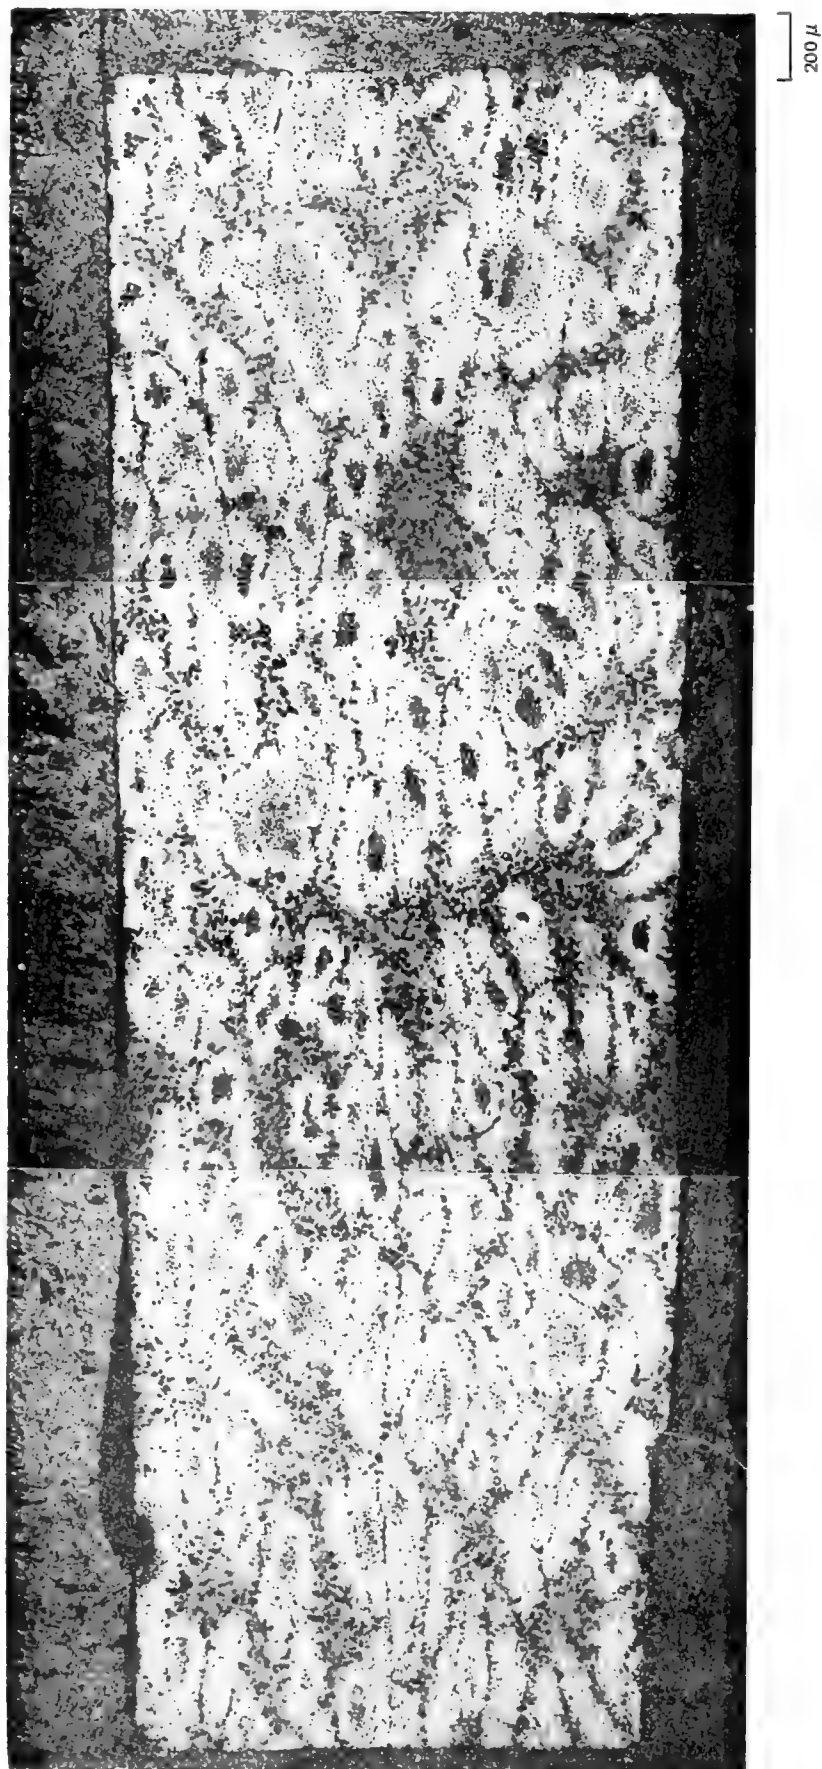

TAPE-MAP OF UNFRACTURED SAMPLE LB95 CELANESE DG-102 FIBER, 7740 GLASS MATRIX,  
HOT PRESSED AT 1050 °C

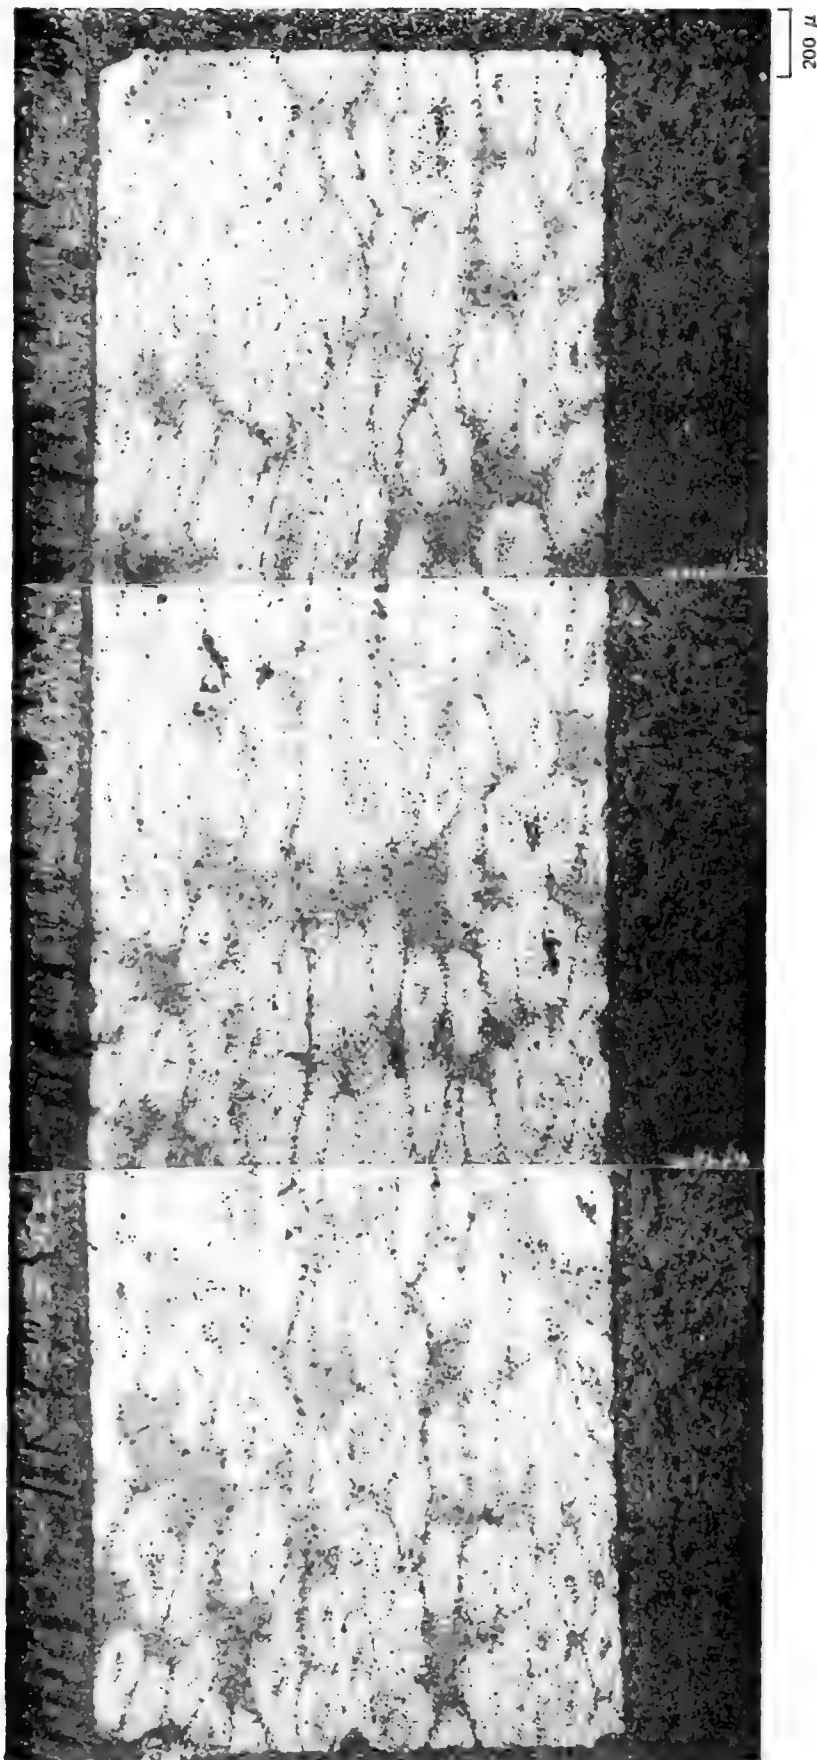

76-07-207-7

TAPE-MAP OF UNFRACTURED SAMPLE LB96 CELANESE DG-102 FIBER, 7740 GLASS MATRIX,  
HOT PRESSED AT 1075 °C





TAPE-MAP OF UNFRACTURED SAMPLE LB97 CELANESE DG-102 FIBER, 7740 GLASS MATRIX,  
HOT PRESSED AT 1100 °C





Table IX

Fiber Content and Composite Strength for Several Celanese Graphite Fibers  
in Corning Glass Works 7740 Glass Matrix Composites

| Sample | Glass | Fiber    | MPa | 3 Point<br>Flexural<br>Strength<br>avg., ksi | Density<br>gms/cm <sup>3</sup> | *Weight % |       | Weight % |       | Vol %  |       | Vol %  |       | Porosity<br>% |
|--------|-------|----------|-----|--|--------------------------------|-----------|-------|----------|-------|--------|-------|--------|-------|---------------|
|        |       |          |     |  |                                | Carbon    | Glass | Carbon   | Glass | Carbon | Glass | Carbon | Glass |               |
| IB 94  | 7740  | Celanese | 356 | 51.7   | 1.97                           | 56.5      | 43.5  | 56.1     | 38.0  | 56.1   | 38.0  | 56.1   | 38.0  | 5.9           |
| 95     | 7740  | Celanese | 230 | 33.4   | 2.021                          | 58.7      | 41.3  | 61.4     | 37.9  | 61.4   | 37.9  | 61.4   | 37.9  | 0.7           |
| 96     | 7740  | Celanese | 290 | 42.0   | 1.937                          | 55.4      | 44.6  | 56.2     | 39.8  | 56.2   | 39.8  | 56.2   | 39.8  | 4.0           |
| 97     | 7740  | Celanese | 342 | 49.6   | 1.969                          | 50.8      | 49.2  | 52.4     | 44.6  | 52.4   | 44.6  | 52.4   | 44.6  | 3.0           |

\*May include residues from polyvinyl alcohol and polystyrene used in sample preparation.

All samples were cut from top and bottom surfaces of the same specimen used to prepare nine flexural strength samples. Temperatures of preparation of samples were 1025, 1050, 1075 and 1100°C respectively.

Figures 13, 14, and 15 examine the nature of the fracture surface of these Celanese DG-102 graphite fiber-Pyrex glass specimens prepared at the several temperatures. It is apparent from the scanning electron micrographs that the breaks are fibrous in appearance. Examination of the higher magnification micrographs indicates that the glass is around each and every fiber and tightly bonded to it which as is shown later accounts for the fine environmental stability of these types of composites.


Figure 16 summarizes the joint effects of temperature and pressure. Here the results of three composites made at two different temperatures and two different pressures are plotted on probability paper. It is seen that as the pressure and temperature are increased toward some optimum value, not only does the average three-point flexural strength of the composite increase but the actual spread in individual values of the three-point flexural tests decreases. The approximate linearity of these plots on probability paper indicates that the distribution of three-point flexural values for a given composite is Gaussian in character and that the Gaussian distribution becomes more sharply peaked as we approach optimum hot pressing conditions.

#### 4. Graphite Fiber Effect


Although processing variables such as the temperature and pressure of the hot pressing operation are very important, their influence on the achieved flexural strength of the graphite fiber-glass composite is actually much less than that of the kind of graphite fiber selected to form the composite. In Table X are shown some of the best and more recent results obtained in measuring the three-point bend strength of four types of graphite fiber in 7740 glass matrices. These results may be summarized by saying that at this time the Hercules-HMS graphite fibers in 7740 glass are expected to average higher than 690 MPa or 100,000 psi in three-point flexural strength with corresponding figures of 500 MPa or 72,000 psi for Thornel 300S fiber, 370 MPa or 54,000 psi for Hercules HTS fiber, and 340 MPa or 49,000 psi for Celanese DG-102 fiber. Again as Table X demonstrates there seems to be no valid connection between the modulus and strength of the fiber used and the flexural strength of the composite. It is obvious therefore that the flexural strength of the composite must be dependent on variables not yet properly studied such as the surface chemistry of the fiber and the degree of bonding obtained between a particular kind of fiber and a particular kind of glass.

In the next major section (Section V) of this report the properties achieved with the Hercules HMS fiber in 7740, which gave the strongest composite, and those achieved with the Celanese DG-102 fiber, which is the composite with the greatest environmental stability, are examined in detail. Before concluding this section, therefore, it seems advisable to examine the properties obtained with

SCANNING ELECTRON MICROGRAPH OF FRACTURE SURFACE  
LB95-R3, 294 MPa (42.6 ksi) 1050°C PREPARATION

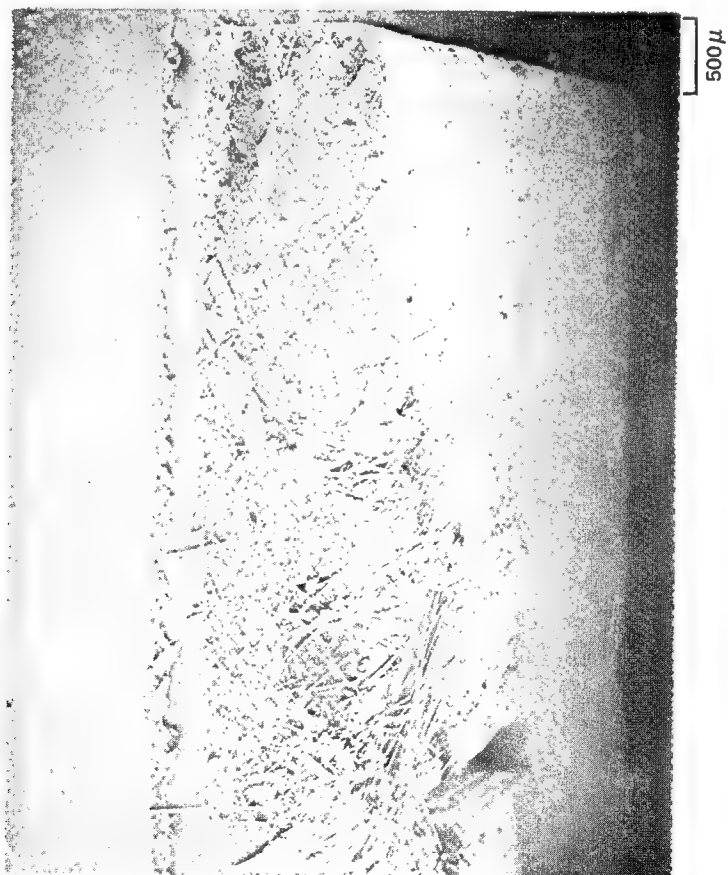

SCANNING ELECTRON MICROGRAPH OF FRACTURE SURFACE  
OF LB96-L2, 274 MPa (39.8 ksi) 1075°C PREPARATION

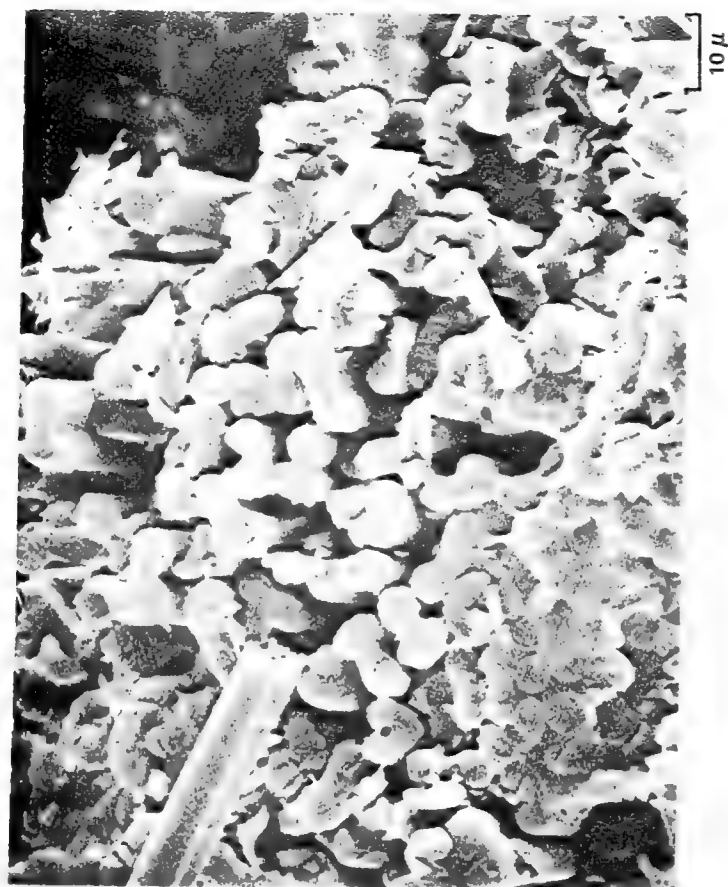

SCANNING ELECTRON MICROGRAPH OF FRACTURED SURFACE OF LB97-L2,  
410 MPa (59.6 ksi) 1100°C PREPARATION

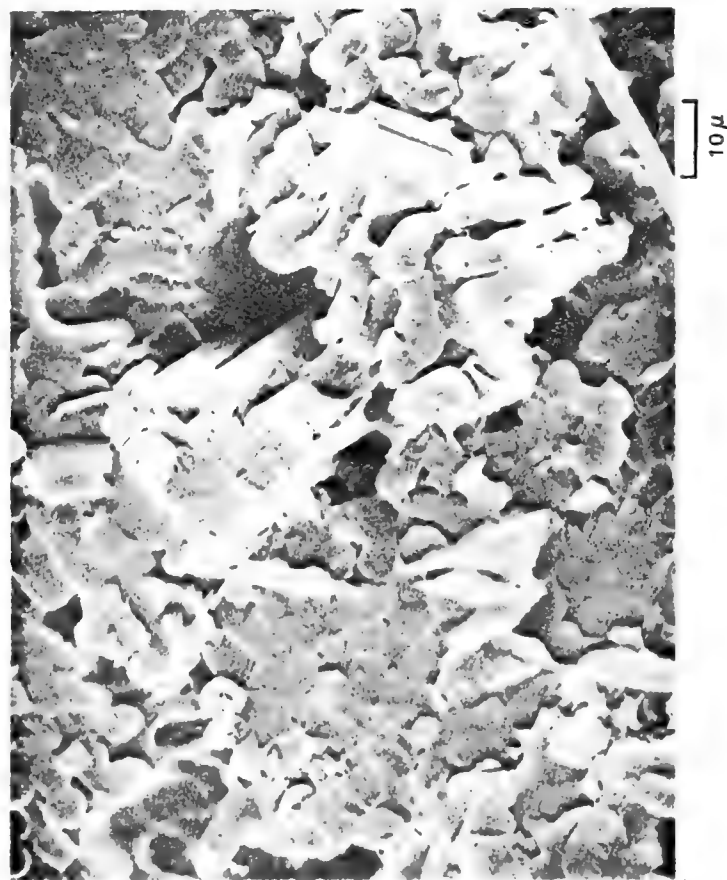
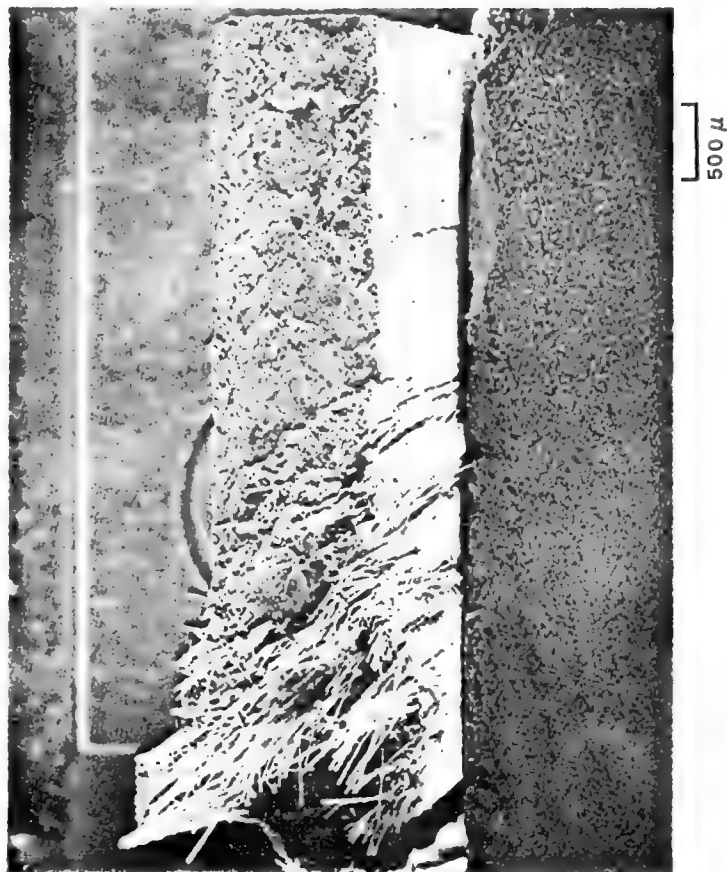


FIG. 15

DISTRIBUTION OF STRENGTH OF THREE THORNEL 300 FIBER  
GLASS MATRIX COMPOSITES

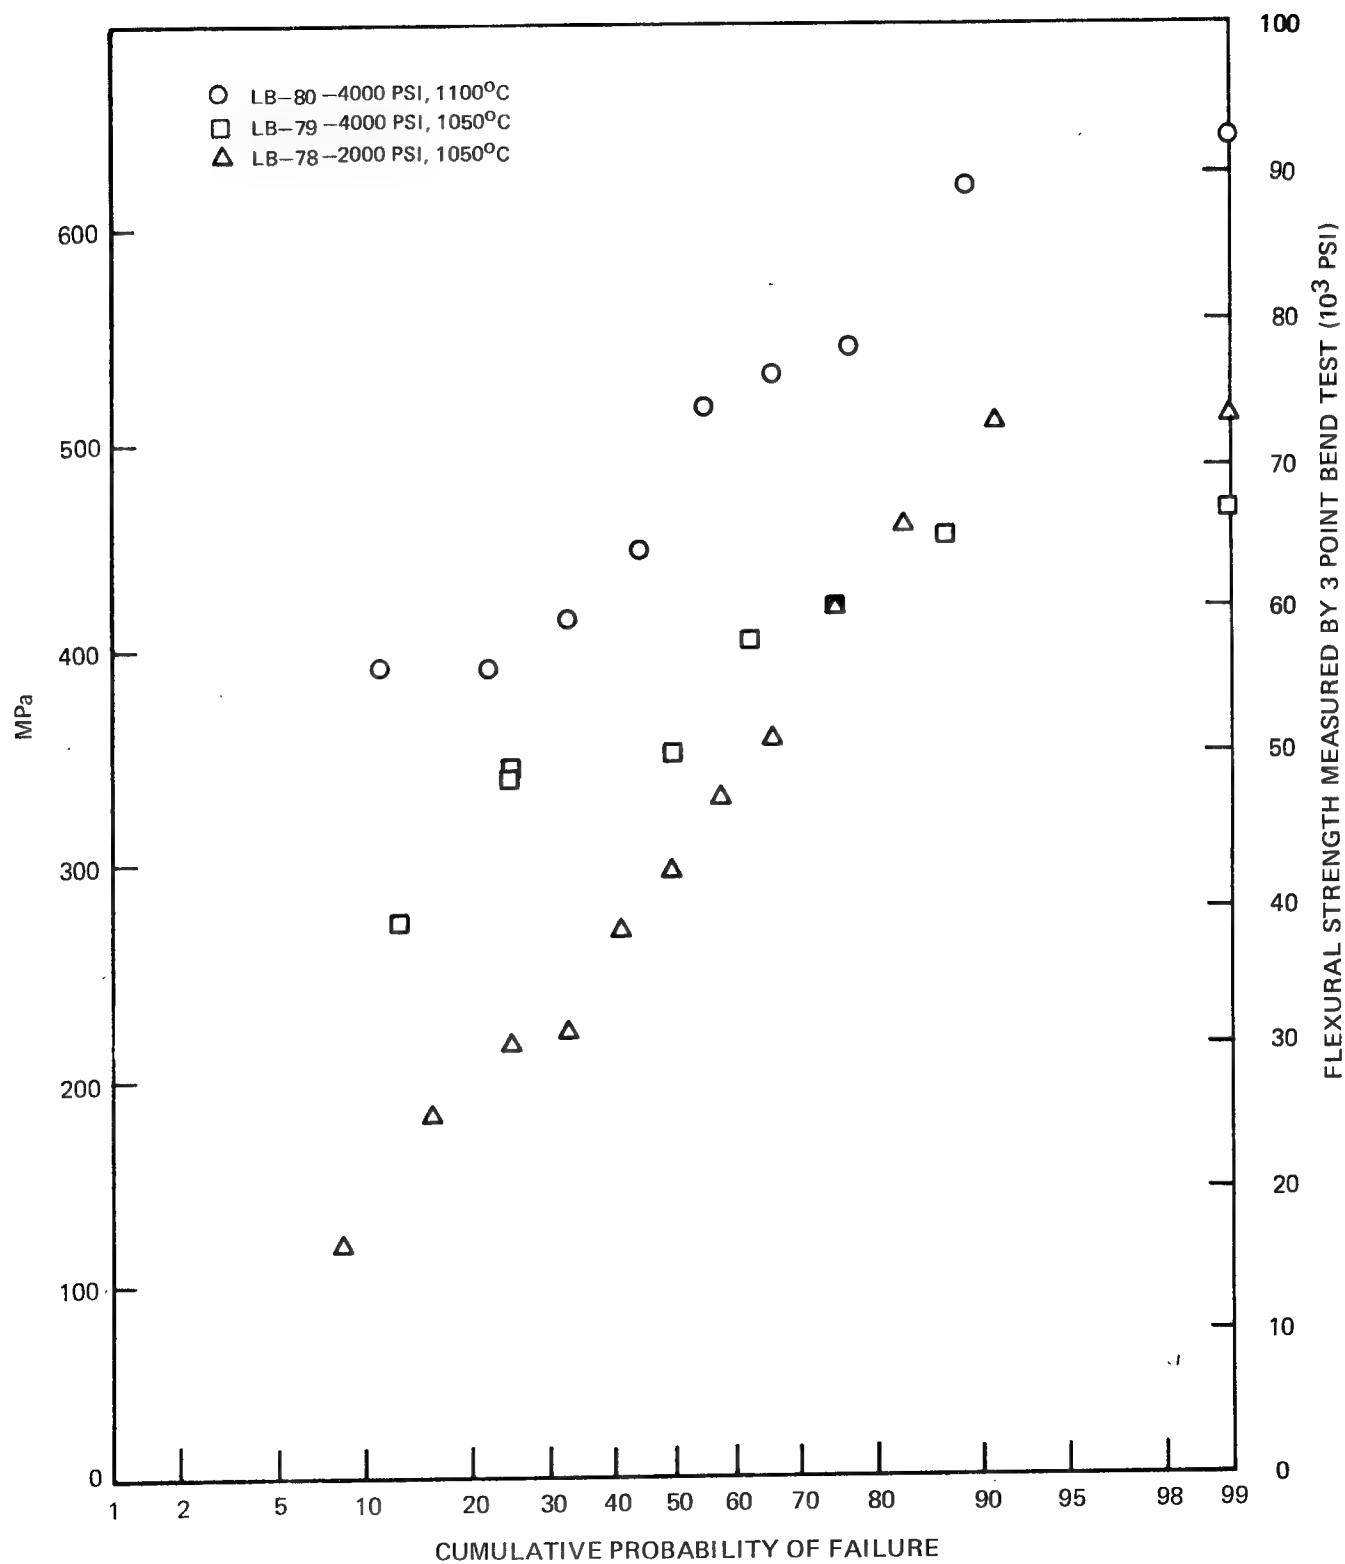


Table X

Choice of Graphite Fiber and Its Effect on Ultimate Three-Point  
Flexural Strength of Graphite Fiber-Glass Matrix Composite

| Sample<br>Number | Type of<br>Fiber | Fiber<br>Modulus<br>$\text{psixl0}^6$ | Fiber<br>Strength<br>$\text{psixl0}^3$ | Number<br>of<br>Fibers<br>in Tow | Glass | Three-Point<br>Flexural<br>Strength<br>MPa | $\text{psixl0}^3$ |
|------------------|------------------|---------------------------------------|--|----------------------------------|-------|--|-------------------|
| LB 135 RC        | Hercules         | 50.9                                  | 392                                    | 10,000                           | 7740  | 673  | 97.7              |
| CB               | HMS              | 351 GPa                               | 2703 MPa                               |                                  |       | 663  | 96.2              |
| LC               |                  |                                       |  |                                  |       | 705  | 102.0             |
| CC               |                  |                                       |  |                                  |       | 734  | 106.0             |
| TC               |                  |                                       |  |                                  |       | 640  | 92.9              |
| TR               |                  |                                       |  |                                  |       | 705  | 102.0             |
| TL               |                  |                                       |  |                                  |       | 733  | 106.0             |
| RL               |                  |                                       |  |                                  |       | 746  | 108.0             |
| RB               |                  |                                       |  |                                  |       | 614  | 89.0              |
| Average          |                  |                                       |  |                                  |       | 689  | 99.98             |
| LB 161 TR        | Thornel          | 33                                    | 385                                    | 1,000                            | 7740  | 504  | 73.1              |
| RC               | 300S             | 228 GPa                               | 2655 MPa                               |                                  |       | 397  | 57.6              |
| RB               |                  |                                       |  |                                  |       | 516  | 74.8              |
| TC               |                  |                                       |  |                                  |       | 474  | 68.8              |
| CC               |                  |                                       |  |                                  |       | 528  | 76.5              |
| CB               |                  |                                       |  |                                  |       | 556  | 80.6              |
| TL               |                  |                                       |  |                                  |       | 467  | 67.7              |
| LC               |                  |                                       |  |                                  |       | 522  | 75.7              |
| LB               |                  |                                       |  |                                  |       | 519  | 75.3              |
| Average          |                  |                                       |  |                                  |       | 498  | 72.23             |
| LB 148 1         | Hercules         | 37.2                                  | 410                                    | 10,000                           | 7740  | 338  | 49.0              |
| 2                | HTS              | 257 GPa                               | 2827 MPa                               |                                  |       | 408  | 59.2              |
| 3                |                  |                                       |  |                                  |       | 341  | 49.5              |
| 4                |                  |                                       |  |                                  |       | 357  | 51.7              |
| 5                |                  |                                       |  |                                  |       | 410  | 59.4              |
| 6                |                  |                                       |  |                                  |       | 389  | 56.4              |
| 7                |                  |                                       |  |                                  |       | 408  | 59.2              |
| 8                |                  |                                       |  |                                  |       | 379  | 54.9              |
| 9                |                  |                                       |  |                                  |       | 456  | 66.1              |
| 10               |                  |                                       |  |                                  |       | 354  | 51.4              |
| 11               |                  |                                       |  |                                  |       | 343  | 49.8              |
| 12               |                  |                                       |  |                                  |       | 407  | 59.1              |
| 13               |                  |                                       |  |                                  |       | 319  | 46.3              |
| 14               |                  |                                       |  |                                  |       | 297  | 43.0              |
| 15               |                  |                                       |  |                                  |       | 348  | 50.4              |
| Average          |                  |                                       |  |                                  |       | 370  | 53.7              |

Table X (cont'd)

| <u>Sample<br/>Number</u> | <u>Type of<br/>Fiber</u> | <u>Fiber<br/>Modulus<br/>psix10<sup>6</sup></u> | <u>Fiber<br/>Strength<br/>psix10<sup>3</sup></u> | <u>Number<br/>of<br/>Fibers<br/>in Tow</u> | <u>Glass</u> | <u>Three-Point<br/>Flexural<br/>Strength</u> |                           |
|--------------------------|--------------------------|---|--|--|--------------|--|---------------------------|
|                          |                          |   |  |  |              | <u>MPa</u>                                   | <u>psix10<sup>3</sup></u> |
| LB 97 L1                 | Celanese                 | 77.0  | 250  | 384  | 7740         | 399  | 57.8                      |
| L2                       | DG 102                   | 530 GPa   | 1724 MPa   |  |              | 411  | 59.6                      |
| L3                       |                          |   |  |  |              | 265  | 38.4                      |
| C1                       |                          |   |  |  |              | 339  | 49.1                      |
| C2                       |                          |   |  |  |              | 340  | 49.3                      |
| C3                       |                          |   |  |  |              | 293  | 42.5                      |
| R1                       |                          |   |  |  |              | 281  | 40.8                      |
| R2                       |                          |   |  |  |              | 362  | 52.5                      |
| R3                       |                          |   |  |  |              | 392  | 56.8                      |
| Average                  |                          |   |  |  |              | 342  | 49.6                      |



the fiber giving the next best result, i.e. Thornel 300 graphite fiber in 7740 glass. In Figs. 17-21 are shown typical optical micrographs of Thornel 300S in 7740 glass. As Figs. 17-19 show, the usual composites made with this material have a very high density of fiber but with a nonuniform distribution with some glass rich areas. This factor may account for the poor high temperature behavior of the Thornel 300 graphite fiber reinforced 7740 glass matrix shown in Table XI where it will be noted that the composite is degraded to about 50% of its original strength when heated in argon at 560°C for 4 hrs and subsequently tested at room temperature and to 25% of its original strength when heated in air for 4 hrs at 560°C. The data obtained for composites made with the Hercules HTS fiber are given in Table X and Fig. 22 as a function of test temperature.

#### 5. Effect of Matrix Composition

The effect of the glass matrix composition on the achieved properties of the graphite fiber reinforced glass matrix composite has received only preliminary study since the C.G.W. 7740 glass seems adequate for a composite whose use temperature, as stated by this contract, is 540°C or 1000°F. The choice of glass matrix composition is, however, important as seen in Table XIII where it is shown that the Hercules HMS graphite fiber used to reinforce a 7740 glass matrix has nearly twice the flexural strength of a Hercules HMS graphite fiber aluminosilicate (C.G.W. 1723) glass matrix.

#### 6. Comparison of Three and Four-Point Flexural Strengths

The effect of span-to-depth ratio on three-point flexural strength was evaluated, over a wide range (20 to 60). The data shown in Table XIV indicate the strength is not a function of the L/D ratio within this range.

The relationship of the three-point flexural strength for these graphite fiber reinforced glass composites to the four-point flexural strength was also evaluated as can be seen in Table XV.

#### 7. High Temperature Limitation on Processing

In Table XVI are shown thermodynamic predictions of reactions which could limit the temperature at which the graphite fiber-reinforced glass composite could be hot pressed. Since thermodynamic considerations merely assure that such reactions can take place and say nothing about the speed with which they occur, it is of interest to investigate the situation experimentally. In


THORNEL 300S GRAPHITE FIBER IN PYREX GLASS MATRIX TAPE—MAP OF CROSS-SECTION, 50X



200 $\mu$


FIG. 17

OPTICAL MICROGRAPHS OF THORNEL 300 FIBER IN C.G.W. 7740 GLASS MATRIX 200X

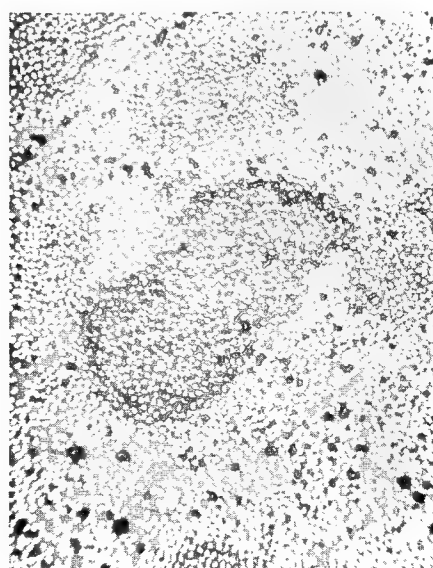


50μ

LB 79 -As-POLISHED UNFRACTURED SAMPLE

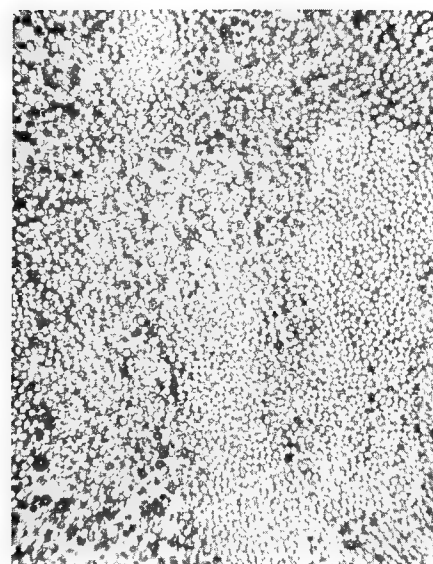

50μ


LB 80-CR-ETCHED-FRACTURED SAMPLE

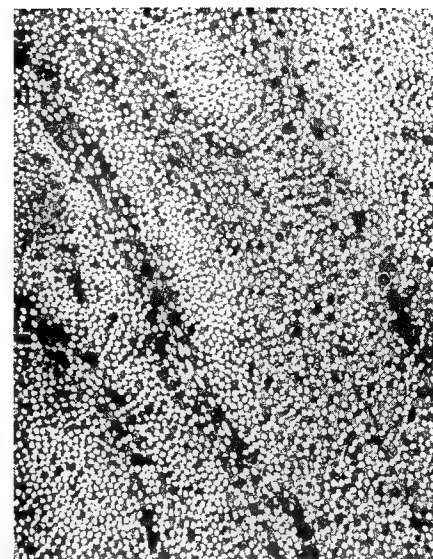

50μ

LB 81-ETCHED-UNFRACTURED SAMPLE

THORNEL 300S GRAPHITE FIBER-PYREX GLASS MATRIX CROSS-SECTION PERPENDICULAR TO  
FIBER DIRECTION

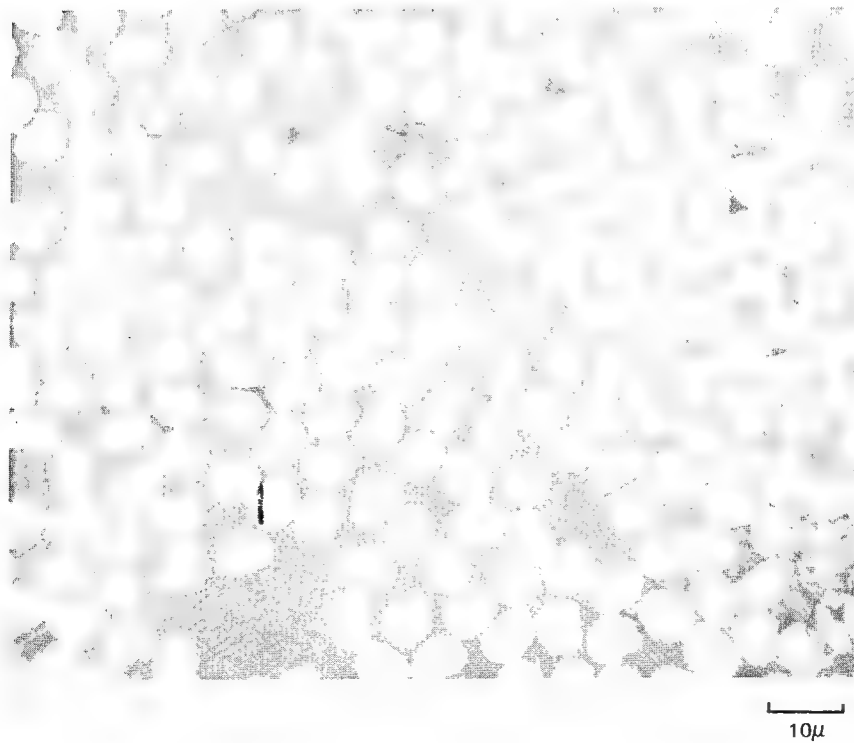

THORNEL 300S GRAPHITE FIBER 7740 GLASS MATRIX CROSS-SECTION PARALLEL TO FIBER  
DIRECTION



400 $\mu$



50 $\mu$

TAPE-MAP OF UNFRACTURED SAMPLE LB 81 THORNEL 300 FIBER C.G.W. 7740 GLASS MATRIX



200 $\mu$

Table XI

Elevated Temperature Exposure of Thornel 300S  
Graphite Fiber Reinforced 7740

| Specimen   | Exposure Conditions |              |                   | 20°C 3-Point<br>Bend Strength |                           | Average    |
|------------|---------------------|--------------|-------------------|-------------------------------|---------------------------|------------|
|            | <u>Time</u>         | <u>Temp.</u> | <u>Atmosphere</u> | <u>MPa</u>                    | <u>10<sup>3</sup> psi</u> |            |
| LB 163 TC  | 4 hrs               | 560°C        | Argon             | 212                           | 30.8                      | 249 (36.1) |
| RC         |                     |              |                   | 206                           | 29.9                      |            |
| RB         |                     |              |                   | 248                           | 36.0                      |            |
| CC         |                     |              |                   | 262                           | 38.0                      |            |
| TL         |                     |              |                   | 316                           | 45.9                      |            |
| LB 163 TR  |                     | none         |                   | 314                           | 45.5                      | 488 (70.8) |
| CB         |                     |              |                   | 501                           | 72.7                      |            |
| CL         |                     |              |                   | 563                           | 81.6                      |            |
| LB         |                     |              |                   | 574                           | 83.2                      |            |
| LB 162 TC* | 4 hrs               | 560°C        | Air               | 154                           | 22.3                      | 122 (17.7) |
| CC*        |                     |              |                   | 113                           | 16.4                      |            |
| LC*        |                     |              |                   | 112                           | 16.2                      |            |
| LB*        |                     |              |                   | 79                            | 11.4                      |            |
| RB*        |                     |              |                   | 152                           | 22.1                      |            |
| LB 162 TR  |                     | none         |                   | 451                           | 65.4                      | 499 (72.4) |
| RC         |                     |              |                   | 445                           | 64.6                      |            |
| CB         |                     |              |                   | 528                           | 76.6                      |            |
| TL         |                     |              |                   | 574                           | 83.3                      |            |

\*Fibers changed color to white as a result of air anneal

Table XII

Three-Point Bend Strength of Hercules HTS Fiber in C.G.W. 7740  
Glass Measured at Elevated Temperatures

| Sample No.             | Test Temperature<br>°C | 3-Point Flexural Strength |                       |
|------------------------|------------------------|---------------------------|-----------------------|
|                        |                        | MPa                       | psi x 10 <sup>3</sup> |
| LB 149 CC <sub>1</sub> | Room Temp.             | 352                       | 57.1                  |
| CC <sub>2</sub>        | Room Temp.             | 318                       | 46.2                  |
| BC                     | Room Temp.             | 290                       | 42.0                  |
| LB                     | Room Temp.             | 293                       | 42.5                  |
| TL                     | 550                    | 537                       | 77.9                  |
| LC <sub>1</sub>        | 550                    | 448                       | 65.0                  |
| LC <sub>2</sub>        | 600                    | 459                       | 66.6                  |
| TR                     | 600                    | 586                       | 85.0                  |
| RC <sub>1</sub>        | 650                    | 511                       | 74.1                  |
| RC <sub>2</sub>        | 650                    | 509                       | 73.8                  |
| RB                     | 700                    | 379                       | 54.9                  |
| TC                     | 700                    | 291                       | 42.2                  |



**FLEXURAL STRENGTH OF HERCULES HTS GRAPHITE FIBER REINFORCED  
7740 GLASS MATRIX COMPOSITE AS A FUNCTION OF TEST TEMPERATURE**

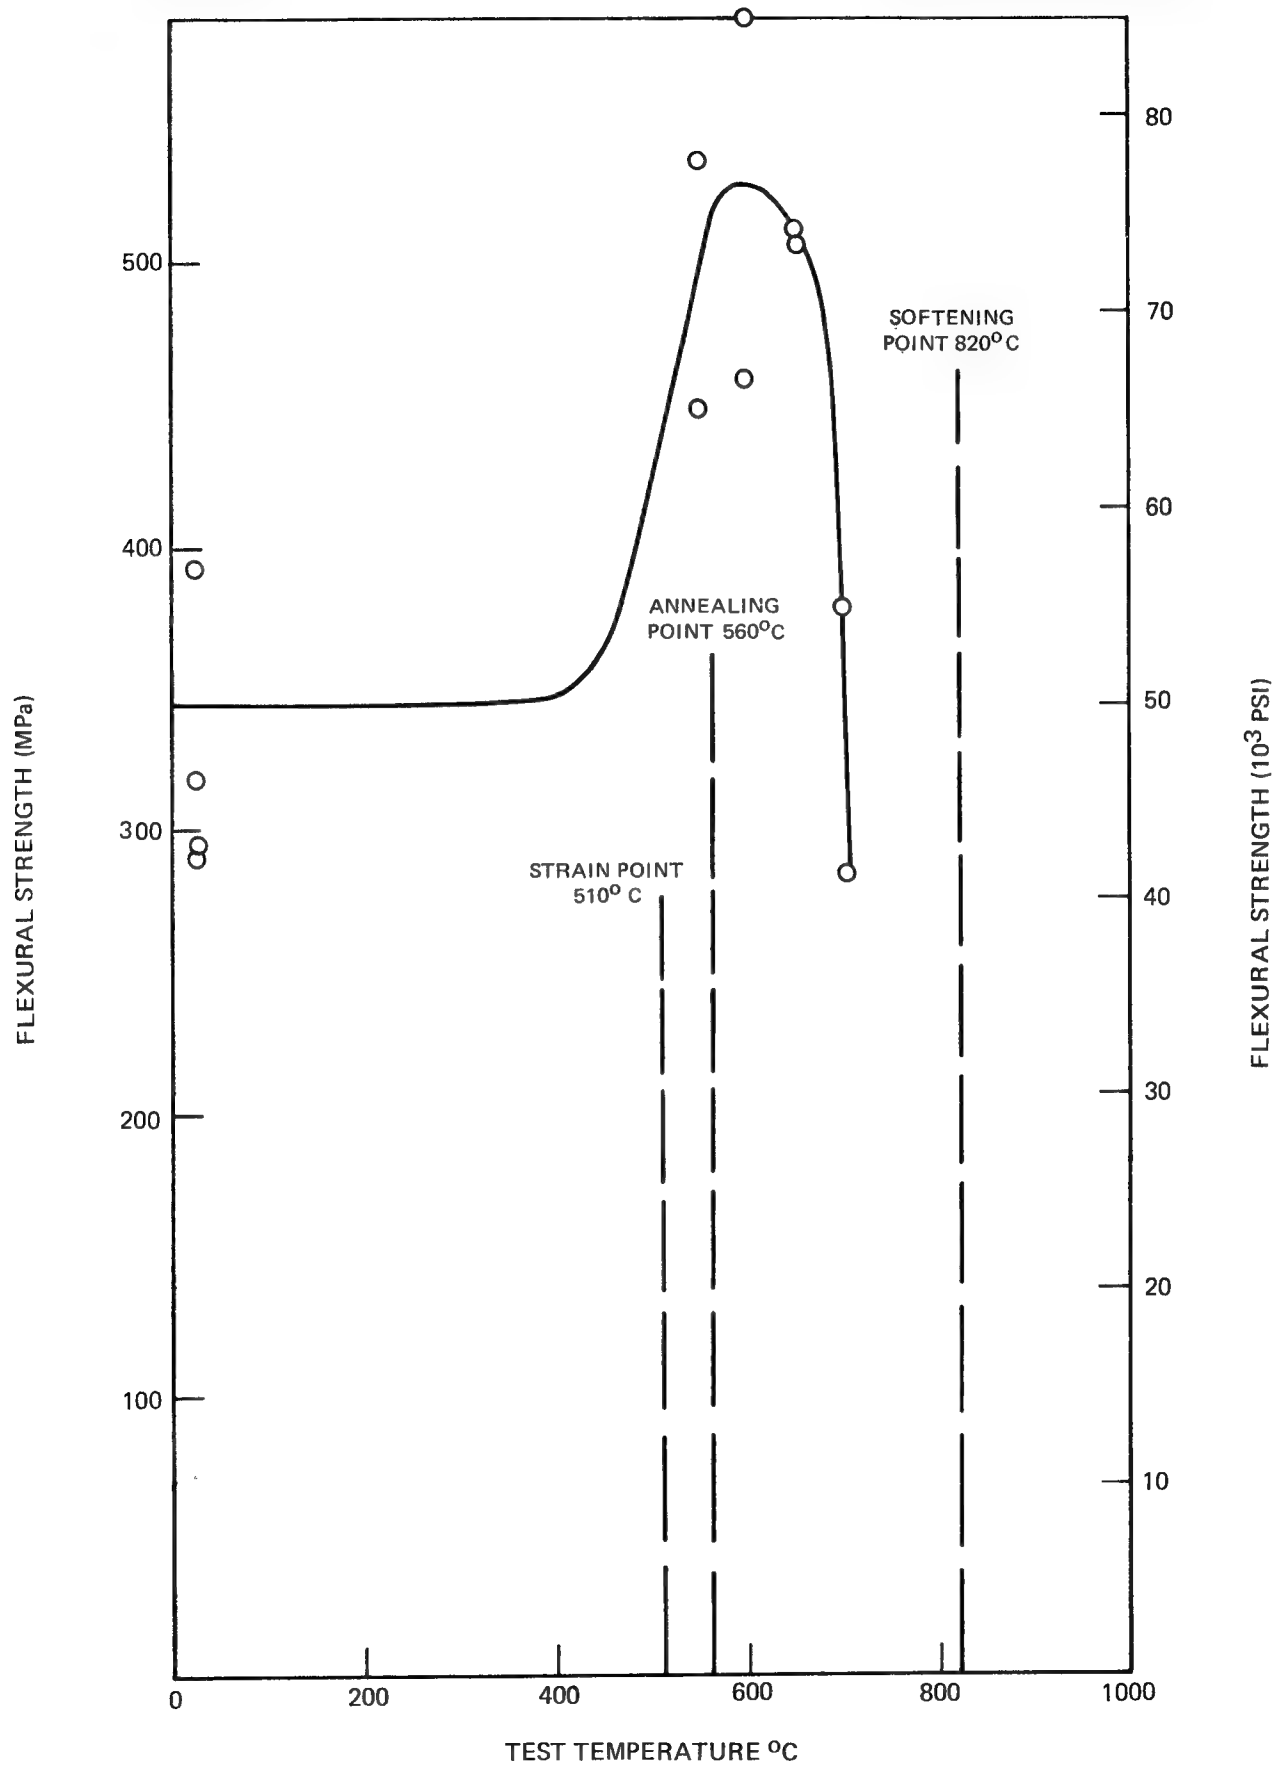


Table XIII

Preliminary Evidence That Choice of Glass Effects the Three-Point  
Flexural Strength of Graphite Fiber-Glass Matrix Composites

| <u>Sample<br/>Number</u> | <u>Type of<br/>Fiber</u> | <u>Type of<br/>Glass</u> | <u>Hot Pressing<br/>Conditions</u> |                    | <u>Three-Point<br/>Flexural Strength</u> |                             |
|--------------------------|--------------------------|--------------------------|------------------------------------|--------------------|--|-----------------------------|
|                          |                          |                          | <u>Temp. °C</u>                    | <u>Press.(psi)</u> | <u>MPa</u>                               | <u>psi x 10<sup>3</sup></u> |
| LB 135                   | RC                       | Hercules                 | 1100                               | 2000               | 673                                      | 97.7                        |
|                          | CB                       | HMS                      |                                    | 13.79 MPa          | 663                                      | 96.2                        |
|                          | LC                       | C.G.W.                   |                                    |                    | 705                                      | 102.0                       |
|                          | CC                       | 7740                     |                                    |                    | 734                                      | 106.0                       |
|                          | TC                       |                          |                                    |                    | 640                                      | 92.9                        |
|                          | TR                       |                          |                                    |                    | 705                                      | 102.0                       |
|                          | TL                       |                          |                                    |                    | 733                                      | 106.0                       |
|                          | RL                       |                          |                                    |                    | 746                                      | 108.0                       |
|                          | RB                       |                          |                                    |                    | 614                                      | 89.0                        |
|                          | Average                  |                          |                                    |                    | 689                                      | 99.98                       |
| LB 172                   | TR                       | Hercules                 | 1120                               | 2000               | 289                                      | 41.9                        |
|                          | RC <sub>1</sub>          | HMS                      |                                    | 13.79 MPa          | 337                                      | 48.9                        |
|                          | RC <sub>2</sub>          | C.G.W.                   |                                    |                    | 324                                      | 47.1                        |
|                          | RC <sub>3</sub>          | 1723                     |                                    |                    | 277                                      | 40.2                        |
|                          | TC                       |                          |                                    |                    | 411                                      | 59.6                        |
|                          | CC <sub>1</sub>          |                          |                                    |                    | 562                                      | 81.6                        |
|                          | CC <sub>2</sub>          |                          |                                    |                    | not tested                               |                             |
|                          | CB                       |                          |                                    |                    | 296                                      | 43.0                        |
|                          | TL                       |                          |                                    |                    | 408                                      | 59.1                        |
|                          | LC <sub>1</sub>          |                          |                                    |                    | 353                                      | 51.1                        |
|                          | LC <sub>2</sub>          |                          |                                    |                    | 299                                      | 43.4                        |
|                          | LB                       |                          |                                    |                    | 371                                      | 53.8                        |
|                          | Average                  |                          |                                    |                    | 357                                      | 51.8                        |

Table XIV

Three Point Flexural Strength Values for HTS Graphite in  
Pyrex Glass Matrix Evaluated at Three L/D Ratios  
LB 148

| Specimen | Span<br><u>in.</u> | Thickness<br><u>in.</u> | L/D   | Three Point<br>Flexural Strength |             | Average<br><u>kpsi</u> |
|----------|--------------------|-------------------------|-------|----------------------------------|-------------|------------------------|
|          |                    |                         |       | <u>MPa</u>                       | <u>kpsi</u> |                        |
| LB 148   |                    |                         |       |                                  |             |                        |
| 1        | 1.5<br>↓           | 0.025                   | 60    | 338                              | 49.0        |                        |
| 2        |                    | 0.025                   | 60    | 408                              | 59.2        |                        |
| 3        |                    | 0.024                   | 62.5  | 341                              | 49.5        |                        |
| 4        |                    | 0.029                   | 51.7  | 357                              | 51.7        |                        |
| 5        |                    | 0.026                   | 57.7  | 410                              | 59.4        | 53.8                   |
| 6        |                    | 0.064                   | 23.4  | 389                              | 56.4        |                        |
| 7        |                    | 0.060                   | 25    | 408                              | 59.2        |                        |
| 8        |                    | 0.056                   | 26.8  | 379                              | 54.9        |                        |
| 9        |                    | 0.062                   | 24.2  | 456                              | 66.1        |                        |
| 10       |                    | 0.062                   | 24.2  | 354                              | 51.4        | 57.6                   |
| 11       |                    | 0.048                   | 31.25 | 343                              | 49.8        |                        |
| 12       |                    | 0.048                   | 31.25 | 407                              | 59.1        |                        |
| 13       |                    | 0.048                   | 31.25 | 319                              | 46.3        |                        |
| 14       |                    | 0.049                   | 30.6  | 297                              | 43.0        |                        |
| 15       |                    | 0.048                   | 31.25 | 348                              | 50.4        | 49.7                   |


Table XV

Comparison of 3-Point Bend and 4-Point Bend Test  
Data for Several Graphite Fiber-Glass Composites

| <u>Specimen</u>   | 3-Point Flexural Strength |            | Strain Gaged<br>4-Point Flexural Strength |            |
|-------------------|---------------------------|------------|---|------------|
|                   | <u>MPa</u>                | <u>psi</u> | <u>MPa</u>                                | <u>psi</u> |
| LB 136 - 3 tests  | 648                       | 94,000     | 517                                       | 75,000     |
| - 6 tests         |                           |            |   |            |
| LB 135F - 9 tests | 977                       | 142,000    | 848                                       | 127,300    |
| LB 135G - 9 tests |                           |            |   |            |
| LB 97 - 9 tests   | 342                       | 49,600     | 309                                       | 44,800     |
| LB 97D - 9 tests  |                           |            |   |            |

Table XVI

Possible Reactions Between  $\text{SiO}_2$  and Carbon  
at Temperatures Above  $1673^\circ\text{K}^*$

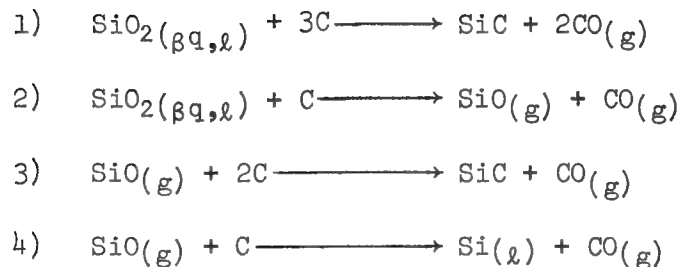

Based on 1st and most important reaction, equilibrium vapors pressures are

| Temp ( $^\circ\text{K}$ ) | Equilibrium $P_{\text{CO}}(\text{atm})$ |
|---------------------------|---|
| 1200                      | $1.02 \times 10^{-4}$                   |
| 1400                      | $6.98 \times 10^{-3}$                   |
| 1600                      | $1.62 \times 10^{-1}$                   |
| 1800                      | 1.84                                    |
| 2000                      | 12.4                                    |

\*Data taken from Bacon, James F., Alex A. Hasapis and James W. Wholley, Jr.,  
Physics & Chemistry of Glasses, Vol. 1, No. 3, June 1960, pp 90-98.

Table XVII the finished weight of the hot-pressed sample is compared with its initial weight as a function of temperature for six Celanese DG-102 graphite fibers in Vycor (C.G.W. 7913) hot-pressed at very high temperatures. The table shows that despite the thermodynamic predictions of reactions at temperatures as low as 1400°C, actual hot pressing operations can be carried out at temperatures of 1600°C for the usual 1 hr dwell time at temperature. Above 1600°C, however, the reactions between glass and fiber make operations impractical. In considering these results it should be noted that the Celanese DG-102 graphite is the fiber with greatest environmental stability and the Vycor glass (C.G.W. 7913) a 96% SiO<sub>2</sub>, 3% Al<sub>2</sub>O<sub>3</sub> glass is a highly stable glass designed for use at high temperatures.

#### 8. Fabrication in New Hot Press


Samples LB 97E,F,G,H,I; LB 135F,G,H,I,J,K,L,M,N,O; LB 148E and F; and LB 161 E and F have been prepared in a new Centorr Hot Press. This equipment is shown in Fig. 23. It permits the fabrication of specimens as large as 6 in. x 4 in. x 1 in. (3 in. thick before pressing) formed with a load up to 60 tons and temperatures of 2100°C in a vacuum of 10<sup>-6</sup> torr or under argon. This press is double acting in place of the single acting presses used early on this program. With this new press samples were obtained that had greatly improved bending strengths.

Table XVII

Loss in Weight of Celanese DG-102 Graphite Fiber Vycor Glass  
Composites as a Function of Temperature

| Sample | Weight of All<br>Material<br>Before Hot Pressing<br><u>gms</u> | Finished<br>Weight of<br>Sample After<br>Hot Pressing 1 hr<br><u>gms</u> | Temperature at<br>Which Hot Pressing<br>Was Performed<br><u>°C</u> |
|--------|--|--|--|
| LB 107 | 22.55  | 22.35  | 1600   |
| LB 108 | 22.55  | 15.92  | 1650   |
| LB 109 | 22.55  | 10.64  | 1700   |
| LB 110 | 22.55  | 10.89  | 1750   |
| LB 111 | 22.55  | 9.01   | 1800   |
| LB 112 | 22.55  | 7.14   | 1850   |

NEW CENTORR HOT PRESS AT UTRC

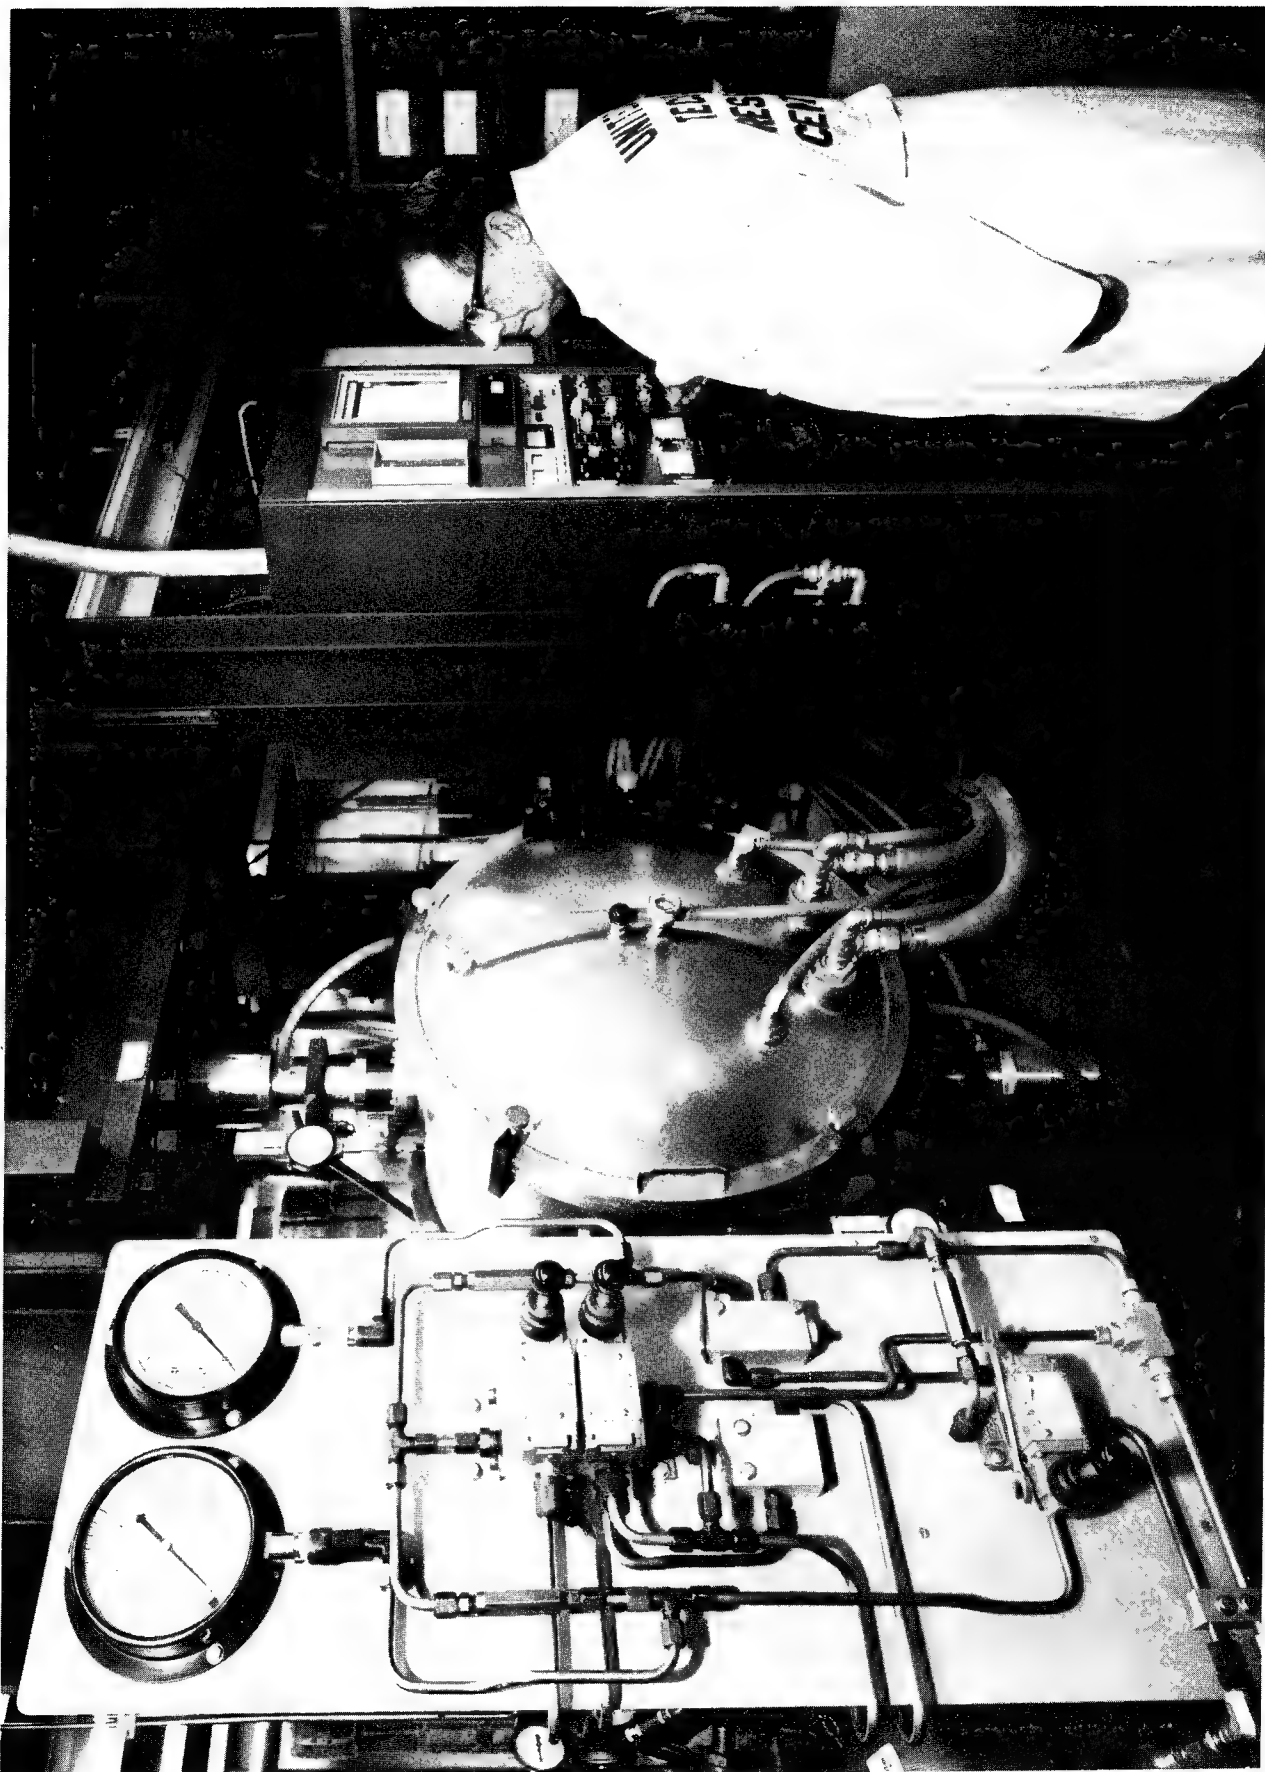



## V. PROPERTIES OF TWO SELECTED SYSTEMS

The two most completely characterized graphite fiber reinforced glass matrix composites developed to date are the Hercules HMS graphite fiber in 7740 and the Celanese DG-102 graphite fiber in 7740 composites. The properties obtained thus far for the HMS graphite composites are as follows. An average three-point flexural strength of 977 MPa or 142,000 psi and an average four-point flexural strength (with strain gages) of 848 MPa or 127,300 psi have been measured. These composites have an average modulus of 200 to 206 GPa or 29 to 30 million psi, and a use temperature of 600°C or 1112°F as judged by the fact that the flexural strength in argon increases as the temperature increases from room temperature to 560°C. Very limited thermal cycling and fatigue tests with loads up to 80% UTS, 100 cycles only, show no deterioration in properties for these composites. But the HMS graphite fiber 7740 glass composites do fall to 72% of room temperature strength when heated in air at 560°C for 4 hrs.

On the other hand, the second type of composite which the first year's research has shown to be of major interest is that consisting of Celanese DG-102 fibers reinforcing a 7740 glass matrix. While it is true that at this time the Celanese DG-102 fiber composite has a RT three-point flexural strength of only 342 MPa or 49,600 psi and a four-point flexural strength (with strain gages) of 309 MPa or 49,800 psi it does have a much higher modulus of 303 GPa or 44 million psi. The Celanese DG-102 fiber composite maintains these properties even when heated in air for 4 hrs at 560°C. It is the purpose of this section to examine the basis for these statements in detail.

## A. Composites of Hercules HMS Graphite Fiber and 7740 Glass

## 1. Microstructure

The microstructure of a typical high strength HMS graphite fiber in 7740 glass composite is shown as an optical tape-map of the entire cross section of a test specimen in Fig. 24 and at higher magnification in Fig. 25. The almost unbelievable high density of fiber packing in these samples is immediately visible together with the great uniformity of fiber distribution. Yet, despite the high fiber density the micros lead to the conclusion that each fiber is still completely surrounded by glass with only a few fibers in actual contact with one another. It is believed that this achievement of higher fiber density accounts in part for the strength of these composites.

OPTICAL TAPE MAP LB135F HERCULES HMS GRAPHITE IN 7740

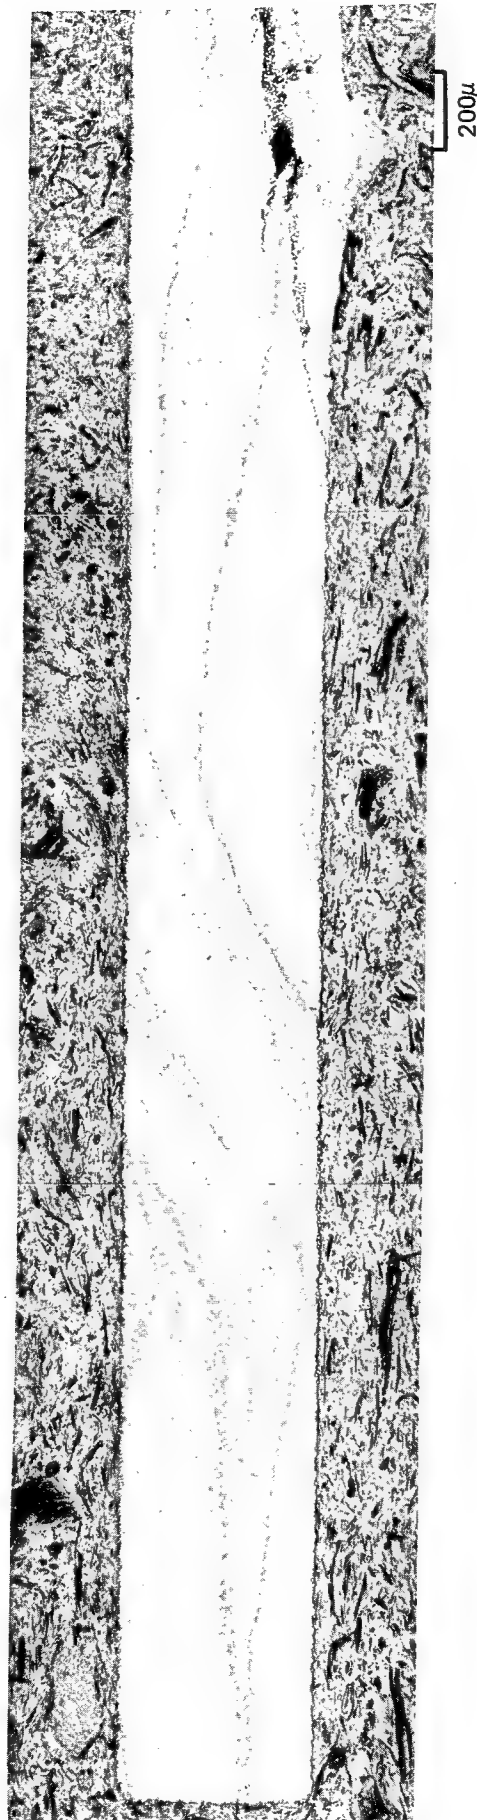


FIG. 24

TYPICAL MICROGRAPHS LB135F HERCULES HMS GRAPHITE FIBER IN 7740

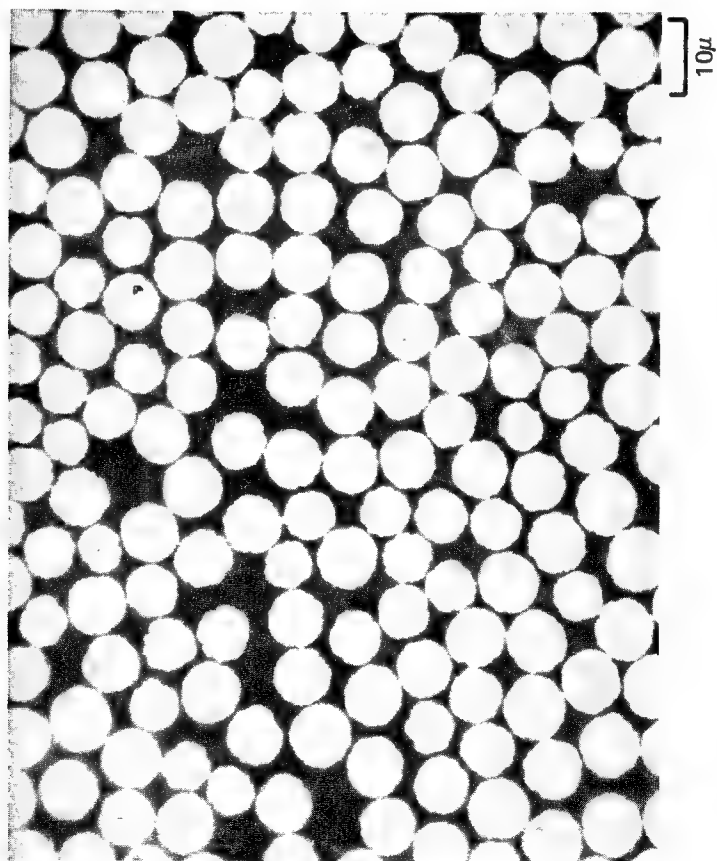


FIG. 25

## 2. Flexural Strength

The three-point flexural strength of the best HMS graphite fiber reinforced Pyrex composite made in the UTRC press originally used for this work is shown in Table XVIII and directly below the flexural strength of a similar composite made in the new Centorr press at a slightly higher temperature. While both sets of data show the very high flexural strengths now customarily to be associated with this type of composite, the difference between the two sets of data must be ascribed to factors as yet poorly understood. For example, the new Centorr press is double acting instead of the single action of the press originally used, the later samples are made in new and more tightly fitting dies, the test specimens from the samples were cut by different technicians and on different grinding and cutting equipment, and the two samples were made from different tapes.



However, not only are both samples of Table XVIII high in flexural strength, they also show small standard deviations or a very small spread in test values as can be seen from the plots on probability paper shown in Figs. 26 and 27. Since the linearity of these plots suggests a Gaussian distribution of flexural strengths with small standard deviations, these materials are unique among most brittle materials and can be employed by the designer with a high degree of confidence.

In Table XIX the four-point strain-gaged flexural strength is shown for the second specimen of Hercules HMS graphite fiber reinforced 7740 produced in the new press. The average four-point flexural strength of 876 MPa (127,000 psi) completely corroborated the three-point flexural data reported in Table XVIII for sample LB 135F. The fact that strain gages were used in this measurement as shown in Table XIX also enables one to compute accurate moduli values for this sample and these average 194 GPa or 28.2 million psi. Using the rule of mixtures this would correspond to an approximate fiber content of 47% by volume. The data of Table XIX illustrate that, as might be expected due to the larger volume of specimens experiencing maximum stress in four-point bend, the composite strength is lower for the four-point test than for the three-point test. The average strength of 883 MPa (128,000 psi) is still quite high and failure strains up to 0.42% were recorded.

Typical load deflection traces for two specimens taken from another hot pressed HMS graphite fiber in Pyrex sample are shown in Fig. 28. Both totally linear and combined linear - nonlinear deflections were exhibited; however, in all cases specimens did not fracture completely but instead cracks were diverted in the interior of the specimen so that failed specimens remained visibly intact after test. The load strain curves for four-point bend tests on a second HMS fiber Pyrex glass sample are shown in Fig. 29 and represent the two types of


Table XVIII

## Flexural Strength of HMS Reinforced 7740

| Sample<br>Number | Thickness<br>in. | Hot Pressing<br>Temperature<br>°C | Type of<br>Load Curve  | Three-Point<br>Flexural Strength |                       |       |
|------------------|------------------|-----------------------------------|--|----------------------------------|-----------------------|-------|
|                  |                  |                                   |  | MPa                              | psi x 10 <sup>3</sup> |       |
| LB 135 RC        | 0.060            | 1100                              |    | 673                              | 97.7                  |       |
|                  | CB               |                                   |  | 0.056                            | 663                   | 96.2  |
|                  | LC               |                                   |  | 0.059                            | 705                   | 102.0 |
|                  | CC               |                                   |  | 0.049                            | 734                   | 106.0 |
|                  | TC               |                                   |  | 0.032                            | 640                   | 92.9  |
|                  | TR               |                                   |  | 0.033                            | 705                   | 102.0 |
|                  | TL               |                                   |  | 0.034                            | 733                   | 106.0 |
|                  | LB               |                                   |  | 0.033                            | 746                   | 108.0 |
|                  | RB               |                                   |  | 0.054                            | 614                   | 89.0  |
| Average          |                  |                                   |  | 689                              | 99.98                 |       |
| LB 135FRC        | 0.059            | 1200                              |  | 1070                             | 155.0                 |       |
|                  | CB               |                                   |  | 0.059                            | 1010                  | 146.0 |
|                  | LC               |                                   |  | 0.068                            | 1050                  | 152.0 |
|                  | CC               |                                   |  | 0.059                            | 1140                  | 165.0 |
|                  | TC               |                                   |  | 0.060                            | 903                   | 131.0 |
|                  | TR               |                                   |  | 0.062                            | 946                   | 137.0 |
|                  | TL               |                                   |  | 0.063                            | 698                   | 101.0 |
|                  | LB               |                                   |  | 0.060                            | 1050                  | 152.0 |
|                  | RB               |                                   |  | 0.061                            | 983                   | 143.0 |
| Average          |                  |                                   |  | 977                              | 142.0                 |       |

## HERCULES HMS-10K REINFORCED 7740

SPECIMEN LB135-F

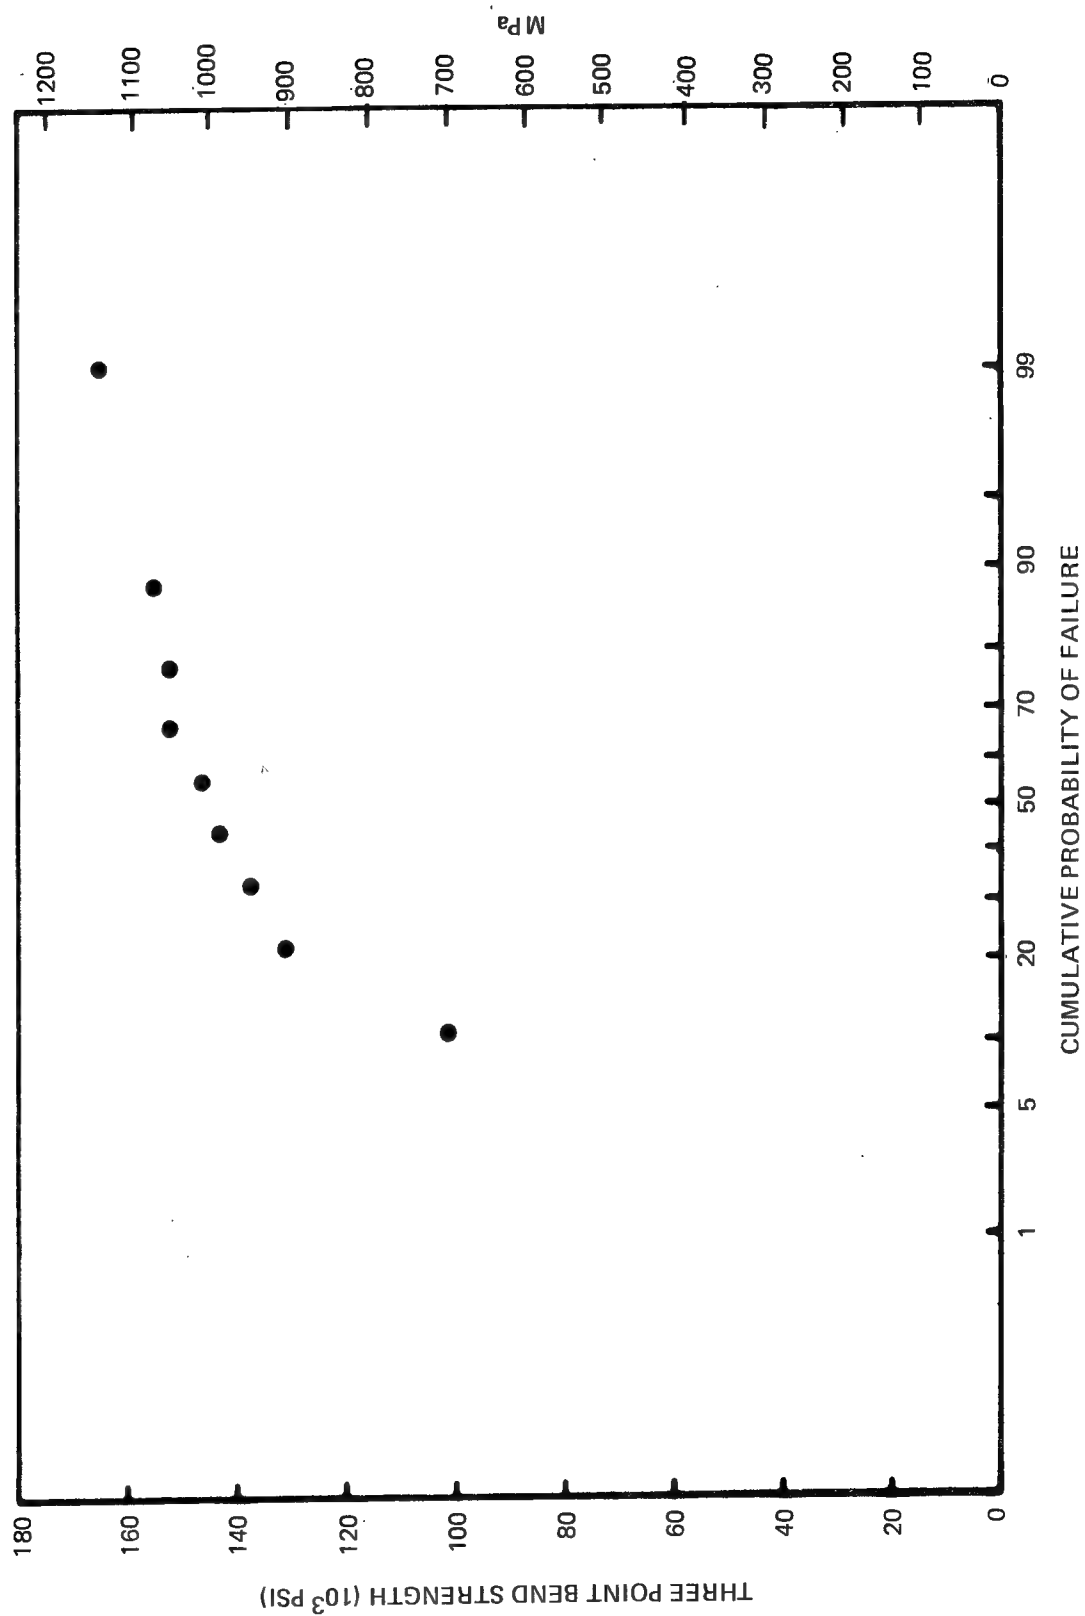

# THREE POINT BEND STRENGTH OF SPECIMENS TESTED AT 22°C

LB-135  
HERCULES HMS-10K REINFORCED 7740

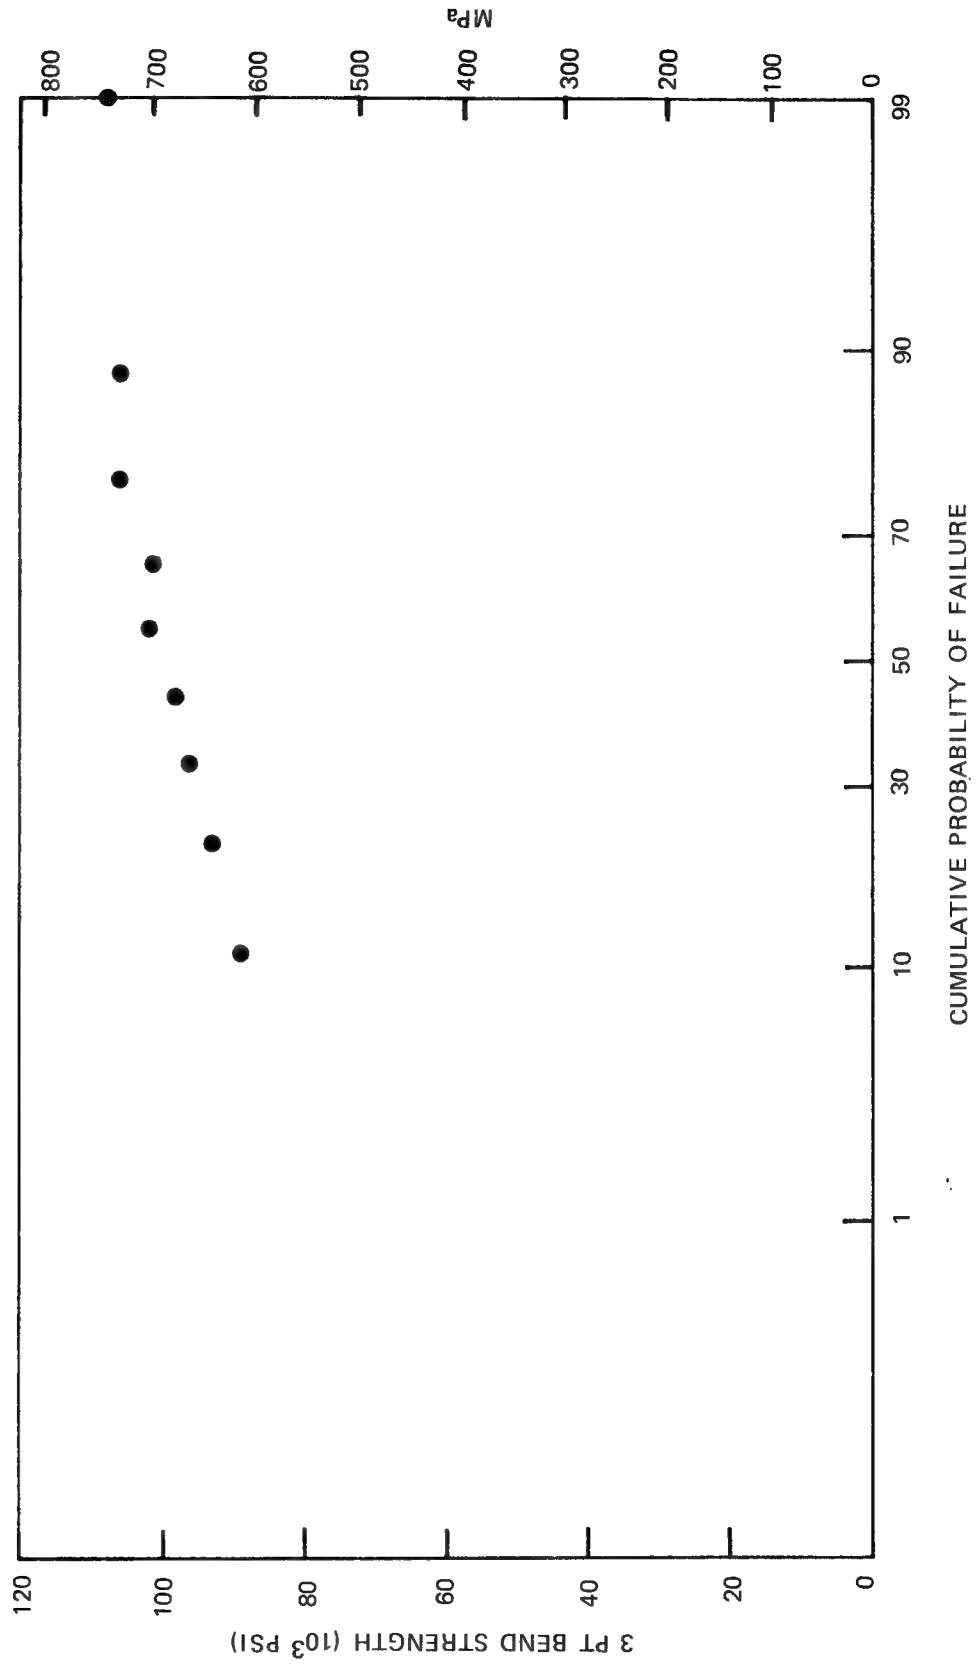


Table XIX

Flexural Properties  
HMS Reinforced 7740 Sample LB 135G

| 4-Point Bend Strength |                           | Elastic Modulus |                           | Strain to Failure              |
|-----------------------|---------------------------|-----------------|---------------------------|--------------------------------|
| <u>MPa</u>            | <u>10<sup>3</sup> psi</u> | <u>GPa</u>      | <u>10<sup>6</sup> psi</u> | <u><math>\epsilon_f</math></u> |
| 896                   | 130                       | 185             | 26.8                      | 0.485                          |
| 938                   | 136                       | 196             | 28.5                      | 0.477                          |
| 800                   | 116                       | 201             | 29.2                      | 0.397                          |
| 876                   | 127                       | 194             | 28.2                      | 0.453                          |
| 878                   | 127                       |                 |                           |                                |



# LOAD-DEFLECTION TRACES FOR THE 3-PT BEND TESTS ON HERCULES HMS-10K REINFORCED 7740


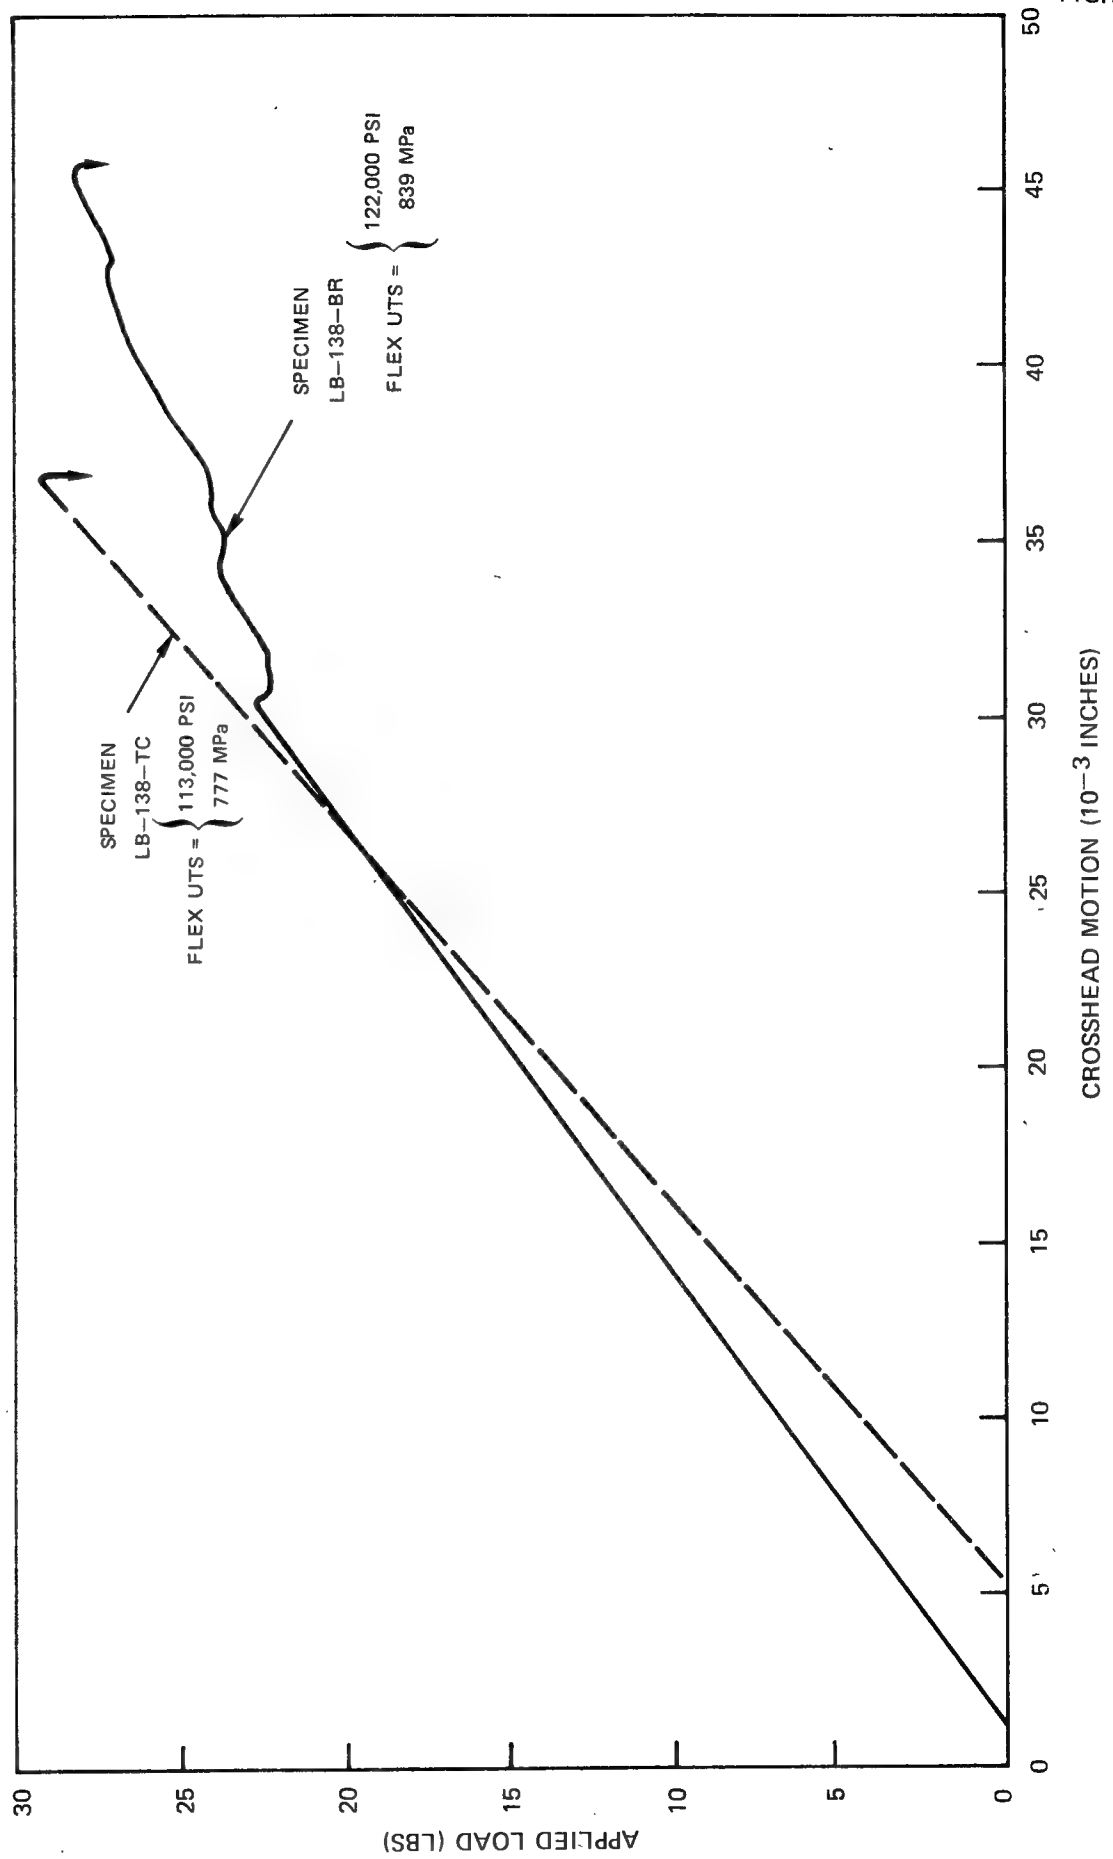


FIG. 28

LOAD-STRAIN TRACES FOR THE 4 PT BEND TESTS ON  
STRAIN GAUGED HERCULES HMS-10K REINFORCED 7740

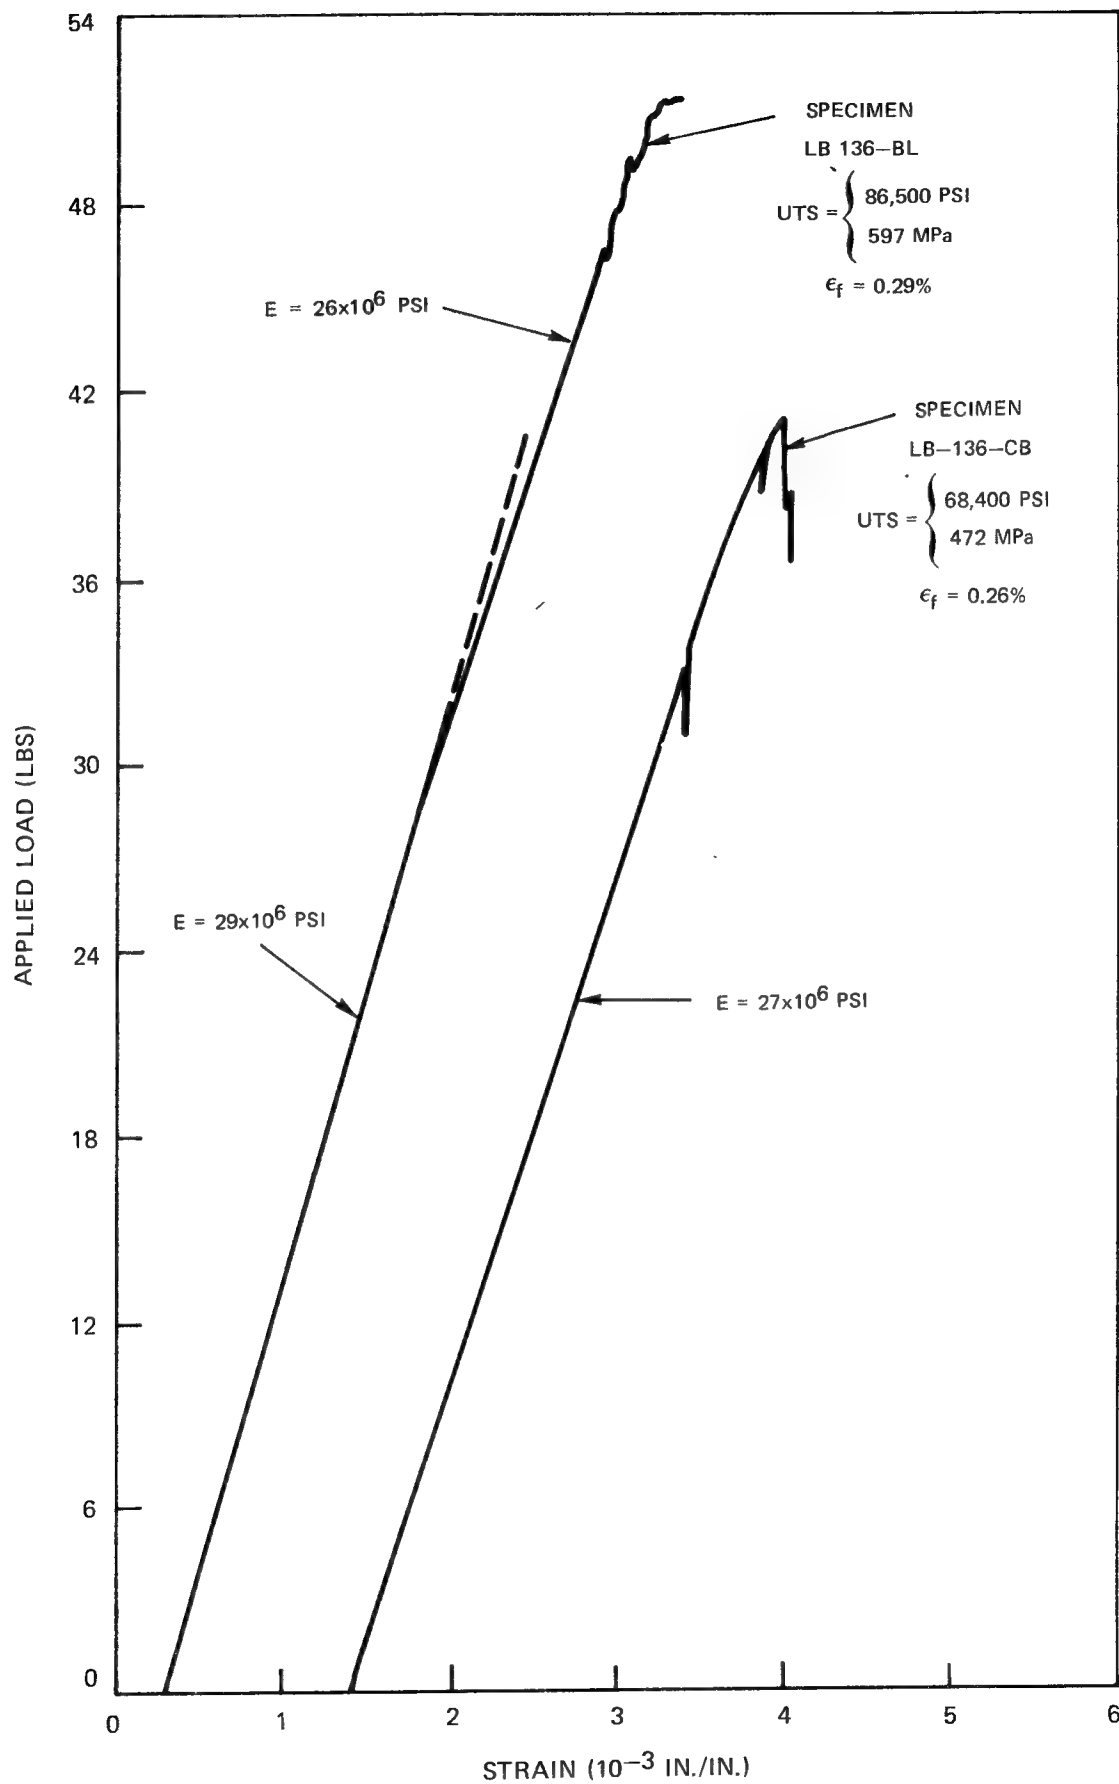

behavior observed. In the case of specimen BL, a nearly bilinear curve was obtained with a secondary elastic modulus  $26 \times 10^6$  psi as compared to the initial value of  $29 \times 10^6$  psi. This type of behavior in composites has often been associated with a transition from elastic-elastic to elastic-plastic regions of fiber-matrix behavior; however, for the current system this transition is unlikely and the operative mechanism is not known. It could be related to some unbonding or matrix fracture mode or it could also be due to some structural defect initiated failure. In contrast, specimen CB demonstrated a linear load-strain trace to failure. It should be noted, however, that there were three major interruptions in this loading curve which resulted in the load dropping off and then recovering. These are indicative of some structural changes in the specimen at regions removed from the strain gage, and thus if viewed from the point of a load vs crosshead displacement curve this specimen would have exhibited a curve like that of specimen BR in Fig. 28. In the four-point test, as well as the three-point test, this material is able to blunt incipient fractures such that the overall specimen can continue to bear load. Also, as in the case of three point bend, all specimens were visibly still intact after fracture, i.e. the cracks were not able to propagate through the whole specimen.

### 3. Effect of Test Atmosphere on Bend Strength

The environmental stability of this system was also evaluated by exposure to air and argon at  $560^\circ\text{C}$ . The data, Table XX, indicate some degradation due to exposure to air. No visible material change could be detected; however, in contrast to the Celanese reinforced 7740 composite, it should be recalled that in this system the fiber does not bond as tightly to the matrix and thus may not be as well protected by the glass. In addition, the higher modulus Celanese fiber, due to its crystallographic orientation, is more oxidation resistant than the somewhat lower modulus Hercules fiber.

### 4. Comparison of Elastic Modulus

The elastic modulus for HMS reinforced 7740 is compared with values of  $E_{11}$  characteristic of other composite systems in Table XXI. The specific modulus comparison given in the last column indicates the superiority of the glass matrix composite.

### 5. High Temperature Flexural Strength

Composite specimens were tested in three-point bend over a series of temperatures up to  $700^\circ\text{C}$  in argon. The resultant data are presented in Fig. 30 and Table XXII. The average strength of 120,000 psi at RT (825 MPa) is higher at  $600^\circ\text{C}$ , i.e. 175,000 psi (1213 MPa), and only at  $700^\circ\text{C}$  is the deformation of the

Table XX

Elevated Temperature Exposure of Hercules HMS-10K  
Graphite Reinforced 7740

| <u>Specimen</u> | <u>Exposure Conditions</u> |       |        | 10 <sup>3</sup> psi |
|-----------------|----------------------------|-------|--------|---------------------|
|                 | Time                       | Temp. | Atmos. |                     |
| LB-138          | 4 hrs                      | 560°C | Argon  | 78.3                |
|                 |                            |       |        | 82.3                |
|                 |                            |       |        | 86.7                |
|                 |                            |       |        | <u>113.0</u>        |
|                 |                            |       |        | 90.1 Avg.           |
| LB-138          |                            | None  |        | 69.6                |
|                 |                            |       |        | 81.1                |
|                 |                            |       |        | 111.0               |
|                 |                            |       |        | <u>122.0</u>        |
|                 |                            |       |        | 95.9 Avg.           |
| LB-137          | 4 hrs                      | 560°C | Air    | 62.1                |
|                 |                            |       |        | 67.6                |
|                 |                            |       |        | 70.2                |
|                 |                            |       |        | <u>72.1</u>         |
|                 |                            |       |        | 68.0 Avg.           |
| LB-137          |                            | None  |        | 79.9                |
|                 |                            |       |        | 91.6                |
|                 |                            |       |        | 92.3                |
|                 |                            |       |        | 99.1                |
|                 |                            |       |        | <u>106.5</u>        |
|                 |                            |       |        | 93.9 Avg.           |

Table XXI

## Room Temperature Elastic Modulus Comparison

| System with<br>Calculated<br>Fiber Contents | Density<br>$\rho$         |                            | Elastic Modulus<br>$E_{11}$ |                    | $E_{11}/\rho$<br>$10^8/\text{psi}/\text{lb}/\text{in.}^3$ |
|---|---------------------------|----------------------------|-----------------------------|--------------------|---|
|   | $(\text{gm}/\text{cm}^3)$ | $(\text{lb}/\text{in.}^3)$ | GPa                         | $10^6 \text{ psi}$ |   |
| 50 v/o<br>Celanese<br>DG-102-<br>7740       | 2.02                      | 0.072                      | 296                         | 43                 | 5.94  |
| 50 v/o<br>HMS-7740                          | 1.98                      | 0.071                      | 193                         | 28                 | 3.94  |
| 42 v/o<br>T50-A1                            | 2.30                      | 0.083                      | 207                         | 30                 | 3.61  |
| 50 v/o<br>B-A1                              | 2.70                      | 0.097                      | 227                         | 33                 | 3.40  |
| 43 v/o<br>B-Ti                              | 3.70                      | 0.133                      | 234                         | 34                 | 2.56  |

FLEXURAL STRENGTH OF HERCULES HMS-10K FIBER REINFORCED 7740 GLASS  
AS A FUNCTION OF TEST TEMPERATURE

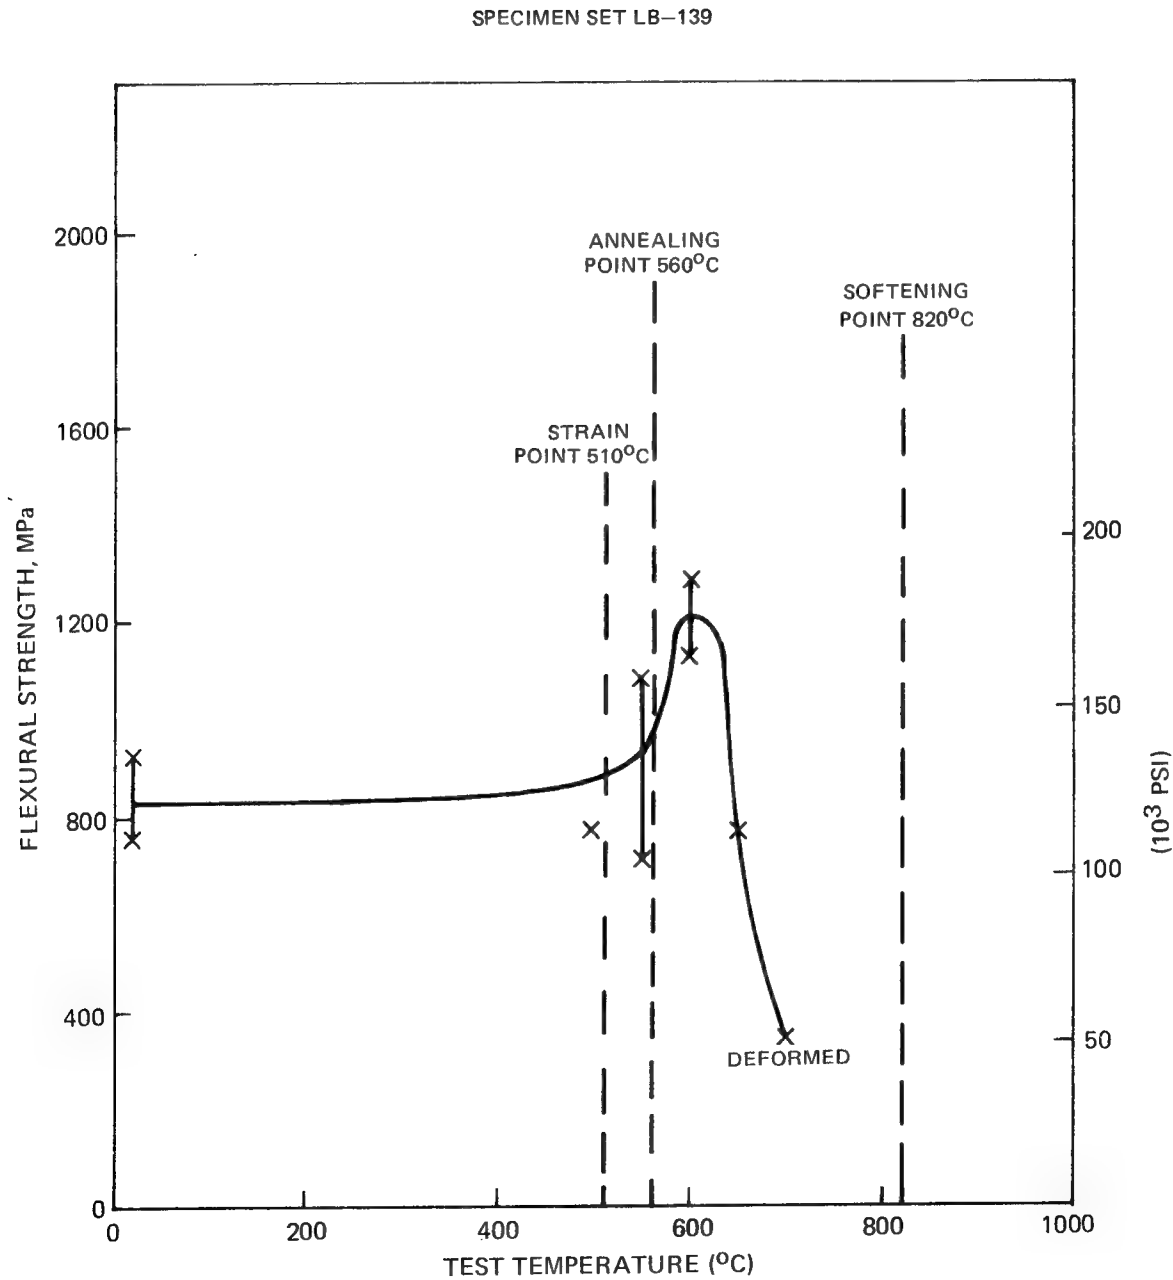


Table XXII

Hercules HMS-10K Reinforced 7740 LB 139

3 Point Flexural Strength Tested at Temperature in Argon

| <u>Test Temperature</u><br>(°C) | <u>Flexural Strength</u> |                     |
|---------------------------------|--------------------------|---------------------|
|                                 | MPa                      | 10 <sup>3</sup> psi |
| 22                              | 863                      | 125                 |
| 22                              | 785                      | 114                 |
| 500                             | 793                      | 115                 |
| 550                             | 1081                     | 157                 |
| 550                             | 706                      | 102                 |
| 600                             | 1292                     | 187                 |
| 600                             | 1134                     | 164                 |
| 650                             | 772                      | 112                 |
| 700                             | 347*                     | 50.3*               |

\*Specimen highly deformed so that this number is not strictly valid

specimen excessively large. The specimen fractures are shown in Fig. 31 indicating a fibrous nature to the RT fracture surface while at the higher temperatures the specimens delaminated in a limited way. None of these specimens failed completely and a bend fixture had to be used to take the photos shown in Fig. 31 since delaminations are not visible in the unstressed condition.

The load deflection traces for these composites are given in Figs. 32 and 33. A significant transition in load-deflection trace characteristics accompanies the change in fracture appearance noted above.

## 6. Comparison of High Temperature Strength with that of Other Composite Systems

### a. Graphite Reinforced Thermoplastic

The three-point bend data presented in Fig. 34 have recently been obtained for a NASA sponsored program at UTRC\*. The fiber is the same Hercules HMS fiber used on this program to reinforce 7740. Note the following points in comparison with Fig. 30.

The resin matrix composite maximum flexural strength at room temperature is approximately equal to the strength of the HMS-7740 at 600°C, although greater at room temperature.

The rate of strength decrease in the vicinity of the resin glass transition temperature is rapid, as it is for the glass matrix composite above 650°C.


### b. Graphite Reinforced Aluminum

The only flexural strength data for graphite reinforced aluminum the authors could find was recently published by W. Harrigan of Aerospace Corporation. These data, for wire and plates, are presented in Fig. 35 as a function of test temperature and compared with the data of Fig. 30.

\*Novak, R. C., Graphite Fiber Reinforced Thermoplastic Resins, NAS3-20077, CR-135196, 1976.




HMS-7740 THREE POINT FLEXURAL TEST SPECIMENS

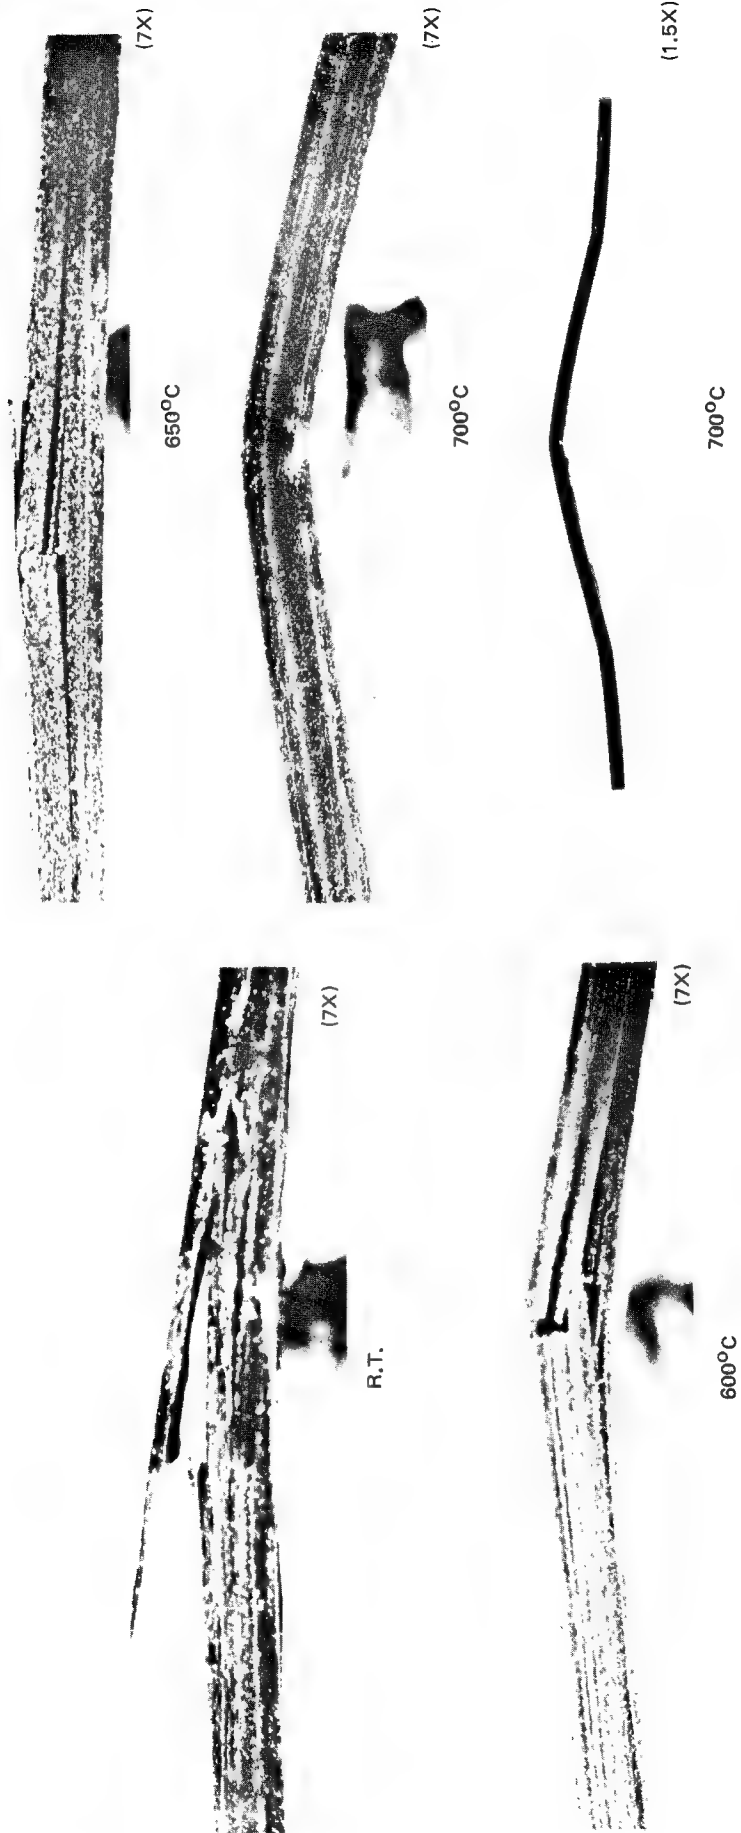

**HERCULES HMS-10K REINFORCED 7740**

LB-139


3 PT BEND AT TEMPERATURE

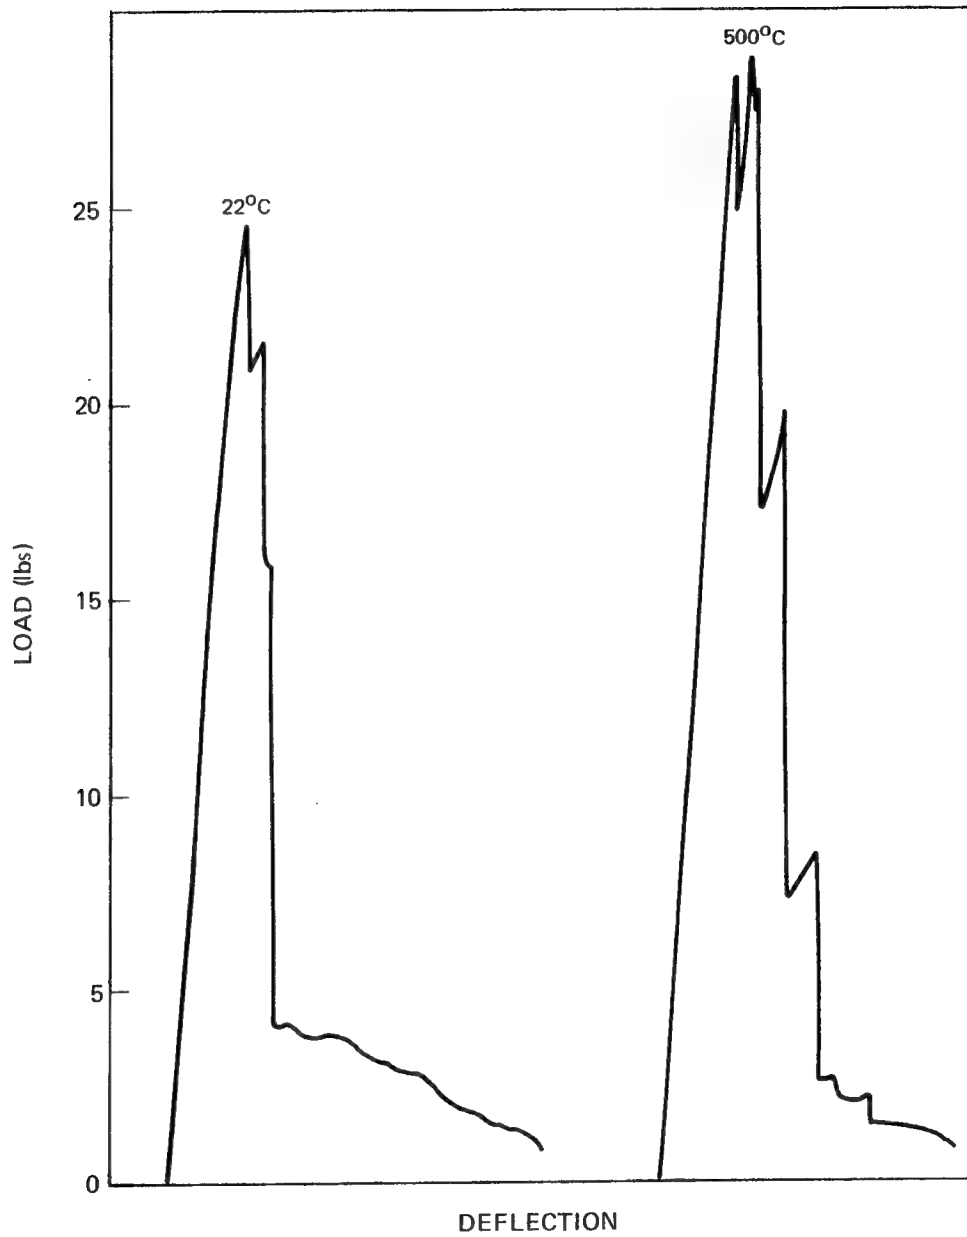


## HERCULES HMS-10K REINFORCED 7740

LB-139

3 PT BEND AT TEMPERATURE

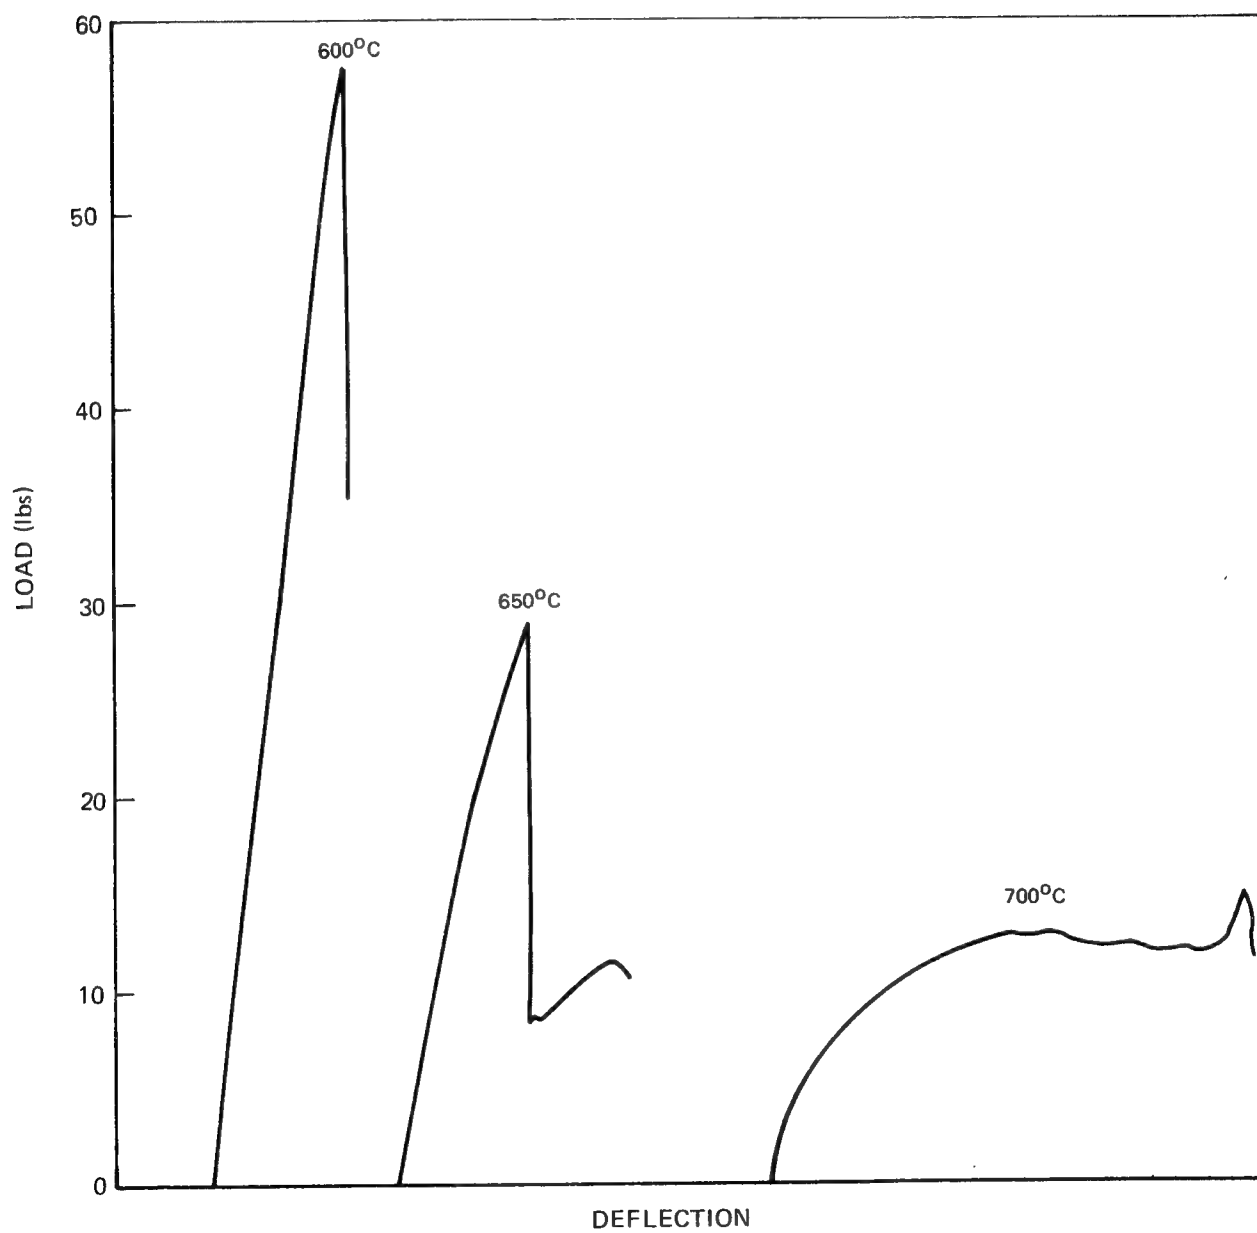


**FLEXURAL STRENGTH OF HERCULES HMS-10K FIBER REINFORCED 7740  
THERMOPLASTICS AS A FUNCTION OF TEST TEMPERATURE\***

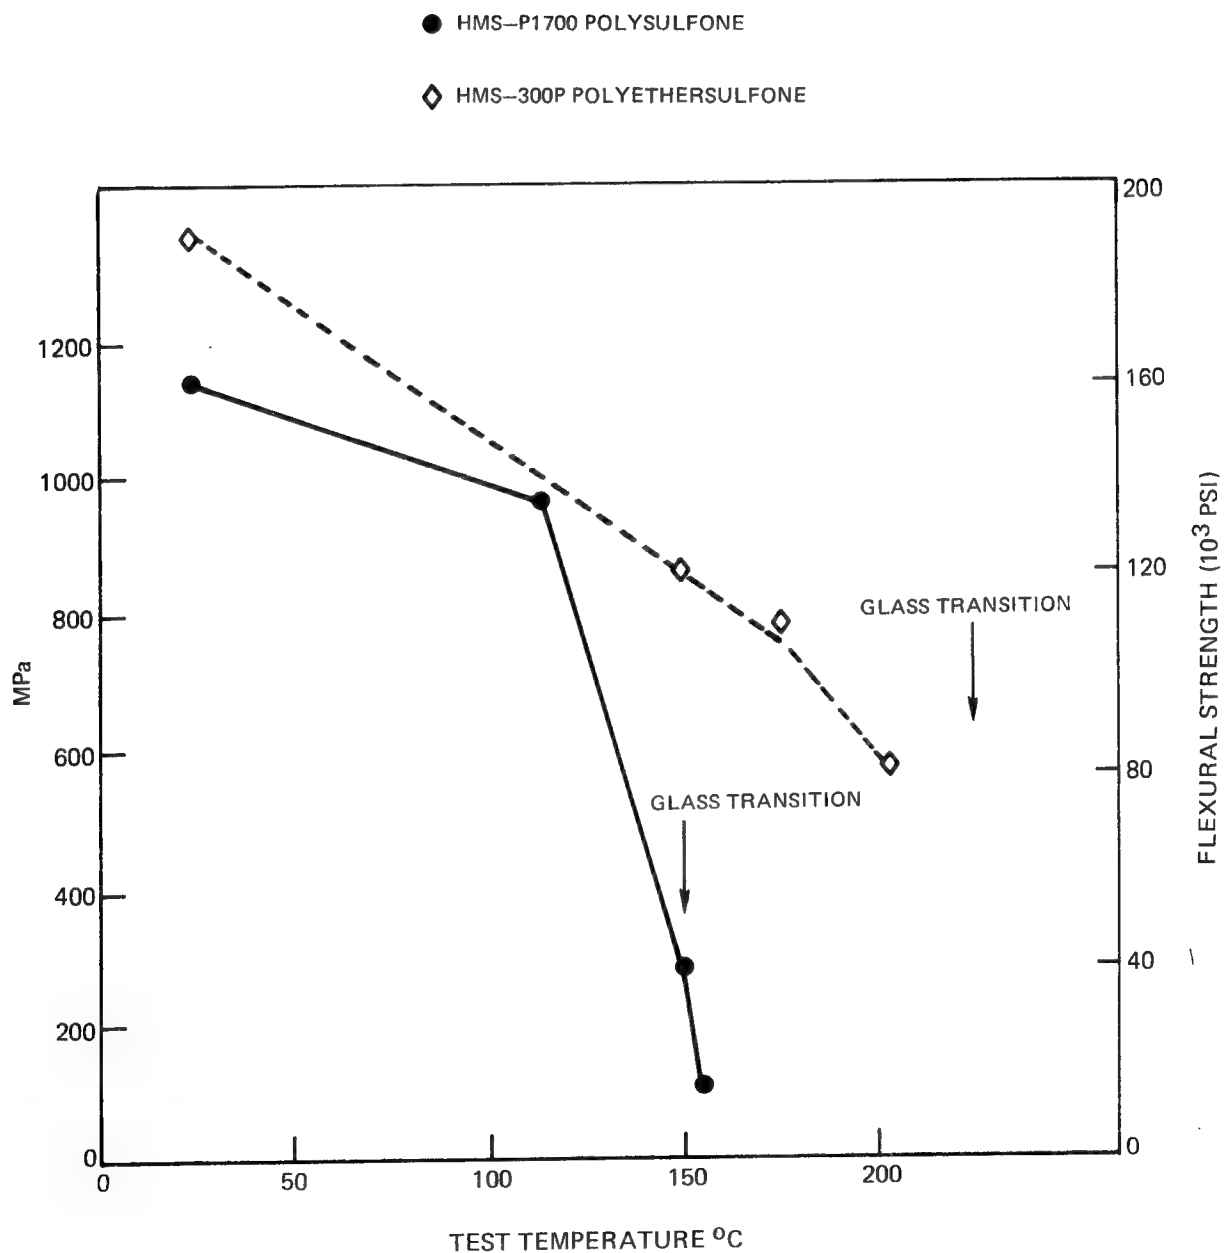

\* UTRC CONTRACT NAS3-20077, 1976

## FLEXURAL STRENGTH COMPARISON

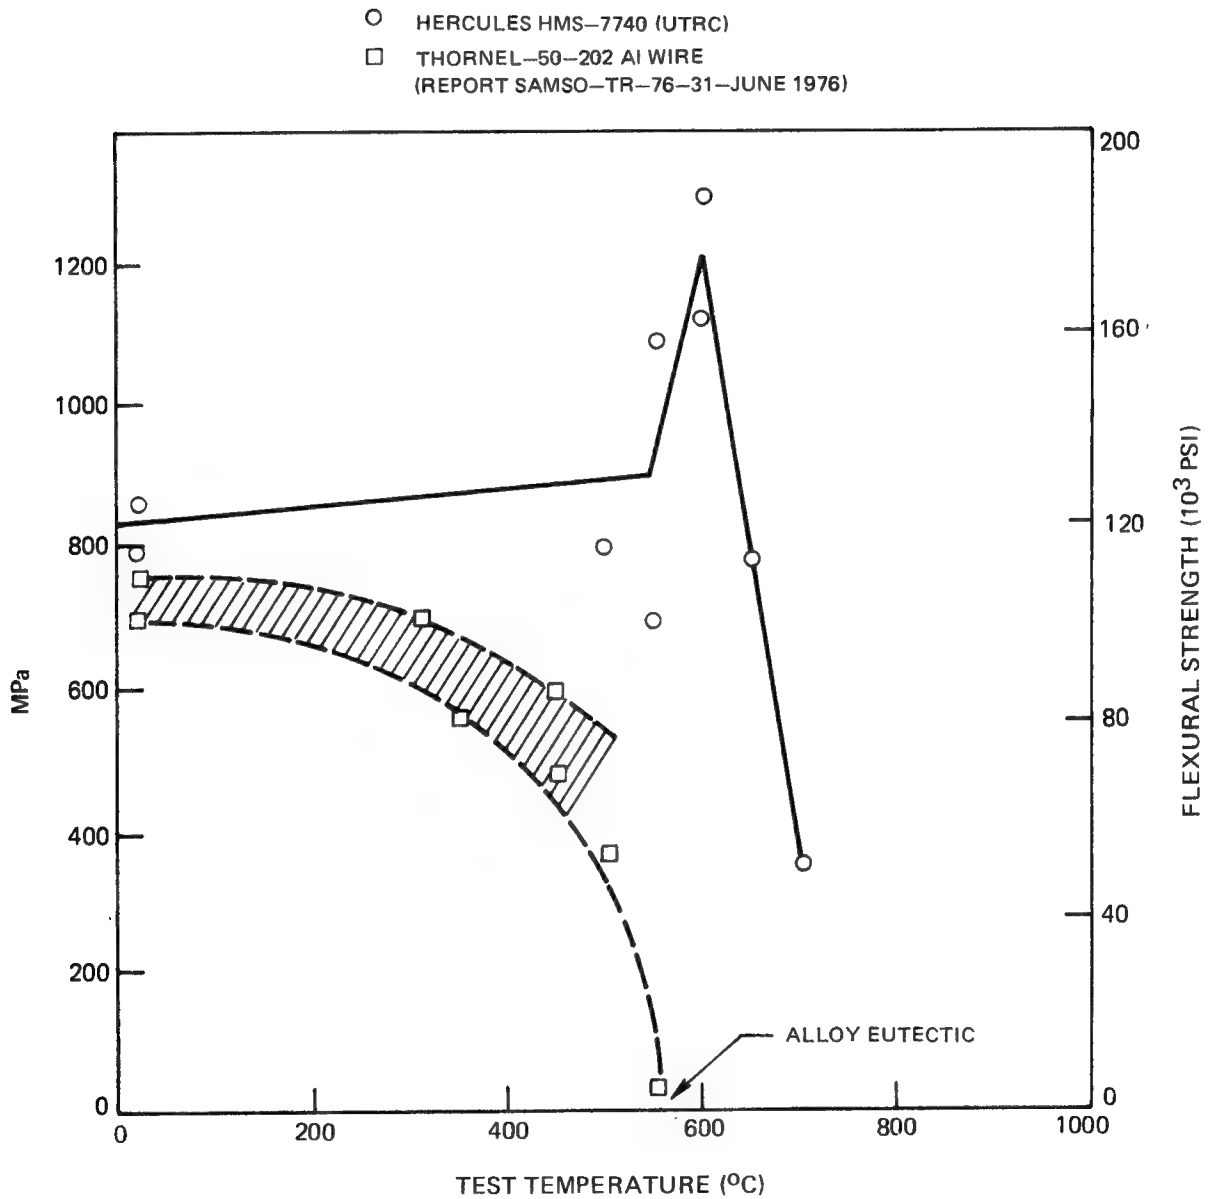

- Over the entire test temperature range, the glass matrix composite is equal to or superior to the aluminum matrix composite in strength.
- On a specific property basis the glass matrix composite would offer an additional advantage which in this case would be significant. The density of the aluminum matrix composite is approximately 2.4 grams per cubic centimeter while that of the HMS-7740 is approximately 2.0 grams per cubic centimeter. The specific strength comparison is given in Fig. 36.
- The maximum use temperature of the glass matrix composite should be significantly greater than that of the graphite aluminum.

#### c. Borsic Reinforced Ti-6Al-4V

This is the only metal matrix composite with a plausible use temperature in the range of RT-500°C (excluding reinforced high temperature superalloys which have a much higher density). Therefore, the comparison with this system at temperatures above 300°C is very meaningful. The data are presented in Fig. 37. In this case flexural data over the temperature range of interest are not available so Borsic-Ti tensile test data were used. To make a more realistic comparison, the Borsic-Ti composite tensile data were multiplied by a factor of 1.4 which, in the past at UTRC, has been shown to be the ratio of flexural strength to tensile strength at room temperature for Borsic-Ti. In addition, the data were divided by composite density to obtain the specific flexural strength comparison shown in Fig. 38. At temperatures above 150°C the glass matrix composite is clearly superior to the titanium matrix composite.


### 7. Fracture Toughness Testing

Notched three point bend specimens were fabricated and tested in an attempt to characterize the fracture toughness of this composite system. The specimen geometry is given in Fig. 39 and specimen dimensions with resultant data are given in Table XXIII.


Two types of mechanical test procedures were used.

- Specimen 140-2 was tested in slow 3 point bend at room temperature.
- The other three specimens were tested using the UTRC instrumented impact testing machine which is capable of operating at elevated temperatures.

## SPECIFIC FLEXURAL STRENGTH COMPARISON

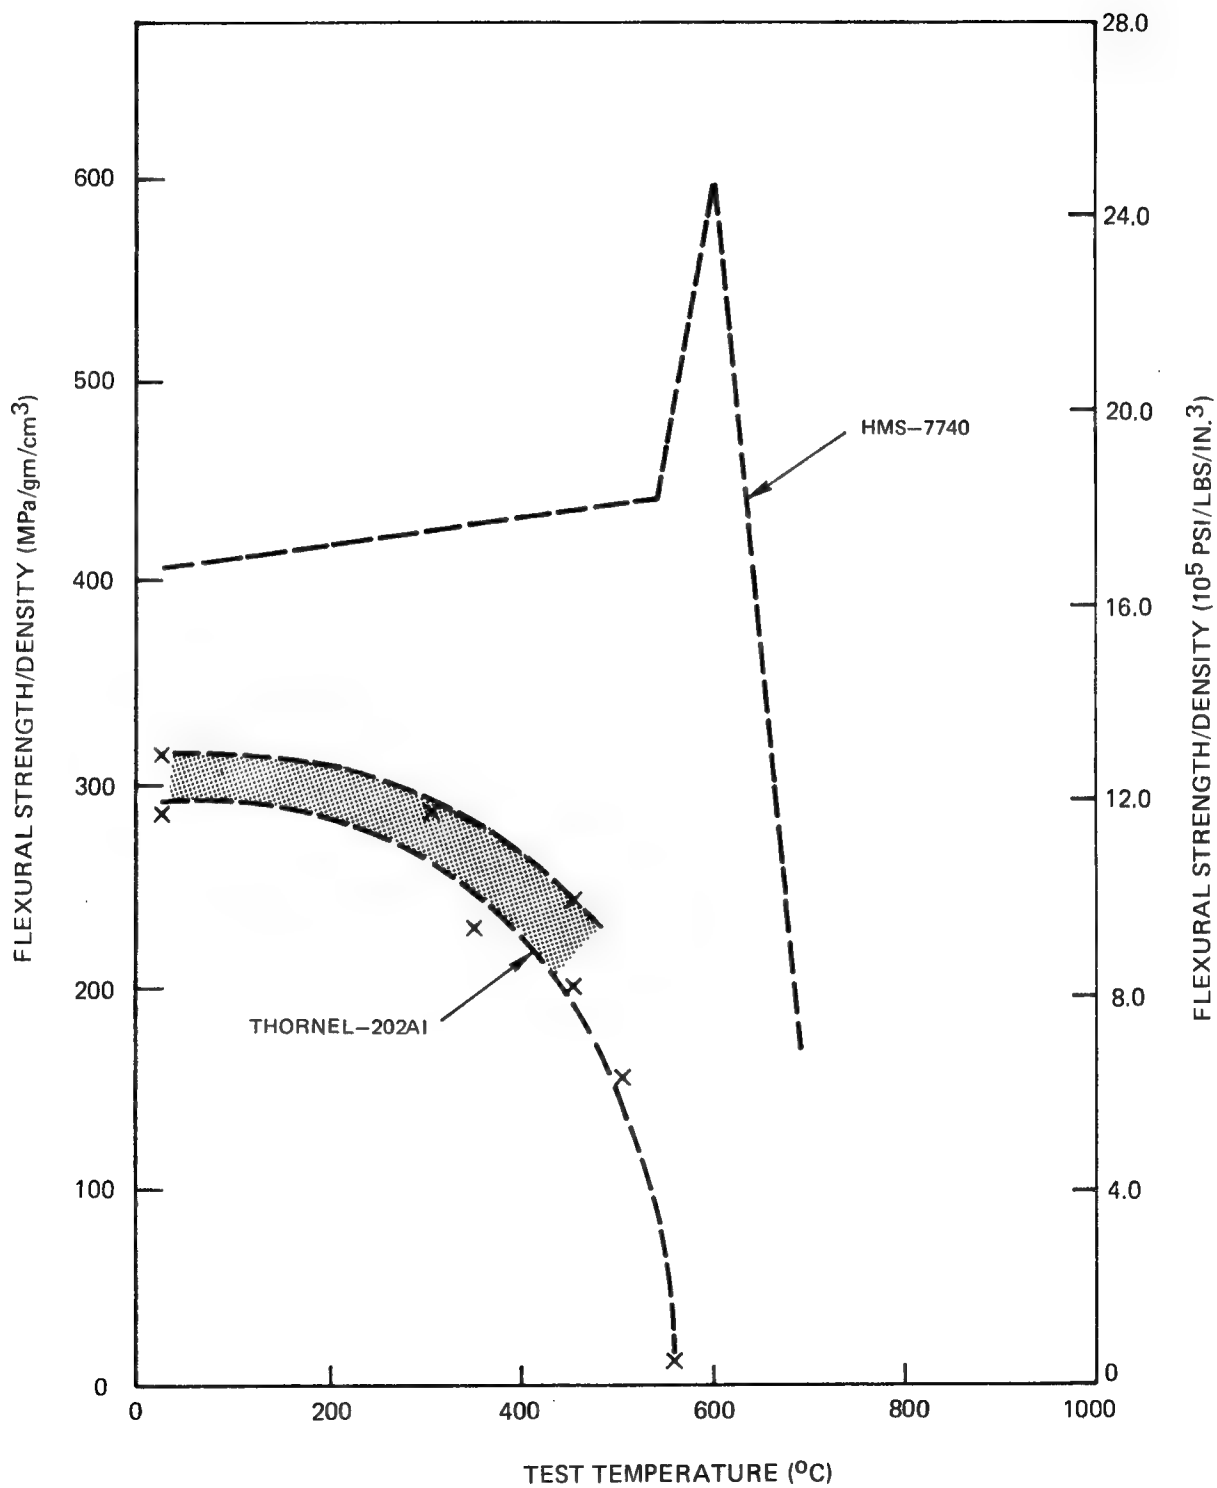


## FLEXURAL STRENGTH COMPARISON

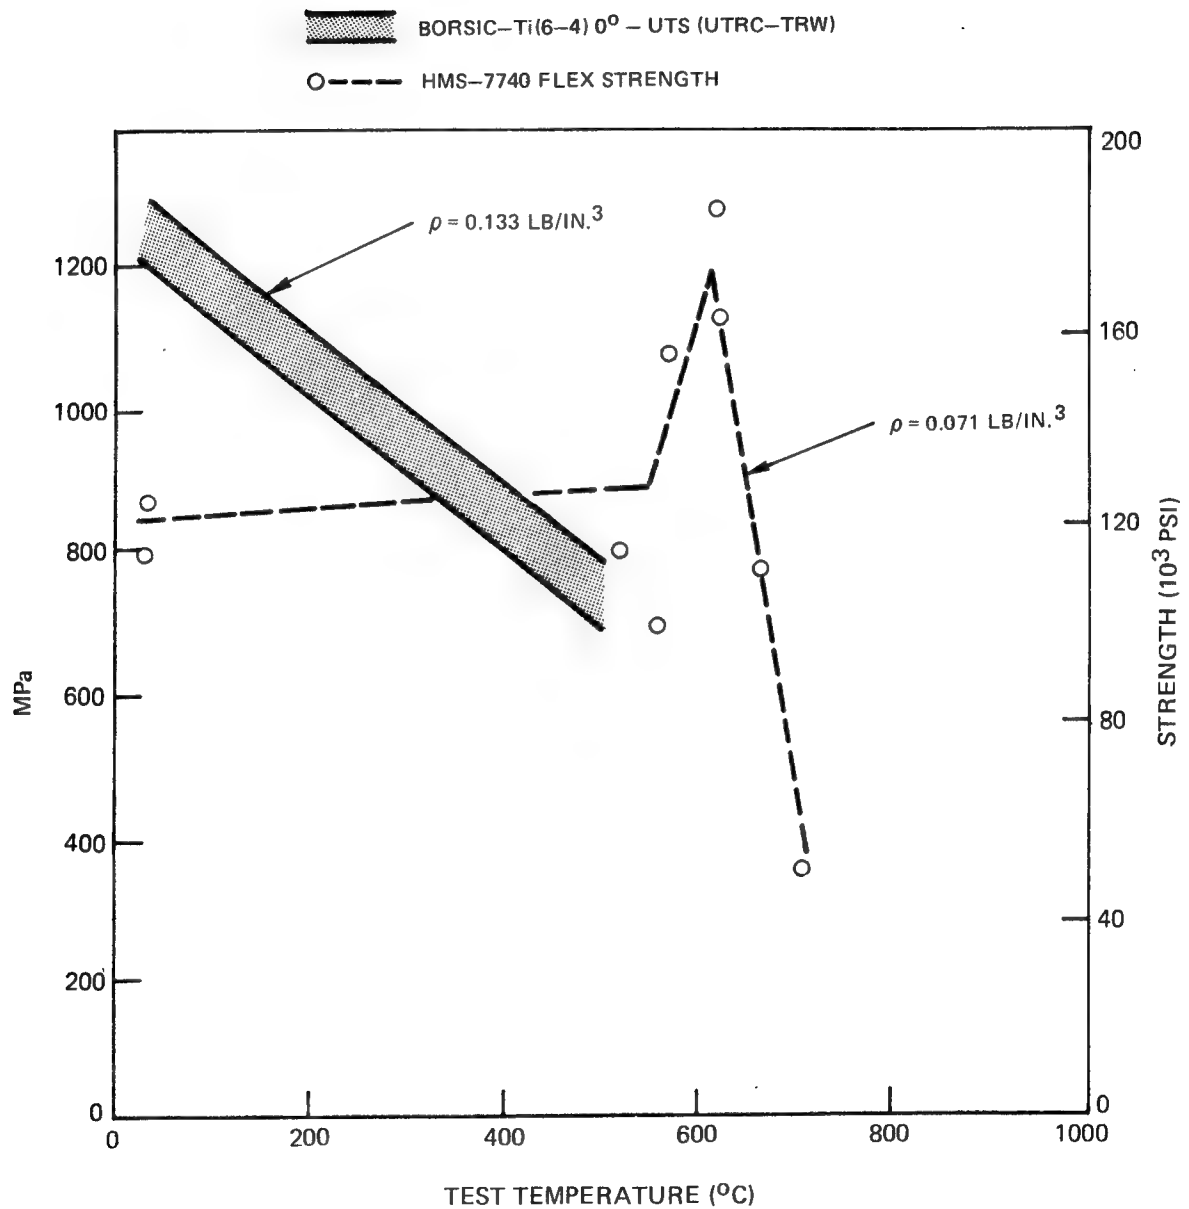



## SPECIFIC FLEXURAL STRENGTH COMPARISON

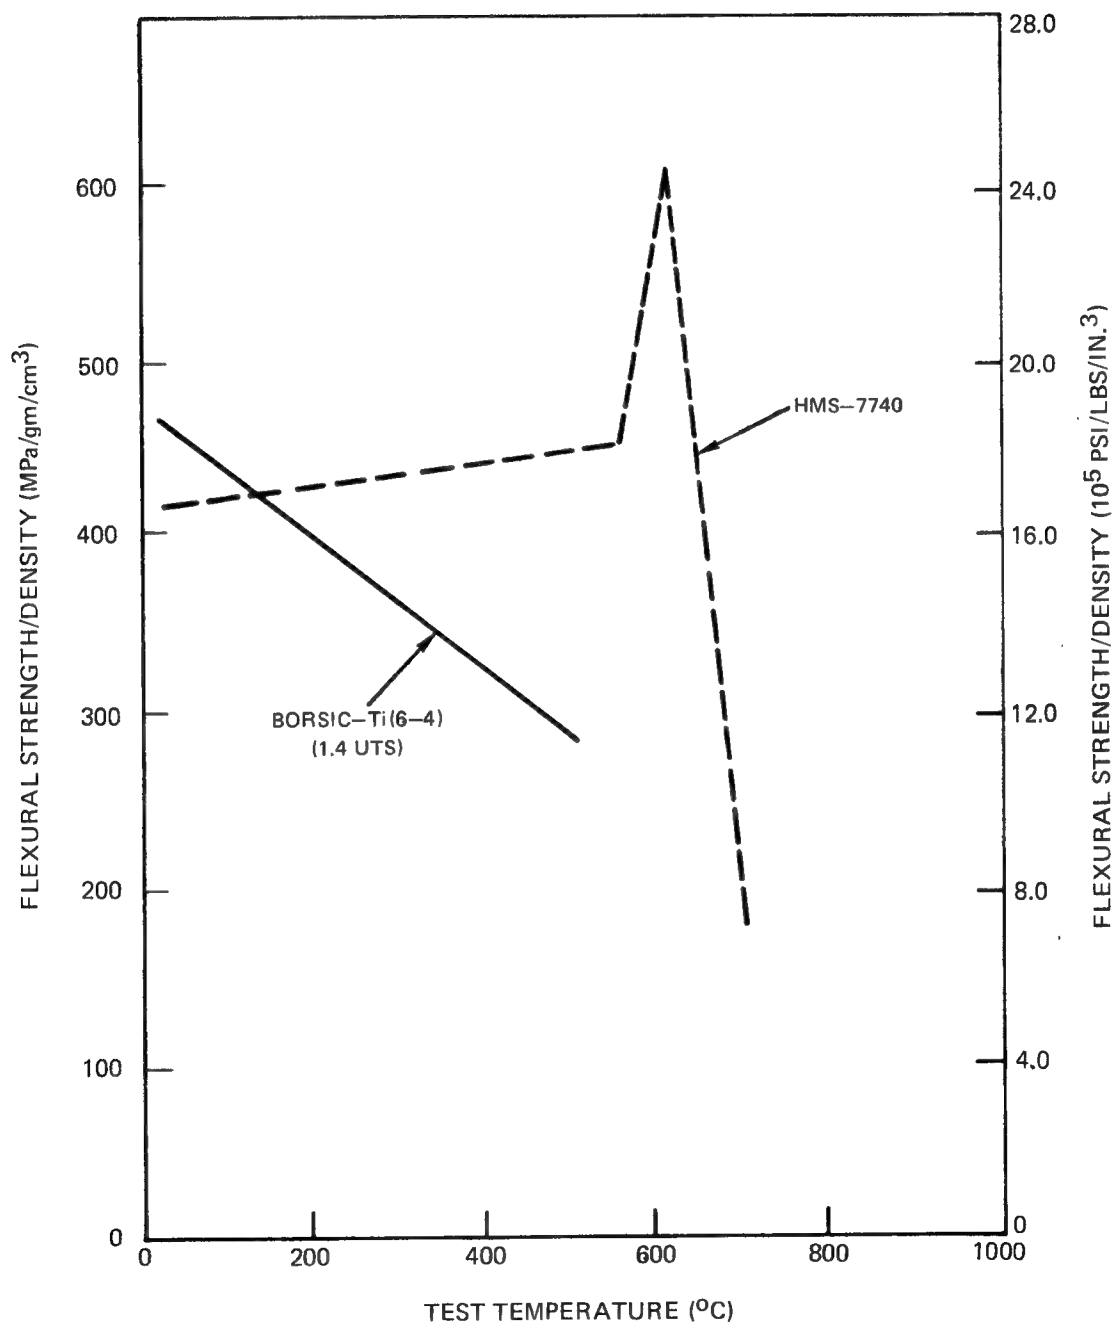

## FRACTURE TOUGHNESS SPECIMEN

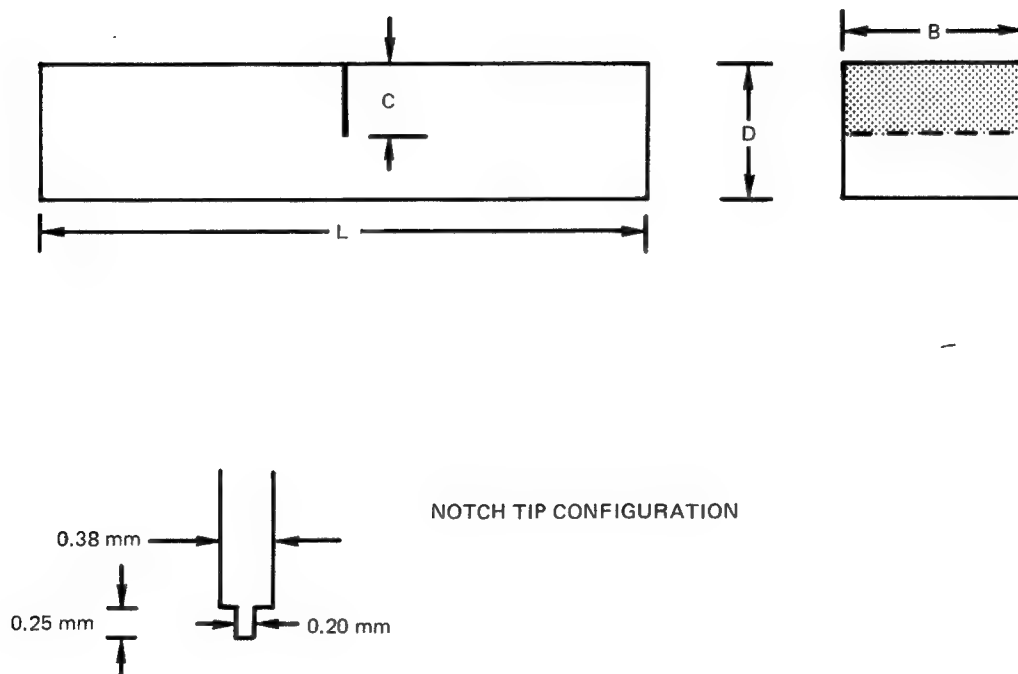


Table XXIII

## Fracture Toughness Specimen Dimensions

| <u>Specimen</u> | <u>C</u><br>(cm) | <u>B</u><br>(cm) | <u>D</u><br>(cm) | <u>Test Span</u><br>cm | <u>L</u><br>cm |
|-----------------|------------------|------------------|------------------|------------------------|----------------|
| LB-140-1        | 0.330            | 0.990            | 0.691            | 3.98                   | 5.0            |
| -2              | 0.305            | 0.990            | 0.691            | 3.80                   | 5.0            |
| LB-157-1        | 0.330            | 0.954            | 0.852            | 3.98                   | 5.0            |
| -2              | 0.330            | 0.954            | 0.852            | 3.98                   | 5.0            |

## Specimen Test Data

| <u>Specimen</u> | <u>Test Speed</u><br>(cm/min) | <u>Test Temp</u><br>°C | <u>K<sub>c</sub></u><br>$\frac{\text{MN}/\text{m}^{3/2}}{10^3 \text{ psi } \sqrt{\text{in}}}$ | <u>Energy Per Unit Area</u><br>$\frac{\text{Joules}/\text{m}^2}{\text{ft-lbs}/\text{in}^2}$ |
|-----------------|-------------------------------|------------------------|---|---|
| LB-140-1        | 20,000                        | 22                     | 21.4  | 23,500  |
| -2              | 0.127                         | 22                     | 22.1  | 11.3  |
| LB-157-1        | 20,000                        | 600                    | 15.8  | 10,600  |
| -2              | 20,000                        | 650                    | 19.0  | 11,800  |
|                 |                               |                        | 17.3  | 5.1   |
|                 |                               |                        |   | 5.7   |

The load vs deflection trace for the slow bend test is presented in Fig. 40. The increase in load to failure is linear and the value of fracture toughness of  $22.1 \text{ MN/m}^{3/2}$  was calculated on the basis of the maximum load.

By comparison, the load-time traces for the instrumented impact tests are given in Figs. 41 and 42. The initial peaks in these tests are the inertial peaks which have to do with the high velocity of impact. Aside from these inertial peaks, the rise to maximum load is also nearly linear for these tests and the value of  $K_C$  was also calculated on the basis of the maximum load.

The data in Table XXIII indicate that at  $22^\circ\text{C}$  there was no effect of dramatically increasing test speed. The fracture toughness did, however, decrease with increasing test temperature. This is opposite to the variation in strength described previously; note that even the values obtained at the higher temperatures are greater when compared to other composites and more conventional engineering alloys, Table XXIV.

#### 8. Effect of Thermal Cycling on Flexural Strength

Sample LB 135G, HMS in 7740, was tested by thermal cycling specimens at an interval of 8 minutes and 20 seconds as indicated by the thermal cycle shown in Fig. 43. As noted in Table XXV and as drawn in Fig. 44, the thermal cycling had little or no effect on the four-point bend strength of the specimens and these, after cycling, looked exactly as they had initially.


#### 9. Fatigue Studies and the Effect on Flexural Strength

Sample LB 135, again an HMS graphite fiber in C.G.W. 7740 glass composite made in the Centorr press, was subjected to four-point flexural fatigue testing. These specimens were prefatigued to between 0.8 and 0.08 of the as-fabricated four-point bend strength. Table XXVI and Fig. 45 show that the samples suffered no deterioration in strength after 100 cycles.


#### 10. Analysis of Graphite Fiber Content of HMS Composites

It has proven very easy to separate the graphite fibers from glass matrix using HF solutions. The fibers are recovered in a virtually intact condition and show no effect of having been encased in glass by hot pressing. In Table XXVII are shown the results of the analysis for two of the composites used in the tests of this section. The sample LB 138 has a three-point flexural strength of 661 MPa and 96,000 psi and was prepared in the older press used in this program as was sample LB 139.

LOAD VS DEFLECTION TRACE FOR SPECIMEN LB-140-2 TESTED AT 22°C

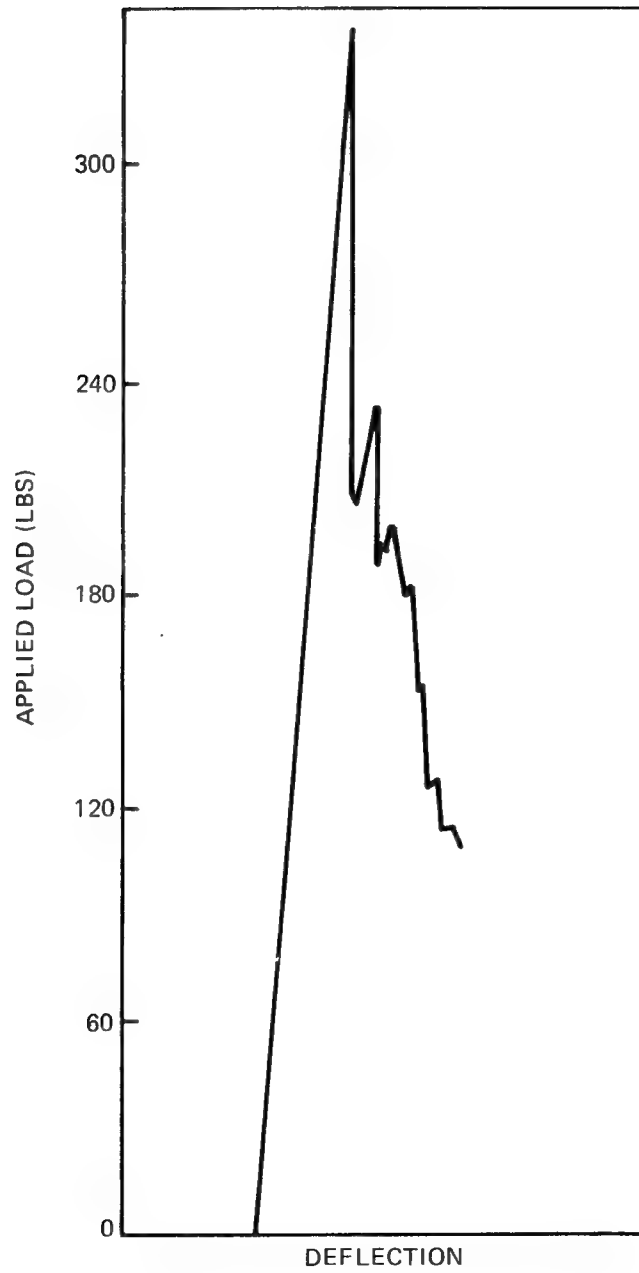

## INSTRUMENTED IMPACT TRACE

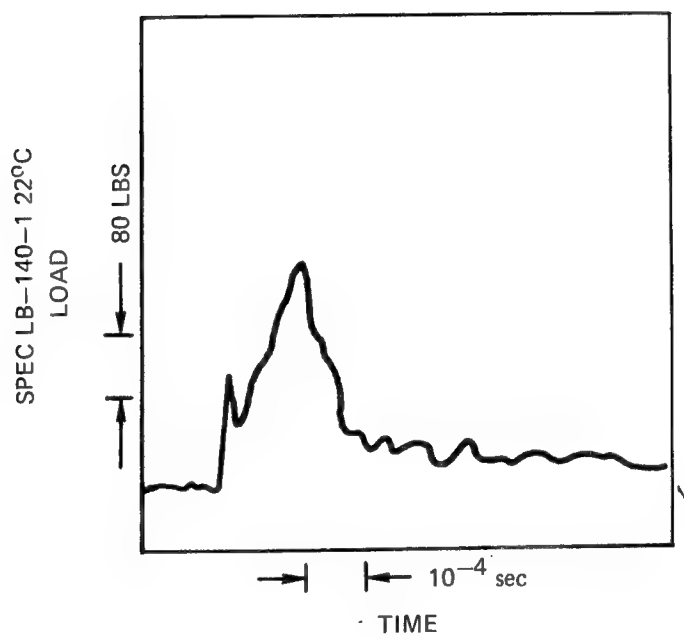

INSTRUMENTED IMPACT TRACES

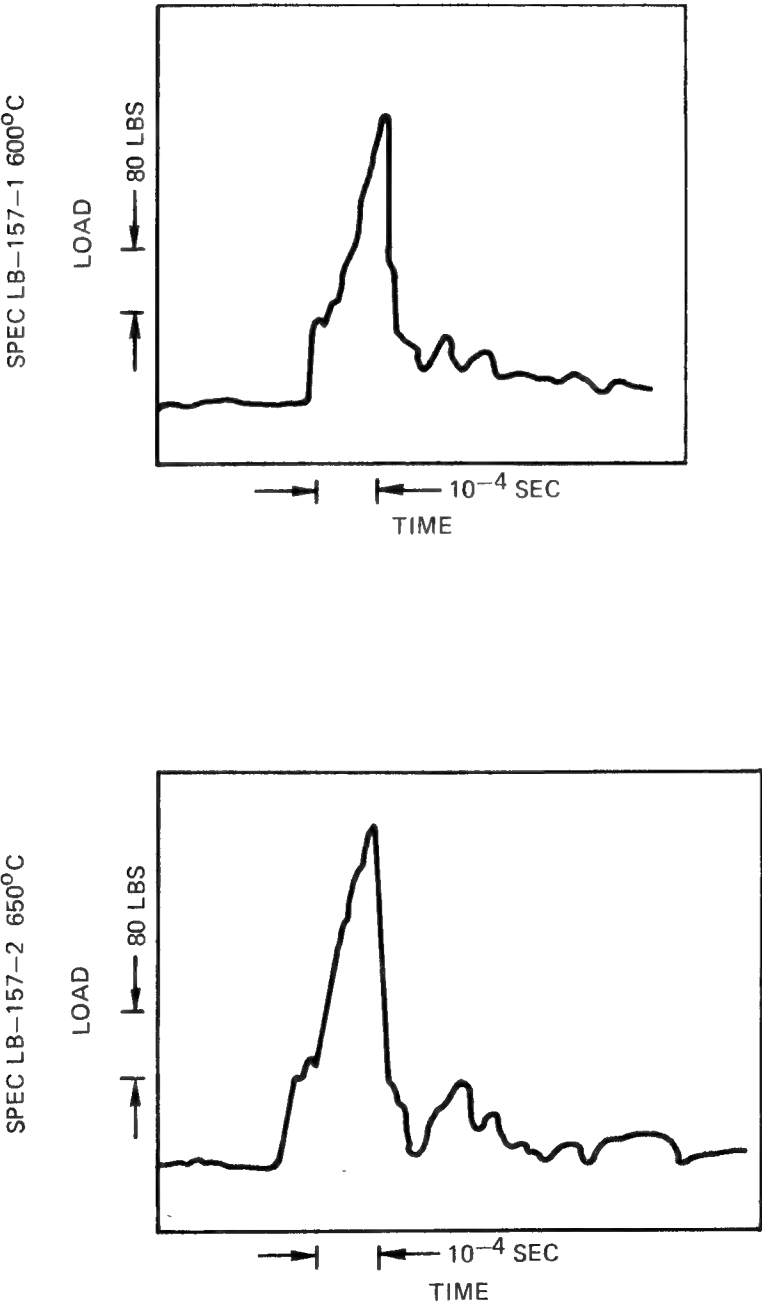


Table XXIV

## Fracture Toughness Comparison at 22°C

| <u>Material</u>             | <u>K<sub>IC</sub></u> |                         |
|-----------------------------|-----------------------|-------------------------|
|                             | MN/m <sup>3/2</sup>   | 10 <sup>3</sup> psi √in |
| 0°-HMS/7740                 | 21.7                  | 19.8                    |
| 0/90-AS Graphite/AR 288*    | 14.25-1.973           | 13-18                   |
| Morganite II/Epoxy**        |                       |                         |
| 0°                          | 35                    | 32                      |
| 90°                         | 1.75                  | 1.6                     |
| 45°                         | 2.52                  | 2.3                     |
| +45°                        | 19.73                 | 18                      |
| 0/+45°/90                   | 24.1                  | 22                      |
| 2014-T6 Aluminum Alloy***   | 21.92                 | 20                      |
| 6061-T651 Aluminum Alloy*** | 29.6                  | 27                      |

\*UTRC data using compact tension specimens

\*\*H. Konish and T. Cruse, J. Comp. Materials, Vol. 6, p 114, 1972

\*\*\*Damage Tolerant Design Handbook MCIC-HB-01



## TEMPERATURE CYCLE

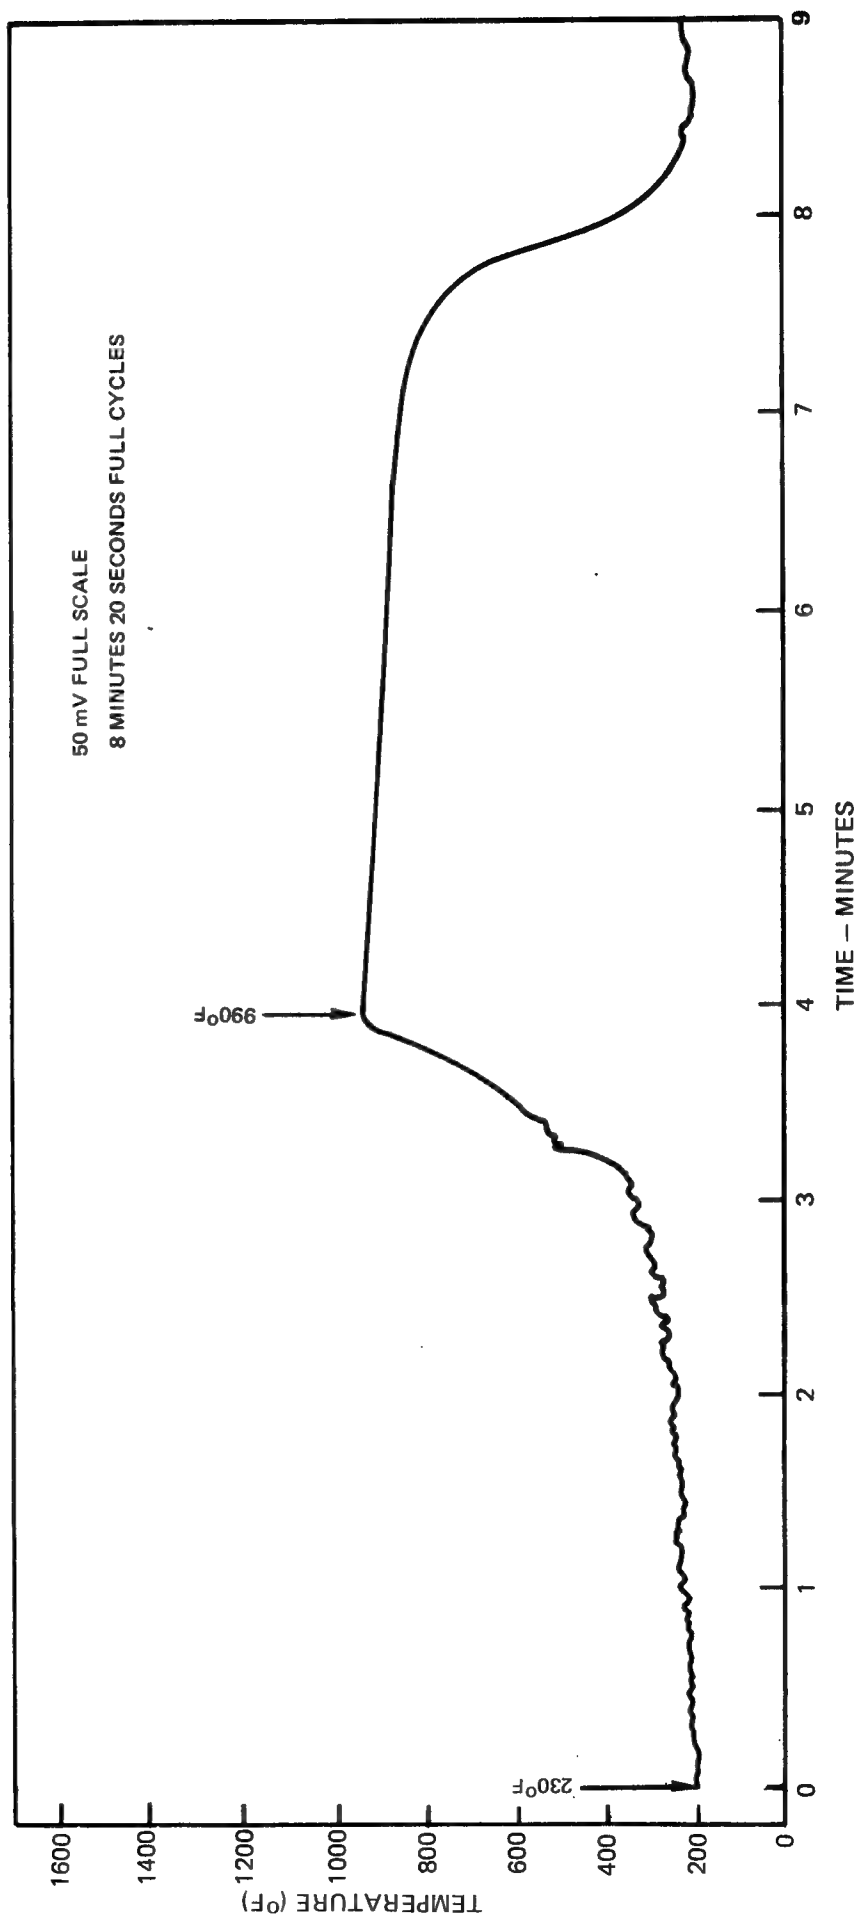


Table XXV

## Thermal Cycling

HMS Reinforced 7740 Spec LB 135 G

| <u>Condition</u>     | <u>4 Point Bend Strength</u> |                     | <u>*Elastic Modulus</u> |                     |
|----------------------|------------------------------|---------------------|-------------------------|---------------------|
|                      | MPa                          | 10 <sup>3</sup> psi | GPa                     | 10 <sup>6</sup> psi |
| As Fabricated        | 896                          | 130                 | 185                     | 26.8                |
|                      | 938                          | 136                 | 196                     | 28.5                |
|                      | 800                          | 116                 | 201                     | 29.2                |
|                      | Average                      | 876                 |                         | 127                 |
| After 20 Cycles **   | 917                          | 133                 | 196                     | 28.5                |
|                      | 910                          | 132                 | 203                     | 29.4                |
|                      | 834                          | 121                 | 189                     | 27.4                |
|                      | Average                      | 889                 |                         | 129                 |
| After 100 Cycles **+ | 786                          | 114                 | 174                     | 25.2                |
|                      | 614                          | 89                  | 167                     | 24.2                |
|                      | 758                          | 110                 | 185                     | 26.9                |
|                      | Average                      | 717                 |                         | 104                 |

\* Tested with major and minor spans of 5cm and 1.27cm

\*\* Cycled while in argon containing glass tube between 590-630°C and 110°C  
Target temperature 560°C or annealing point of glass matrix

\*\*+ The 100 cycles extended overnight with result that temperature exceeded target temperature (annealing point of glass matrix is 560°C or 1040°F) by 33°C.

**FLEXURAL STRENGTH OF HMS THORNEL 300-7740 GLASS COMPOSITE  
AFTER THERMAL CYCLING**

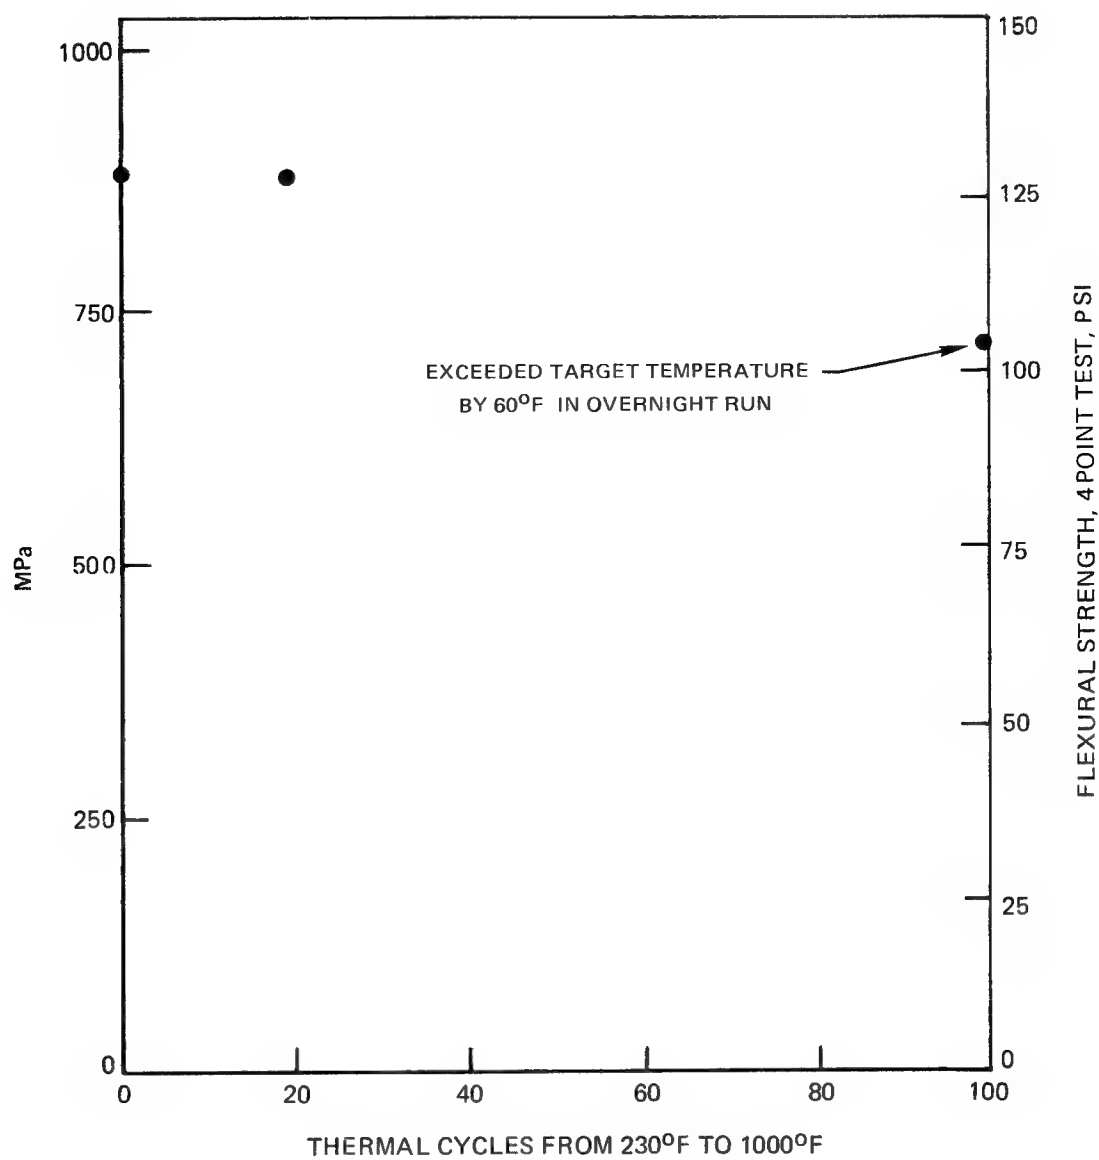


Table XXVI

Four Point Flexural Fatigue  
(Major and minor spans of 5 cm and 1.27 cm)

HMS Reinforced 7740 Spec LB 135 H

| <u>Condition</u>                               | <u>4 Point Bend Strength</u> |                     | <u>Elastic Modulus</u> |                     |
|--|------------------------------|---------------------|------------------------|---------------------|
|  | MPa                          | 10 <sup>3</sup> psi | GPa                    | 10 <sup>6</sup> psi |
| As Fabricated                                  | 548                          | 79                  | 200                    | 29.0                |
|  | 532                          | 77                  | 195                    | 28.3                |
| After 3 cycles<br>between 484 GPa and 48 GPa   | 325                          | 47                  | 185                    | 26.8                |
| After 20 cycles<br>between 337 GPa and 34 GPa  | 519                          | 75                  | 186                    | 26.9                |
| After 20 cycles<br>between 390 GPa and 39 GPa  | 658                          | 95                  | 194                    | 28.1                |
| After 20 cycles<br>between 450 GPa and 45 GPa  | 574                          | 83                  | 210                    | 30.5                |
| After 20 cycles<br>between 520 GPa and 52 GPa  | 638                          | 92                  | 208                    | 30.1                |
| After 100 cycles<br>between 430 GPa and 43 GPa | 575                          | 84                  | 207                    | 30.0                |
| After 100 cycles<br>between 445 GPa and 44 GPa | 573                          | 83                  | 201                    | 29.1                |

EFFECT OF FATIGUE ON BEND STRENGTH OF HMS THORNEL 300 FIBER IN  
7740 GLASS MATRIX COMPOSITE

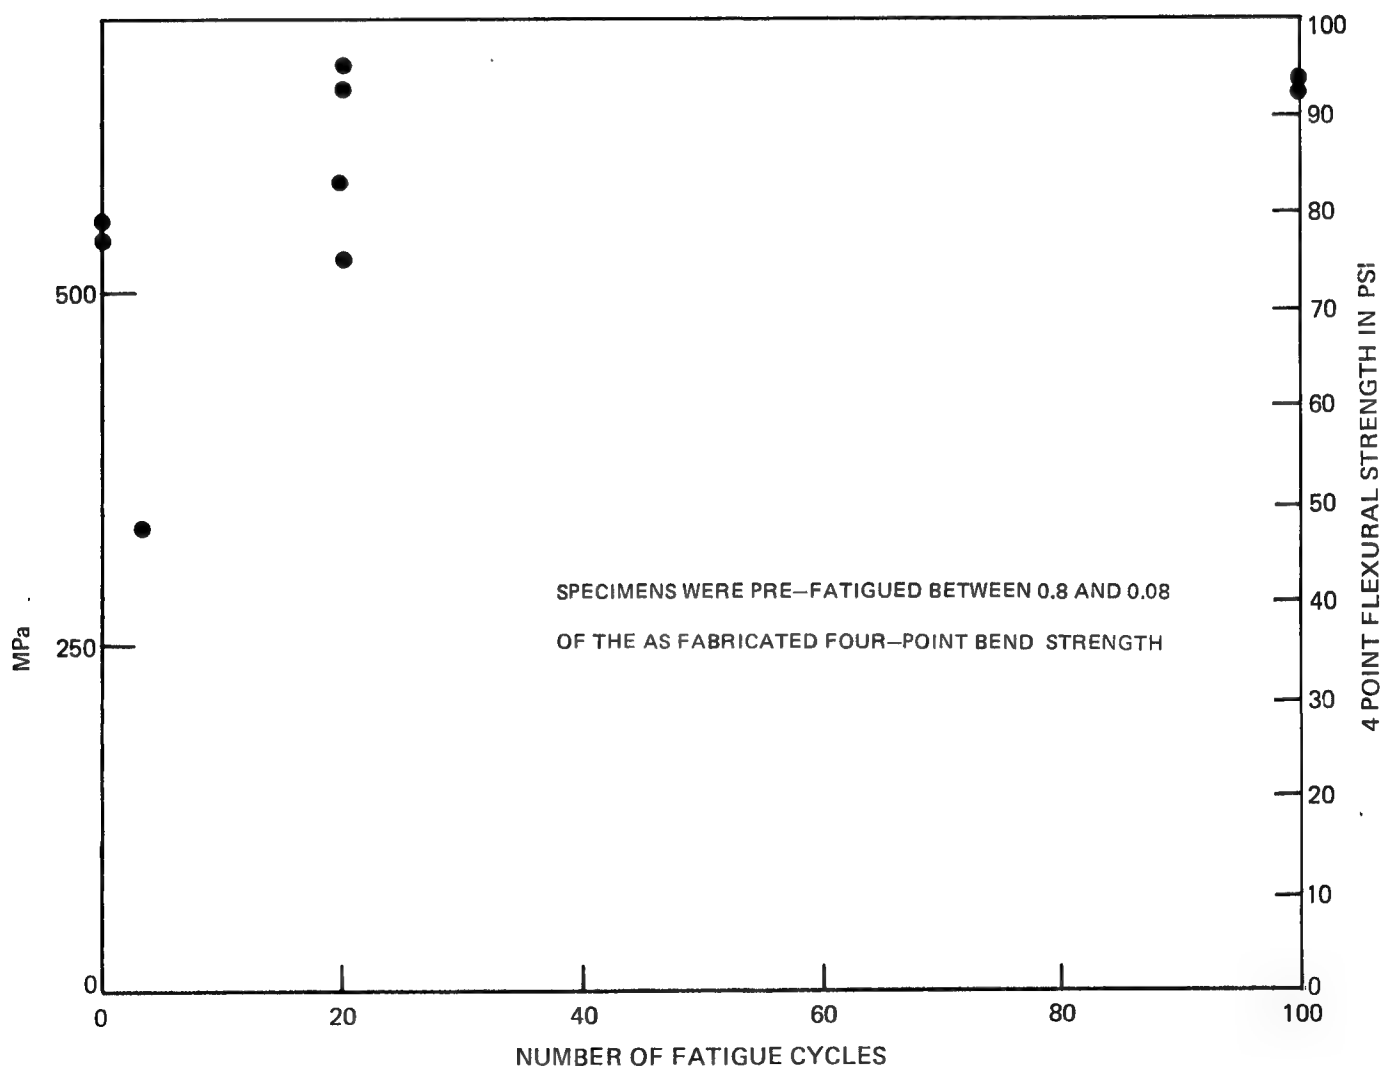


Table XXVII

Determination of Graphite Fiber Content for Several  
Graphite Fiber-Pyrex Glass Matrix Samples

| <u>Sample Identity</u> | <u>Vol % C</u> | <u>Vol % Glass</u> | <u>% Porosity</u> | <u>Weight % C</u> | <u>Weight % Glass</u> | <u>Analysis No.</u> |
|------------------------|----------------|--------------------|-------------------|-------------------|-----------------------|---------------------|
| LB 138 HMS             | 59.2           | 40.6               | 0.2               | 54.2              | 45.8                  | 72340               |
| LB 139 HMS             | 62.1           | 36.6               | 1.3               | 57.9              | 42.1                  | 72341               |

## B. Composites of Celanese DG-102 Graphite Fiber and Pyrex Glass

Because composites formed of Celanese DG-102 graphite fibers in Pyrex glass showed strengths only about one-third as great as the composites made with HMS graphite fiber in Pyrex glass, they have not been studied as extensively. But these same Celanese DG-102 graphite fibers in Pyrex glass composites have now been shown to have very much greater environmental stability than those made with HMS graphite fibers and Pyrex. Research during the second year of this program will attempt to produce composites with higher strength; we now obtain at room temperature only about one-third of the strength of the fiber in the composite that would be predicted based on the law of mixtures


### 1. Microstructure

The typical microstructures found in the Celanese DG-102 graphite fiber-Pyrex glass composites are shown in Figs. 46 and 47. The optical tape map of Fig. 46 shows that in the composites of Celanese fiber made to date the memory of the individual tows persists. Figure 47 reflects the fact that a Celanese fiber-Pyrex glass tow fractures in a brittle-brittle manner just as one would expect with an all ceramic material and this is further emphasized by the scanning electron micrograph at the bottom of the figure, which shows again that each fiber is indeed surrounded by glass and very tightly bonded to it. It is this tight bonding that probably accounts for both the low strength of the composite and its superior environmental stability.

### 2. Effect of Atmosphere

The three-point flexural strength of several specimens of Celanese DG-102 graphite fiber reinforced Pyrex glass composites was measured at room temperature. Other specimens of the same composites were first heated for 4 hrs at 560°C in either air or argon before carrying out the flexural tests at room temperature. As Table XXVIII shows, within experimental error, the exposure to either air or argon had no effect on the properties of the composite in contrast to similar tests carried out on HMS graphite fiber reinforced Pyrex composites where the air exposure at temperature resulted in a very high loss of strength. While admittedly both of the composites tested for which the data are shown in Table XXVIII are well below the average strength of Hercules HMS graphite fiber reinforced Pyrex matrix composites the data of this table are important in nature since all other graphite reinforced glass composites tested by UTRC show a pronounced degradation in strength when heated in air and subsequently tested. Further research in this area is obviously necessary in an attempt to improve the strength of these composites while maintaining their unique environmental stability.

TAPE-MAP OF CELANESE DG 102 FIBER IN C.G.W. 7740 GLASS MATRIX - UNFRACTURED SAMPLE

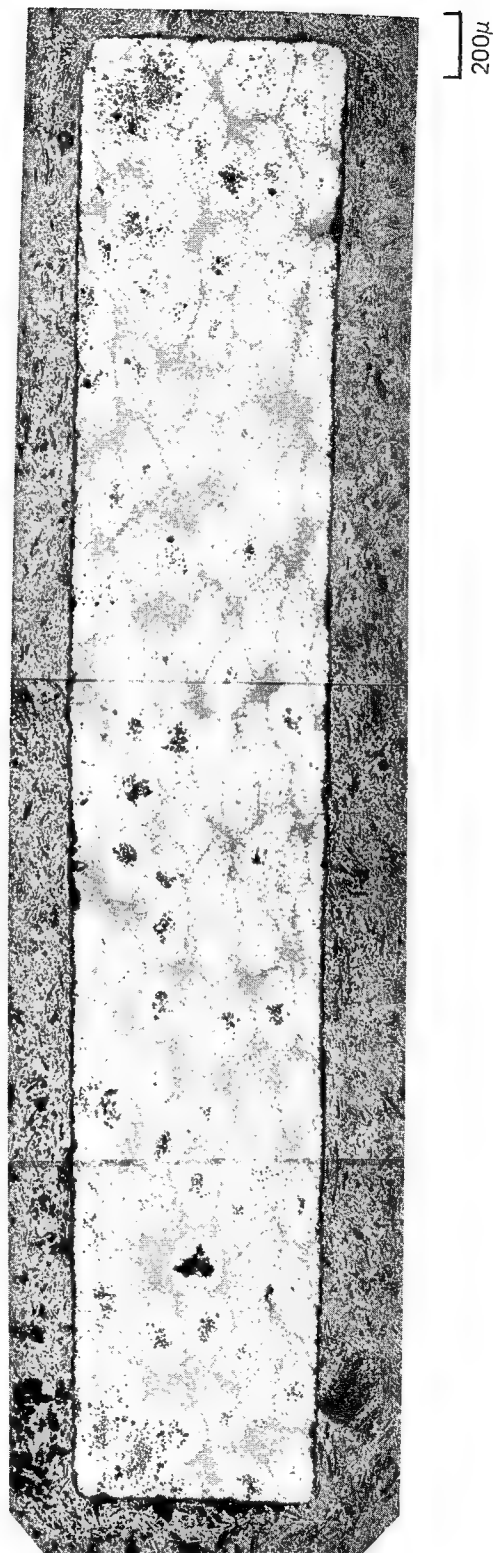




SCANNING ELECTRON MICROGRAPHS FRACTURE SURFACE CELANESE  
DG 102 FIBER IN C.G.W. 7740 GLASS MATRIX



LB 91-R1

500μ

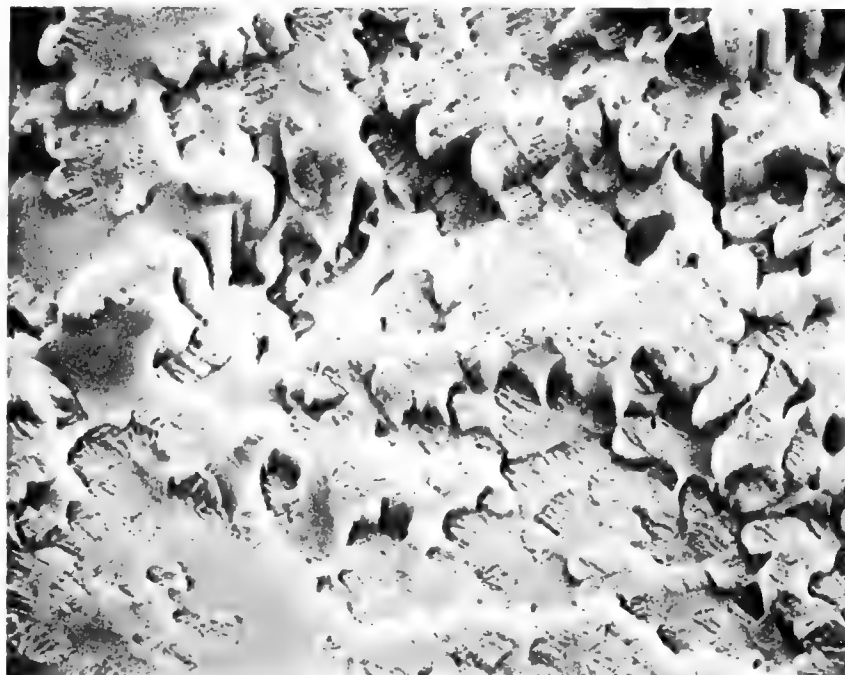

LB 91-L1

10μ

Table XXVIII

Effect of Atmosphere on Strength of Celanese DG-102 Graphite  
Fiber Reinforced C.G.W. 7740 Glass Composites

| <u>Specimen</u> | <u>Exposure Conditions</u> |              |               | <u>20°C 3-Point<br/>Bend Strength</u> |                           |      |
|-----------------|----------------------------|--------------|---------------|---------------------------------------|---------------------------|------|
|                 | <u>Time</u>                | <u>Temp.</u> | <u>Atmos.</u> | <u>MPa</u>                            | <u>10<sup>3</sup> psi</u> |      |
| LB-131          | 4 hrs                      | 560°C        | Argon         | 180                                   | 26.1                      |      |
|                 |                            |              |               | 233                                   | 33.7                      |      |
|                 |                            |              |               | 245                                   | 35.6                      |      |
|                 |                            |              |               | 291                                   | 42.2                      |      |
|                 |                            |              |               | 303                                   | 44.0                      |      |
|                 |                            |              |               | <u>328</u>                            | <u>47.6</u>               |      |
|                 |                            |              |               | 263                                   | 38.2                      | Avg. |
|                 |                            |              |               |                                       |                           |      |
| LB-131          |                            | None         |               | 155                                   | 22.5                      |      |
|                 |                            |              |               | 187                                   | 27.1                      |      |
|                 |                            |              |               | 192                                   | 27.8                      |      |
|                 |                            |              |               | 221                                   | 32.0                      |      |
|                 |                            |              |               | 275                                   | 39.9                      |      |
|                 |                            |              |               | <u>326</u>                            | <u>47.9</u>               |      |
|                 |                            |              |               | 227                                   | 32.9                      | Avg. |
|                 |                            |              |               |                                       |                           |      |
| LB-132          | 4 hrs                      | 560°C        | Air           | 145                                   | 21.1                      |      |
|                 |                            |              |               | 188                                   | 27.2                      |      |
|                 |                            |              |               | 202                                   | 29.3                      |      |
|                 |                            |              |               | 234                                   | 33.9                      |      |
|                 |                            |              |               | 280                                   | 40.6                      |      |
|                 |                            |              |               | <u>308</u>                            | <u>44.7</u>               |      |
|                 |                            |              |               | 226                                   | 32.8                      | Avg. |
|                 |                            |              |               |                                       |                           |      |
| LB-132          |                            | None         |               | 172                                   | 25.0                      |      |
|                 |                            |              |               | 225                                   | 32.6                      |      |
|                 |                            |              |               | 228                                   | 33.1                      |      |
|                 |                            |              |               | 241                                   | 34.9                      |      |
|                 |                            |              |               | 279                                   | 40.5                      |      |
|                 |                            |              |               | <u>312</u>                            | <u>45.3</u>               |      |
|                 |                            |              |               | 243                                   | 35.2                      | Avg. |
|                 |                            |              |               |                                       |                           |      |

### 3. Typical Flexural Strength and Modulus

Table XXIX lists the three-point flexural strength, the four-point flexural strength, and modulus for two typical samples of Celanese DG-102 graphite fiber reinforced Pyrex glass composites. Sample LB 97 was hot pressed in an older press at 1100°C and 13.8 MPa (2000 psi) while sample LB 97E was produced in the new press at 1200°C and 13.8 MPa (2000 psi). While slightly stronger composites of this nature have been produced the values of this table are more typical and representative of this composite at this stage of development.

### 4. Flexural Strength at Elevated Temperatures

The Celanese fiber reinforced 7740 composite system was tested in three-point bend as a function of temperature. In carrying out these tests an argon atmosphere was used.

The test results for specimen set LB 98 are presented in Fig. 48 and Table XXX. As can be seen, there is a marked change in composite performance with increasing temperature. As the composite reaches the annealing point of the matrix glass, the composite flexural strength is nearly double the value at room temperature. This increase in strength is probably due to the increased strain capacity of the matrix. For this composite system, of Celanese fiber and 7740, the bond between fiber and matrix is very strong. Therefore, it is likely that the composite strength is limited by the matrix failure strain at room temperature. At temperatures above the strain point of the glass, however, the matrix can deform to a greater extent, because of its lower viscosity. Thus, a larger percentage of the fiber strain, and hence strength, can be utilized. At temperatures above the annealing point (560°C), a large decrease in strength is noticed, however, the strengths calculated above this temperature are fictitious because the specimens do not fracture; instead the specimens deform to a very large extent. This is illustrative of an even further drop in matrix viscosity. At 700°C the viscosity of 7740 is  $10^{10}$  poises while at 510°C it is  $10^{14.5}$  poises.

Examination of the specimen fracture modes confirms the above description. At room temperature the specimens fracture without any permanent deformation and very little fiber pull out on the fracture surface, Fig. 49. At 500-550°C there is also no sign of specimen plastic deformation, however, additional fiber pull out is visible on the fracture surface, Fig. 50. This fiber-matrix separation occurred on the tensile side of each specimen. Finally at 700°C, Fig. 51, the specimen does not fracture but instead deforms to the full extent of motion of the test apparatus. In the last figure of this series, Fig. 52, we show the manner in which the sample plastically deformed to fit the test plunger. At the time of deformation the sample was still carrying a load of 42,000 psi

Table XXIX

Flexural Strength of Typical Specimens of Celanese Graphite Fiber  
DG-102 Reinforced C.G.W. 7740 Glass Matrix Composites

A. 3-Point Flexural Tests with 5.0 cm Span

| Specimen LB 97 | Flexural Strength |      |
|----------------|-------------------|------|
|                | MPa               | ksi  |
| L 1            | 399               | 57.8 |
| L 2            | 411               | 59.6 |
| L 3            | 265               | 38.4 |
| C 1            | 339               | 49.1 |
| C 2            | 340               | 49.3 |
| C 3            | 293               | 42.5 |
| R 1            | 281               | 40.8 |
| R 2            | 362               | 52.5 |
| R 3            | 392               | 56.8 |
| Average        | 342               | 49.6 |

B. 4-Point Flexural Tests with Inner Span 1.25 cm and Outer Span 5.0 cm

| Specimen LB 97E | Flexural Strength |      | Modulus |                     |
|-----------------|-------------------|------|---------|---------------------|
|                 | MPa               | ksi  | GPa     | 10 <sup>6</sup> psi |
| TR              | 289               | 41.9 | 277     | 40.2                |
| CR              | 301               | 43.7 | 269     | 39.0                |
| BR              | 336               | 48.7 | 271     | 39.3                |
| Average         | 309               | 44.8 | 272     | 39.5                |

FLEXURAL STRENGTH OF CELANESE FIBER REINFORCED 7740  
GLASS AS A FUNCTION OF TEST TEMPERATURE


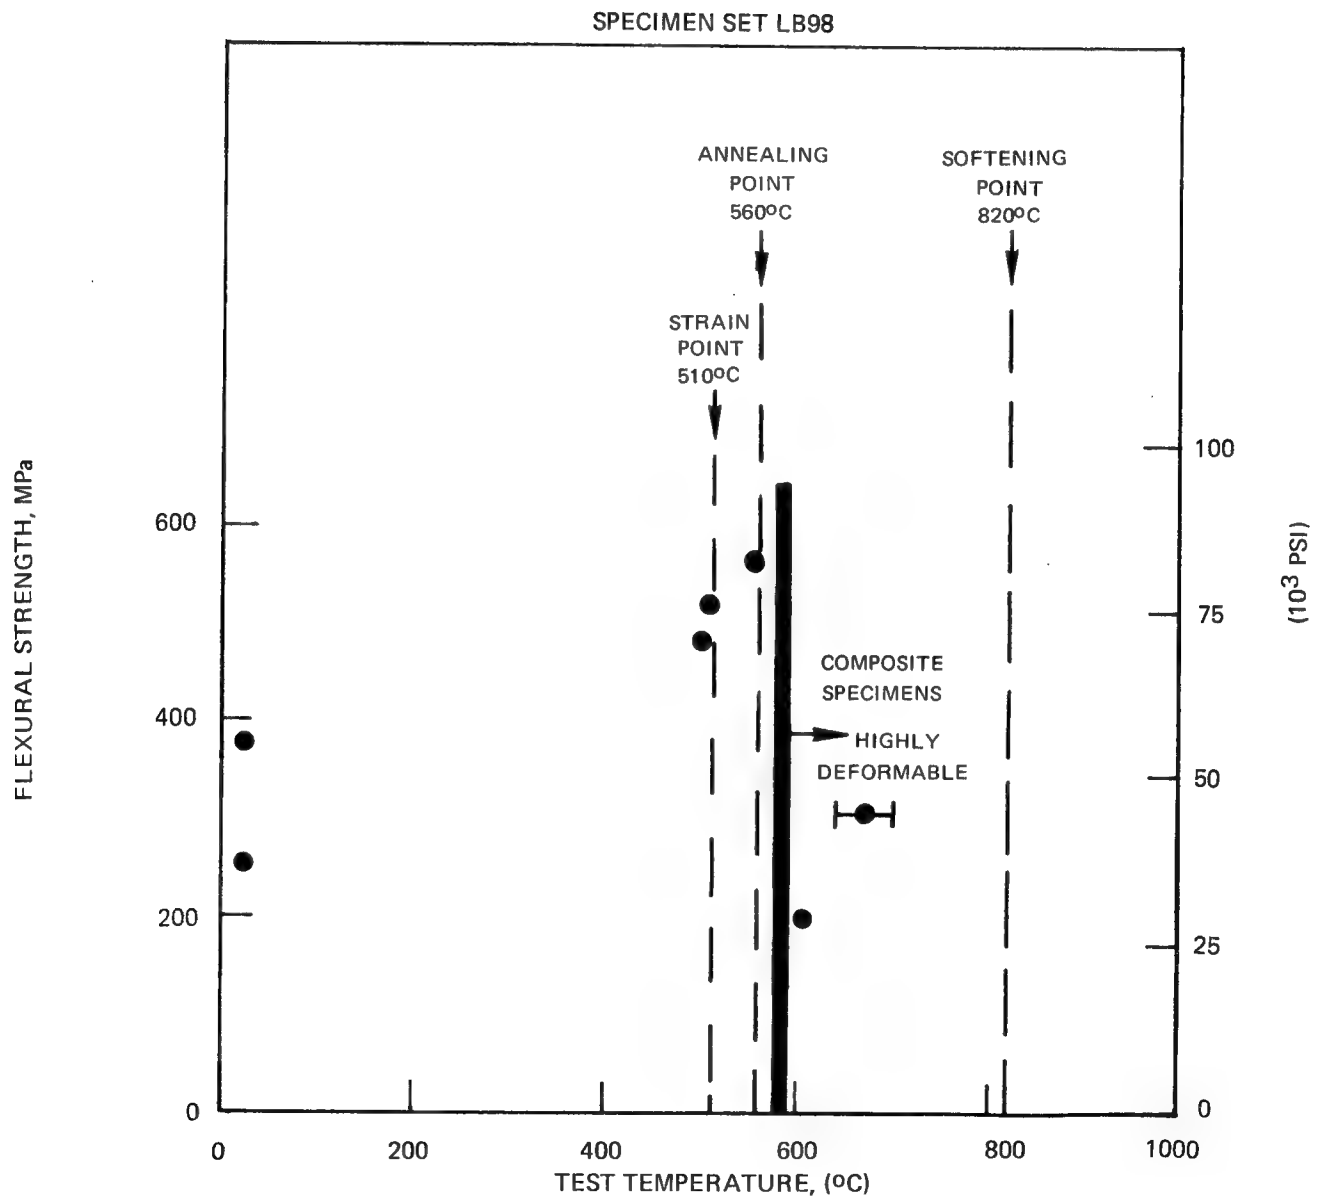


Table XXX

Flexural Strength of Celanese Graphite Fiber DG-102 Reinforced  
C.G.W. 7740 Glass Composite at Elevated Temperatures

| <u>Specimen</u> | Temperature at Which<br>Flexural Strength was<br>Measured °C | 3-Point Flexural Strength<br>Span 5.0 cm |            |
|-----------------|--|--|------------|
|                 |  | <u>MPa</u>                               | <u>ksi</u> |
| LB 98BL         | RT   | 374                                      | 54.2       |
| CR              | RT   | 250                                      | 36.2       |
| TL              | 500  | 515                                      | 74.7       |
| BR              | 500  | 481                                      | 69.7       |
| CL              | 550  | 565                                      | 82         |
| TR              | 600  | 196                                      | 28.4       |
| TC              | 700  | 292                                      | 42.3       |
| CC              | 700-635  | 305                                      | 44.3       |

CELANESE FIBER REINFORCED 7740  
TEST TEMPERATURE 22 °C  
LB-98

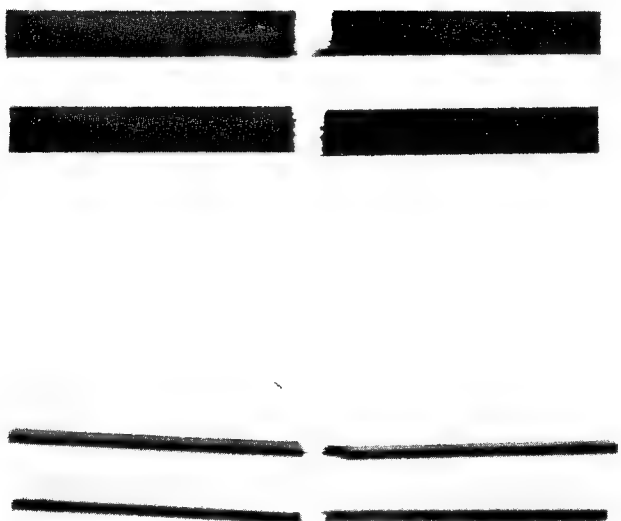

CELANESE FIBER REINFORCED 7740  
TEST TEMPERATURE 500-550 °C  
LB-98





CELANESE FIBER REINFORCED 7740  
TEST TEMPERATURE 700 °C  
LB-98




**3 POINT BEND SPECIMEN LB98-CC**

TEST TEMPERATURE = 700°C



a) OVERALL SIDE VIEW

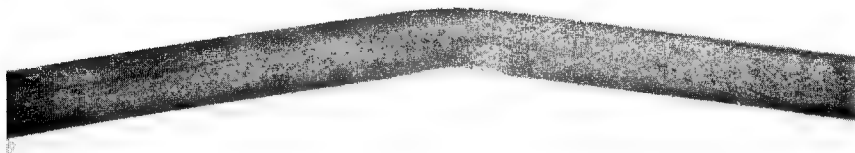600  $\mu$ 

b) AREA LOADING-SIDE VIEW

2000  $\mu$ c) BUCKLED AREA OF CONTACT WITH LOADING NOSE  
-TOP VIEW2000  $\mu$

which is also the approximate room temperature flexural strength for these high modulus graphite fiber composites. This behavior may be compared to the deformation under load undergone by a graphite fiber epoxy resin matrix as it passes through the transition from brittle to ductile behavior.

From the above it would appear that a use temperature of up to 550°C would be reasonable for this composite system. Specimen performance approaches that of resin matrix composites tested at much lower temperatures. As an example, approximately 50% unidirectional Celanese fiber reinforced epoxy typically exhibits a tensile strength of 758 MPa (110,000 psi) at 22°C while the current composites of Celanese fiber reinforced C.G.W. 7740 glass fail at 345 MPa (50,000 psi) at 22°C and 565 MPa (82,000 psi) at 550°C for a volume percent fiber of 47%.

## VI. CONCLUSIONS AND RECOMMENDATIONS

At the end of the first year's research, we have two principal types of graphite fiber reinforced glass matrix composites, each of which have some excellent but different properties.

The first type of composite consists of Hercules HMS graphite fiber reinforced C.G.W. 7740 glass matrix. Its properties are:

- Room temperature 4-point flexural strength of 848 MPa (127,300 psi)
- Average flexural modulus of 200 to 206 GPa (29 to 30 million psi)
- Use temperature in argon or vacuum of 600°C (1112°F)
- 50% higher flexural strength at 560°C than at room temperature
- No loss in strength with thermal or fatigue cycling in argon or vacuum
- Greatly increased toughness compared to glass, i.e. about same as commonly used lower temperature composites
- When heated in air to 560°C suffers severe loss of strength.

The second type of composite consists of Celanese DG-102 fiber reinforced C.G.W. 7740 glass matrix with these properties:

- Room temperature 4-point flexural strength of 309 MPa (45,000 psi)
- Average flexural modulus of 272 to 303 GPa (39.5 to 40 million psi)
- Use temperature of 600°C again with 50% higher strength at this temperature than at room temperature
- No loss in strength when heated in air to 560°C for 4 hrs and subsequently tested.

Based on the observations made during the first year's effort, the following recommendations are offered:

A systematic study of the mechanism controlling the oxidation of the HMS graphite fiber 7740 glass matrix composites at elevated temperatures should be carried out.

At the same time an effort should be made to partially block the bond between the Celanese DG-102 graphite fiber in 7740 glass matrices to see if a higher percentage of the strength of the graphite fiber can be attained while maintaining the oxidation resistance of these composites.

The number of graphite fiber, glass and/or Pyroceram matrix combinations should be expanded and evaluated to see if some new combination can offer both strength and oxidation resistance.

Biaxially reinforced specimens should be fabricated and evaluated.

An extensive characterization of the properties of the best graphite fiber-glass matrix system should be undertaken to provide a better understanding of how such composites can be used.

# REFERENCES

1. Siefert, August C.: Fiber-Reinforced Ceramics, U.S. Patent 3,607,608, Sept. 21, 1971.
2. Siefert, August C.: Method of Making Glass-Metal Fiber Composites, U.S. Patent 3,792,985, Feb. 19, 1974.
3. Sambell, R. A. J., D. H. Bowen, D. C. Phillips: Carbon Fibre Composites with Ceramic and Glass Matrices, Part I, Discontinuous Fibres Journal of Materials Science, 7 (1972) pp 663-675.
4. Sambell, R. A. J., A. Briggs, D. C. Phillips, and D. H. Bowen: Carbon Fibre Composites with Ceramic and Glass Matrices, Part II, Continuous Fibres Journal of Materials Science, 7 (1972) pp 676-681.
5. Phillips, D. C.: The Fracture Energy of Carbon-Fibre Reinforced Glass, Journal of Materials Science, 7 (1972) pp 1175-1191.
6. Phillips, D. C., R. A. J. Sambell, D. H. Bowen: The Mechanical Properties of Carbon Fibre Reinforced Pyrex Glass, Journal of Materials Science, 7 (1972) pp 1454-1464.
7. Levitt, S. R.: High Strength Graphite Fibre/Lithium Aluminosilicate Composites, Journal of Materials Science, 8 (1973) pp 793-806.
8. Phillips, D. C.: Interfacial Bonding and the Toughness of Carbon Fibre Reinforced Glass and Glass Ceramics, Journal of Materials Science, 9 (1974) pp 1847-1854.
9. Lange, F. F.: Fracture Energy and Strength Behavior of Sodium Borosilicate Glass-Al<sub>2</sub>O<sub>3</sub> Composite System, Journal American Ceramic Society, Vol. 54, No. 12, pp 614-620, Sept. 1971.
10. Hasselman, D. P. H. and R. M. Fulrath: Proposed Fracture Theory of a Dispersion Strengthened Glass Matrix, Journal American Ceramic Society, Vol. 49, No. 2, pp 69-72, Feb. 1966.
11. Harris, Bryan: The Nature and Properties of Carbon Fibres and Their Composites, Carbon Fibres in Engineering, Editor, Marcus Langley, McGraw-Hill, London, 1973, pp 1-45.

12. Sambell, R. A. J., D. C. Phillips and D. H. Bowen: The Technology of Carbon Fibre Reinforced Glasses and Ceramics, Harwell Materials Bulletin, AERE-R7612, Feb. 1974.
13. Donald, I. W. and P. W. McMillan: Review, Ceramic-Matrix Composites, Journal of Materials Science II (1976) pp 949-972.

NASA Contractor Report 145245

DISTRIBUTION LIST

NAS1-14346

No. of  
Copies

|  |         |
|--|---------|
| NASA Langley Research Center<br>Hampton, VA 23665<br>Attn: Report & Manuscript Control Office, Mail Stop 180A<br>Dennis L. Dicus, Mail Stop 188B | 1<br>59 |
| NASA Ames Research Center<br>Moffett Field, CA 94035<br>Attn: Library, Mail Stop 202-3   | 1       |
| NASA Dryden Flight Research Center<br>P. O. Box 273<br>Edwards, CA 93523<br>Attn: Library  | 1       |
| NASA Goddard Space Flight Center<br>Greenbelt, MD 20771<br>Attn: Library   | 1       |
| NASA Lyndon B. Johnson Space Center<br>2101 Webster Seabrook Road<br>Houston, TX 77058<br>Attn: JM6/Library                                      | 1       |
| NASA Marshall Space Flight Center<br>Huntsville, AL 35812<br>Attn: Library, AS61L  | 1       |
| Jet Propulsion Laboratory<br>4800 Oak Grove Drive<br>Pasadena, CA 91103<br>Attn: Library, Mail 111-113   | 1       |
| NASA Lewis Research Center<br>21000 Brookpark Road<br>Cleveland, OH 44135<br>Attn: Library, Mail Stop 60-3                                       | 1       |
| NASA John F. Kennedy Space Center<br>Kennedy Space Center, FL 32899<br>Attn: Library, IS-DOC-1L  | 1       |
| National Aeronautics & Space Administration<br>Washington, DC 20546<br>Attn: RW  | 1       |
| Plastics Technical Evaluation Center<br>SARPA-FR-M-D<br>Picatinny Arsenal<br>Dover, NJ 07801<br>Attn: A. M. Anzalone, Building 3401              | 1       |



NASA Contractor Report 145245

DISTRIBUTION LIST

NAS1-14346

No. of  
Copies

NASA Scientific & Technical Information Facility  
6571 Elkridge Landing Road  
Linthicum Heights, MD 21090

30 plus original